

कृत्रिम रेशों से निर्मित टायर सूत, डोरी और
टायर डोरी कपड़ा — परीक्षण के तरीके
भाग 3 भार और दीर्घीकरण लक्षण
(दूसरा पुनरीक्षण)

**Tyre Yarns, Cords and Tyre Cord
Fabrics Made from Man-Made
Fibres — Methods of Test
Part 3 Load and Elongation
Characteristics
(Second Revision)**

ICS 83.160; 59.060.01

© BIS 2023



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002
www.bis.gov.in www.standardsbis.in

FOREWORD

This Indian Standard (Part 3) (Second Revision) was adopted by the Bureau of Indian Standards, after the draft finalized by the Technical Textiles for Mobiltech Sectional Committee had been approved by the Textiles Division Council.

This standard first published in 1968 and subsequently revised in 1989. The second revision has been made in the light of experience gained since its last revision and to incorporate the following major changes:

- a) The title of the standard has been modified; and
- b) The pre-tension to the specimen in tensile testing machine has been modified.

This standard has been published in various parts. The other parts under this series are:

- Part 1 Definition of terms
- Part 2 Linear density
- Part 4 Dip pick-up
- Part 5 Heat shrinkage and heat shrinkage force
- Part 6 Wet contraction and wet contractile force
- Part 7 Heat degradation
- Part 8 Thickness
- Part 9 Sampling of tyre yarns, cords and tyre cord fabrics made from rayon
- Part 10 Creep
- Part 11 Commercial mass
- Part 12 Sampling of tyre yarns, cords and tyre cord fabrics made from polyamide
- Part 13 Static Adhesion of textile tyre cord to vulcanized rubber

The composition of the committee responsible for the formulation of this standard is listed in Annex A.

In reporting the results of a test made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 2022 'Rules for rounding off numerical values (second revision)'

Indian Standard

**TYRE YARNS, CORDS AND TYRE CORD FABRICS MADE
FROM MAN-MADE FIBRES — METHODS OF TEST
PART 3 LOAD AND ELONGATION CHARACTERISTICS**

(*Second Revision*)

1 SCOPE

This standard (Part 3) prescribes a method for determination of breaking load, elongation at break, load at specified elongation, elongation at specified load and tenacity of man-made fibre tyre yarns and cords taken from cheeses, cones, bobbins, spools, hanks, or tyre-cord fabrics.

2 REFERENCE

The standards listed below contain provisions which through reference in this text, constitute provisions of this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision and parties to agreements based on this standard are encouraged to investigate the possibility of applying the most recent editions of the standards listed below.

<i>IS No.</i>	<i>Title</i>
IS 6359 : 1971	Method for conditioning of textiles

3 SAMPLING

3.1 Sample for the lot shall be drawn so as to be representative of the lot. Sample drawn in accordance with the relevant material specification or as agreed to between the buyer and the seller shall be held to be representative of the lot.

4 CONDITIONING OF TEST SPECIMENS

4.1 Unless otherwise agreed to between the buyer and the seller, the test sample shall be conditioned to a state of moisture equilibrium from the dry side in standard atmosphere as prescribed in IS 6359.

NOTE — When a test sample under zero tension has been left in such a way as to expose, as far as possible, all portions of it to the standard atmosphere for 24 h, the test sample shall be deemed to have reached a state of moisture equilibrium

4.2 For testing of oven-dry specimens, dry the sample to constant mass by placing it in a drying oven maintained at $(105 \pm 3) ^\circ\text{C}$ and fed with air from standard atmosphere.

NOTE — Normally, complete drying of the sample is achieved in 2 h.

5 ATMOSPHERIC CONDITIONS FOR TESTING

5.1 The test shall be carried out in a standard atmosphere (*see* 4.1).

6 APPARATUS**6.1 Testing Machine**

A single strand tensile strength testing machine working on one of the following principles shall be used:

- a) Constant-rate-of-load (CRL);
- b) Constant-rate-of-traverse (CRT); or
- c) Constant-rate-of-extension (CRE).

The specimens shall break within (20 ± 2) s in case of constant-rate-of-load and constant rate-of-extension machines. In case of constant rate-of-traverse machine, the rate of traverse shall be (300 ± 15) mm/min and the load range of the machine shall be such that the observed values would be between 10 percent and 90 percent of the full scale load. The permissible error in the machine at any point in this range shall not exceed ± 1 percent. The machine shall be provided with the following:

- a) Two clamps with the following provisions to grip the specimen:
 - 1) Each clamp of the machine shall be bollard type in which the yarn is gripped between the plain-faced jaws and then makes a half-turn round a cylindrical extension of one of the jaws before passing on to the other similar clamp. The cylindrical friction surface shall be between 10 mm to 20 mm in diameter. An outline of the above type of clamp is shown in Fig. 1. The length of the specimen between points A and A' is the test length.

- 2) Each clamp shall be provided with a mechanical or pneumatic device so constructed that through its means, a specimen can be secured firmly between the jaws of the clamps so that it does not slip during the test. Also, the edge of the surface of each jaw shall be such that it would not cut or damage the specimen during testing.

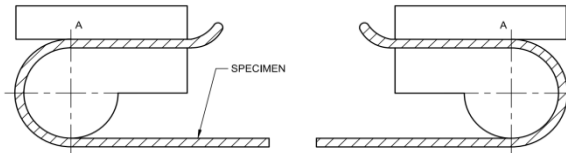


FIG. 1 RECOMMENDED GRIPPING CLAMPS

NOTE — For checking suitability of chosen clamps for testing, samples of various gauge length (namely 200 mm, 400 mm, 600 mm, 800 mm, 1 000 mm) may be stretched to break and elongation at break plotted against the gauge length to obtain graph as shown in Fig. 2.

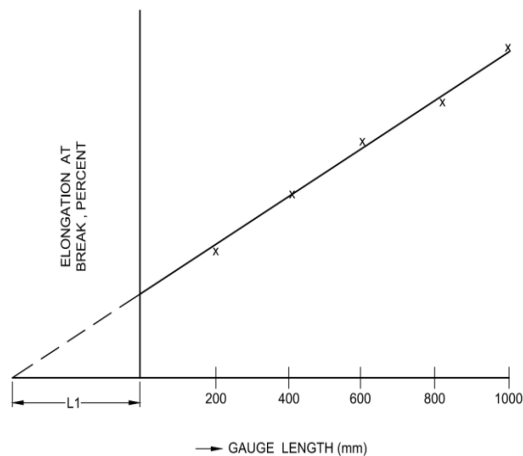


FIG. 2 SELECTION OF SUITABLE CLAMPS

If $L1$ exceeds 10 percent of gauge length to be used, the clamps or clamping surfaces are not suitable and may only be used if the parties agree.

- b) Means for applying standard pre-tension of (5 ± 1) mN/tex to the specimen when clamped (the tension device may be deadweight, a spring, or an air-actuated mechanism);
- c) Means for adjusting the distance between the clamps; and
- d) A scale or dial or autographic chart recorder graduated so as to give load, elongation at pre-determined load/break and load at specified percentage elongation.

6.2 Drying Oven

Provided with forced ventilation and capable of maintaining a temperature of (105 ± 3) °C.

7 PROCEDURE

7.1 Test on Conditioned Specimens

7.1.1 Set the clamps of the testing machine so that the distance between the clamps is (250 ± 2) mm, (500 ± 2) mm, or as agreed to between the buyer and the seller. With the help of preliminary specimens, set the machine so that the specimen breaks within (20 ± 2) s in case of constant-rate-of-load and constant-rate-of-extension machine and in case the machine is of constant-rate-of-traverse type, set it at a rate of traverse of (300 ± 15) mm/min. Take the yarn or cord from the conditioned sample and discard a first few metres of yarn or cord. Fix one end in the jaws of one clamp in such a way that the twist does not change. Apply the required pretension from the free end and secure it in the jaws of the other clamp.

7.1.2 Operate the machine and carry the test to rupture and record the breaking load, elongation at pre-determined load as required, elongation at break and load at specified percentage elongation (LASE) from the load elongation curve of the autographic chart recorder provided.

NOTES

1 If a specimen under test breaks within 1 cm of the point of contact of either jaw, or there is slippage in the jaw, the result should be recorded but not included in the final result. If such breaks exceed 10 percent of the number of specimens tested, overhaul the jaws of the clamps. If necessary, test the specimens with suitable snubbing device, namely, soft leather or paper, though under these conditions, observed values for elongation will not be comparable with those obtained with regular clamps. Give specimens of very low twist multifilament yarns of which more than 10 percent of the specimens breaks in the clamps, a twist of (120 ± 10) turns/metre prior to test for breaking load.

2 When using automated testers in the normal manner, it is usually impossible to cancel the results of defaulted tests. Such results may have a large influence on the final results. To avoid these errors, it is necessary to watch the running test and to correct the test results for any jaw breaks or other defaulted tests. Where the results are read from a digital system and not from the recording chart, the elongation at break is determined at the instant when the measured force has fallen by a predetermined percentage of the full scale value after having passed the minimum value and there will be a systematic deviation in the recorded elongation. The predetermined percentage must be agreed upon between the parties and included in the test report.

3 If yarn is tested directly from the package in automatic testers, it can result in a different relaxation state of the yarn and the test result may differ from that of a relaxed state.

7.1.3 Open both the clamps and remove the broken specimen. Test another test specimen in a similar manner, discarding at random several metres of yarn between the two successive tests. Perform minimum 10 tests or more as agreed to between the buyer and the seller. In case of sample of yarn or cord from fabrics, a minimum of 10 tests or more as agreed to between the buyer and the seller shall be carried out. The selection of test specimens shall be as agreed to between the buyer and the seller.

7.2 Test on Oven Dry Specimens

7.2.1 Mount the thread without disturbing the twist on a support which would allow the yarn or cord to contract during drying. Put the material in drying oven maintained at $(105 \pm 3) ^\circ\text{C}$ (see 4.2). Immediately after drying, mount the yarn or cord, under pre-tension, in the clamps of the tensile testing machine kept in the standard atmosphere near the oven, care should be taken to see that no change in twist occurs while the specimen is being removed from the oven to the testing machine and clamped. Carry the test to rupture as specified in 7.1.1 and 7.1.2.

7.2.2 Maintain the interval from the commencement of loading to the moment of rupture as (20 ± 2) s and the interval between the moment at which the test specimen leaves the oven and the moment at which it breaks as (30 ± 2) s.

7.2.3 Discard unused portion of yarn or cord outside the oven before mounting a fresh specimen. Perform a minimum of 10 tests or more as agreed to between the buyer and the seller.

8 CALCULATIONS

8.1 Breaking Load

Calculate the mean breaking load in newtons from all the observed values and the coefficient of variation.

8.2 Elongation

Calculate the mean elongation at pre-determined load as required and at break in percent from all the observed values.

8.3 Load at Specified Percentage Elongation

Calculate the mean load at specified percentage elongation in newtons as required.

8.4 Tenacity

Calculate the tenacity by the following formula:

Tenacity, in cN/tex =

$$\frac{\text{Mean breaking load in newtons}}{\text{Mean linear density in tex}} \times 100$$

NOTE — The linear density of yarn or cord shall be determined from the same package in accordance with Part 2 of this standard.

9 REPORT

9.1 The test report shall include the following:

- a) Description of the material tested;
- b) Name of the instrument and capacity;
- c) Mean time for break or rate-of-traverse;
- d) The type of test (conditioned or oven dry);
- e) Specimen length;
- f) Number of tests performed;
- g) Mean breaking load and coefficient of variation, if required;
- h) Mean elongation at a predetermined load, if required;
- j) Mean elongation at break;
- k) Mean load at specified percentage elongation (LASE), if required;
- m) Mean tenacity; and
- n) Temperature used for conditioning, that is, $(27 \pm 2) ^\circ\text{C}$ or $(20 \pm 2) ^\circ\text{C}$.

ANNEX A
(Foreword)

COMMITTEE COMPOSITION

Technical Textiles for Mobiltech Sectional Committee, TXD 38

<i>Organization</i>	<i>Representative(s)</i>
Northern India Textile Research Association, Ghaziabad	DR M. S. PARMAR (<i>Chairperson</i>)
Arvind Limited, Ahmedabad	SHRI PABITRA SAHOO SHRIMATI MAMTA CHAUDHARY (<i>Alternate</i>)
Autoliv India Ltd, Mysore	SHRI DEEPAK RAO
BMD Pvt Ltd, Banswara	DR NAVDEEP K. PHOGAT
Century Enka Limited, Pune	SHRI MILIND ASHTAPUTRE SHRI KRISHNAGOPAL LANDSARIA (<i>Alternate</i>)
Federation of Indian Chambers of Commerce and Industry, New Delhi	SHRI TUSHAR PATEL SHRI MAHENDRA HADA (<i>Alternate</i>)
Garware Technical Fibres Limited, Pune	DR ABHAY GUPTA
ICAR - Central Institute for Research on Cotton Technology, Mumbai	DR G. KRISHNA PRASAD DR A. ARPUTHARAJ (<i>Alternate</i>)
Indian Technical Textile Association, Mumbai	DR ANUP RAKSHIT SHRI ANKIT DESAI (<i>Alternate</i>)
Kusumgar Corporates Pvt Ltd, Mumbai	SHRI SIDDHARTH Y. KUSUMGAR DR M. K. TALUKDAR (<i>Alternate</i>)
Metro Tyres Ltd, Ludhiana	SHRI SAMIR MAYRA
Northern India Textile Research Association, Ghaziabad	SHRIMATI NEHA KAPIL
Office of the Textile Commissioner, Mumbai	SHRI V. K. KOHLI SHRI HUMAYUN. K. (<i>Alternate</i>)
SGS Limited, Gurugram	SHRI GAURAV SARSWAT SHRI ASHISH SARSWAT (<i>Alternate</i>)
SRF Limited, Gurugram	SHRI ANKUR SHARMA SHRI BHARATH KUMAR (<i>Alternate</i>)
Testtex India Laboratories Pvt Ltd, Mumbai	SHRIMATI MEETA SHINGALA SHRI DIPTI RANJAN PRUSTY (<i>Alternate</i>)
Textiles Committee, Mumbai	SHRI KARTIKAY DHANDA SHRIMATI SHILPI CHAUHAN (<i>Alternate</i>)
The Synthetic and Art Silk Mills Research Association, Mumbai	SHRI SANJAY SAINI SHRI PREMNATH SURWASE (<i>Alternate</i>)
Uniproducts Pvt Ltd, Rewari	SHRI VIKAS YADAV
VOICE, New Delhi	SHRI M. A. U. KHAN SHRI B. K. MUKHOPADHYAY (<i>Alternate</i>)
BIS Directorate General	SHRI J. K. GUPTA, SCIENTIST 'E'/DIRECTOR AND HEAD (TEXTILES) [REPRESENTING DIRECTOR GENERAL (<i>Ex-officio</i>)]

Member Secretary
SHRI BANOTHU RANGA
SCIENTIST 'B'/ASSISTANT DIRECTOR
(TEXTILES), BIS

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website-www.bis.gov.in or www.standardsbis.in.

This Indian Standard has been developed from Doc No.: TXD 38 (18872).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 th Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 th Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Plot No. E-9, Road No.-8, MIDC, Andheri (East), Mumbai 400093	{ 2821 8093

Branches : AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. CHANDIGARH. CHENNAI. COIMBATORE. DEHRADUN. DELHI. FARIDABAD. GHAZIABAD. GUWAHATI. HIMACHAL PRADESH. HUBLI. HYDERABAD. JAIPUR. JAMMU & KASHMIR. JAMSHEDPUR. KOCHI. KOLKATA. LUCKNOW. MADURAI. MUMBAI. NAGPUR. NOIDA. PANIPAT. PATNA. PUNE. RAIPUR. RAJKOT. SURAT. VISAKHAPATNAM.