
रंग रोगन, वार्निश और संबंधित उत्पादों के लिए
नमूने और परीक्षण की पद्धति
भाग 1 तरल रंग रोगन पर परीक्षण (सामान्य और भौतिक)

अनुभाग 1 नमूनाकरण
(चौथा पुनरीक्षण)

**Methods of Sampling and Test for
Paints, Varnishes and Related
Products**

**Part 1 Tests on Liquid Paints (General
and Physical)**

Section 1 Sampling
(*Fourth Revision*)

ICS 87.040

© BIS 2023



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002
www.bis.gov.in www.standardsbis.in

FOREWORD

This Indian Standard (Part 1/Sec 1) (Fourth Revision) was adopted by the Bureau of Indian Standards, after the draft finalized by the Paints, Varnishes, and Related Products Sectional Committee had been approved by the Chemical Division Council.

This standard (Part 1/Sec 1) is one of a series dealing with methods of sampling and test for paints, varnishes, and related products. The other sections of this Indian Standard (Part 1) are:

Section 2 Preliminary examination and preparation of samples for testing;

Section 3 Preparation of panels;

Section 4 Brushing test;

Section 5 Consistency;

Section 6 Flash point;

Section 7 Mass per litres determination of density Pycnometer method; and

Section 8 Pigments and extenders determination of pH value of aqueous suspension.

This standard prescribes methods of sampling for paints, varnishes and related products. Correct sampling forms the basis for the subsequent tests and their results. The various sampling procedures need to be carried out with great care by operators having the required knowledge and experience. This standard intended to supplement general instructions to obtaining uniform and samples of convenient size and adequately representative of the product being sampled.

In the third revision, this standard superseded 3 of IS 82 : 1973 'Method of sampling and test for thinners and solvent for paints (*first revision*)', IS 85 : 1950 'Methods of test for oil pastes for paints' and IS : 197-1969 'Methods of sampling and test for varnishes and lacquers (*second revision*)'.

This revision has taken to bring out the standard in the latest style and format of the Indian Standard. It also incorporates amendments issued to the last version of the standard. In addition, the following changes have been made:

- a) Terminology of batch, lot, individual sample, representative sample, etc has been added for better understanding;
- b) Valve sampling tube and bottom or zone sampler apparatus have been added;
- c) Criteria for storing sample has been prescribed; and
- d) References of Indian standards have been updated wherever required.

The composition of the committee responsible for the formulation of this standard is listed in Annex A.

In reporting the result of a test or analysis made in accordance with this standard, If the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'.

Indian Standard

**METHODS OF SAMPLING AND TEST FOR PAINTS,
VARNISHES AND RELATED PRODUCTS**

PART 1 TESTS ON LIQUID PAINTS (GENERAL AND PHYSICAL)

SECTION 1 SAMPLING

(Fourth Revision)

1 SCOPE

This standard prescribes methods of sampling for paints, varnishes and related products. It is one of a series of standards dealing with sampling and testing of these products. This standard aims at obtaining uniform samples of convenient size and adequately representative of the product being sampled. The sample or samples so obtained are suitable for examination and preparation prior to testing.

2 REFERENCES

The standards listed below contain provisions, which through reference in this text, constitute provisions of and necessary adjuncts to this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision and parties to agreements based on this standard are encouraged to investigate the possibility of applying the most recent editions of the standards listed below:

<i>IS No.</i>	<i>Title</i>
IS 1303 : 1983	Glossary of terms relating to paints (<i>second revision</i>)

3 TERMINOLOGY

For the purpose of this standard, the definitions given in IS 1303 and following shall apply.

3.1 Batch

Definite quantity of material produced under uniform conditions.

3.2 Lot

In a single consignment, all the packages containing paints, varnishes and related products of the same type, grade and form, and drawn from the same batch of manufacture, shall constitute a lot. If the consignment consists of packages containing paints, varnishes and related products of different types, grades and forms, packages containing paints, varnishes and related products of same type, grade, form and batch of manufacture shall be grouped together and each such group shall constitute a separate lot.

3.3 Individual Sample

Part of a product taken from a bulk material by one sampling operation.

3.4 Representative Sample

Sample which complies, within the precision of the test methods used, in all of its characteristic features with the material sampled.

3.5 Average Sample

Mixture of equivalent portions of individual sample.

3.6 Top Sample

Individual sample taken at or near the surface of a material.

3.7 Middle Sample

Individual sample taken at a level corresponding to approximately half of the total volume below the surface.

3.8 Bottom Sample

Individual sample taken at or near the lowest level of a material.

3.9 All-layer Sample

Individual sample taken through the total height of the material, so that all layers are collected proportionately.

3.10 Composite Sample

Individual sample taken from a number of different levels of a material

3.11 Intermittent Sample

Individual sample taken intermittently from a flow of material.

3.12 Continuous Sample

Sample taken continuously from a flow of material.

3.13 Storage Sample

Individual sample average sample or continuous sample which is taken and stored for a specified period for reference purpose.

4 TYPES OF PRODUCTS

The sampling procedures appropriate for use with paints, varnishes and related products depend on the nature and the physical properties of the products. The following types of products may conveniently be distinguished.

4.1 Type A

Fluid products consisting of a single homogeneous liquid phase, such as varnishes and thinners.

4.2 Type B

Fluid products consisting of two liquid phases, such as emulsions.

4.3 Type C

Fluid products consisting of one or two liquid phases together with one or more solid phases. Such products are normally called 'paints' and include 'emulsion' paints.

4.4 Type D

Viscous products (which usually consist of one or more solid phases with small amounts of a liquid phase) such as putties, mastics, lutes, cements and pigment pastes in oil or varnish. This type also includes very viscous resinous materials.

4.5 Type E

Products in powder form.

5 SAMPLING EQUIPMENT

5.1 General

The choice of sampling device depends on the type

of material being sampled, the type of container, the level to which the container is filled and the sample size required. The sampling tools in general used for sampling raw materials, may also be used for sampling finished products. Sampling equipment is required for two separate operations

- a) Mixing the product to make it as homogeneous as possible; and
- b) Taking a truly representative sample.

5.2 Materials and Design

All sampling equipment shall be made of material not subject to deterioration, unaffected by the products being sampled and incapable of contaminating the sample. The design of the equipment shall take into account convenience in use and ease of cleaning (for example, any grooves, acute internal angles, or areas which are inaccessible or difficult to inspect for cleanness, shall be avoided).


5.3 Apparatus for Mixing

Broad-bladed stirrers of suitable length to reach the bottom of the container being sampled. Mechanical stirrers may also be used.

NOTE — In certain circumstances, when stirring a product of low flash point or where an explosive hazard exists the only metal permitted is bronze.

5.4 Apparatus for Taking Samples

5.4.1 *Sampling Tubes Glass or Metal, (see Fig. 1).*

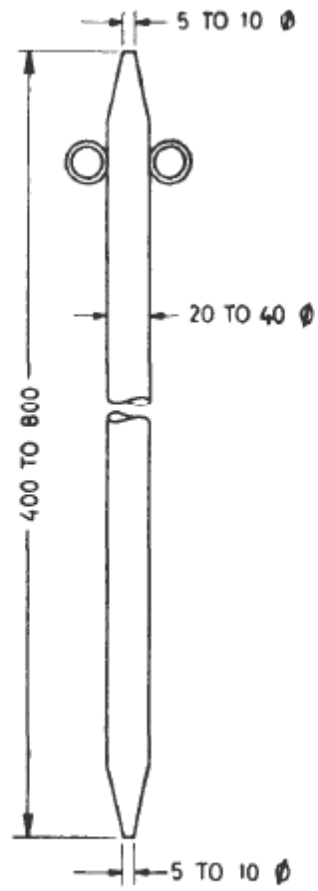

All dimensions in millimetres.

FIG. 1 SUITABLE DESIGN OF SAMPLING TUBE

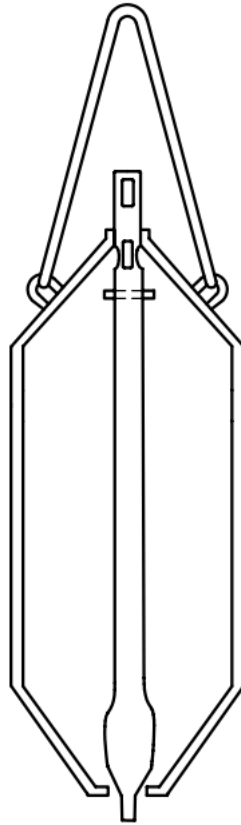


FIG. 2 BOTTOM OR ZONE SAMPLER

5.4.2 Small Dip Cans

5.4.3 Weighted Sampling Cans, with valve closures, for taking samples at all levels.

5.4.4 Scoops, Triers or Spatulas

5.4.5 Valve Sampling Tube

5.4.6 Bottom or Zone Sampler, (see Fig. 2) particularly suitable for taking sample from large containers.

5.5 Sample Containers

New containers of suitable size and with large apertures shall be used. These may be:

- a) Metal containers of which the interior is not coated with varnish and which are fitted with tight metal closures; and
- b) Glass containers which can be tightly closed with closures which are not affected by the sample. Amber glass provides a partial protection against the action of light and the contents can be further shielded, if necessary, by an external opaque covering or packaging.

5.6 Labels

Suitable labels or other means of marking or

identifying samples shall be provided.

5.7 Cleaning of Sampling Equipment

Strict cleanliness must always be observed. All sampling apparatus must be dry and free from residue, so as not to contaminate the sample. After each use, the apparatus shall be thoroughly cleaned with the aid, if necessary, of a brush or clean cotton rag, and shall then be rinsed with a suitable solvent.

6 SAFETY PRECAUTIONS

A number of hazards may arise in the course of sampling. Many volatile products which are flammable or toxic may be present and hazards may arise from sparking or static electricity. The samplers must always be informed (this must be stated on the labels or packaged products) of the dangers arising from the nature of the products and must handle them with due care, using protective equipment, if required.

NOTE — All statutory regulations concerning safety and hygiene shall be complied with.

7 TYPES OF SAMPLING

There are two main types of sampling, which may be carried out corresponding to the following stages:

- a) When the manufacture of the product has been completed but the product is still in the final manufacturing vessels, or when it is being transferred into the delivery containers (cans, drums, barrels, etc); and
- b) When sampling from the delivery containers which may also be bulk transport containers. Such sampling shall take place at the manufacturer's premises unless, by special agreement between the purchaser and the vendor, sampling is permitted at the purchaser's premises, in which case the product after receipt must not have been treated in any way.

8 METHODS OF SAMPLING

8.1 When the type of sampling specified in 7 (a) is required, the following procedures shall be applicable.

8.1.1 For Fluid Products (Types A, B and C)

When the sample is to be taken directly from the final manufacturing vessel, the product shall first be thoroughly stirred (*see* Note 1) and the sample taken by means of a suitable weighted sampling can from different levels (*see* Note 2) in the vessel. When the sample is to be taken in the course of transferring the product into the delivery containers, it shall be made up from small sub-samples taken at regular intervals during the filling process. In the former case, it is important to strain the sample before filling the sample container, using the same procedure as normally used when filling the delivery containers.

NOTES

1 Clear varnishes and similar products in settling tanks shall not be stirred before sampling.

2 An additional safeguard to check the relative densities of samples taken from different levels and if these are not within

the agreed tolerances, to continue stirring until the agreed tolerances are met.

8.1.2 For Viscous or Powdery Products (Types D and E)

The product shall be inspected in the final manufacturing vessel and, if uniform in appearance, the sample shall be taken from various parts of the bulk using a sampling tube, scoop or trier. Alternatively, a number of small samples can be taken at regular intervals during filling of the delivery containers.

8.2 When the type of sampling specified in 7 (b) is required, the following procedures shall be applicable.

8.2.1 For Fluid Products (Types A, B and C)

If the product is supplied in a bulk container, the same procedure applies as in **8.1.1** for sampling from the final manufacturing vessel. However, in the absence of a circulating pump or other means of agitation, it is usually necessary to take approximately equal size samples at different levels (*see* Note) in order to obtain a representative sample of the whole.

NOTE — An additional safeguard to check the relative densities of samples taken from different levels and if these are not within the agreed tolerances, to continue stirring until the agreed tolerances are met.

8.2.1.1 If the product is supplied in a consignment of containers, the total number of containers shall be noted and then a selection made at random of the containers for sampling. It is recommended that approximately $\sqrt{n}/2$ containers shall be sampled, where n is the total number of containers in the consignment (*see* Table 1). Only sound, unopened containers shall be chosen for sampling, unless it is desired specifically to examine damaged or opened containers.

Table 1 Sampling Scheme

SI No.	Number of Containers in Consignment (n)	Number of Containers to be Sampled
(1)	(2)	(3)
i)	2 - 10	2
ii)	11 - 20	3
iii)	21 - 35	4
iv)	36 - 50	5
v)	51 - 70	6
vi)	71 - 90	7
vii)	91 - 125	8
viii)	126 - 160	9
ix)	161 - 200	10

and thereafter one container for every additional 58 containers.

The following procedures shall then be adopted:

- a) Each selected container shall be opened in turn and examined for the presence of surface skin, separation of the contents (for example, water or solvent) or the presence of foreign matter;
- b) After completing the removal of any surface skin if present, the stirrer shall be inserted into the container and the extent and type of settling, namely soft, hard or hard-dry, shall be noted. The presence or absence of a gel shall also be noted, care being taken not to confuse gelling and thixotropy (*see* Note);

NOTE — Both thixotropic and gelled Paints and varnishes have a jelly-like consistency, but whereas the consistency of the former is markedly reduced by stirring or shaking, the consistency of a gelled paint or varnish cannot be reduced in this way.

- c) Any settled pigment shall be redispersed with the stirrer and the ease of redispersion noted. The closure shall then be replaced securely, the container shall be inverted and left inverted while the other containers are examined. Finally, the containers shall be shaken and rolled to effect complete redispersion and re-incorporation of the pigment, preferably using mechanical means;
- d) The containers shall be re-opened and examined for uniformity. Successive stirring, shaking and rolling shall then be continued until the contents are homogeneous, the bottom end of the stirrer being examined for undispersed pigment from time to time during the stirring, The time required to attain uniformity shall be noted; and
- e) When the contents of the containers have become homogeneous, they shall be sampled, using the small dip can to transfer the product to the sample container, which shall be filled so that there is an ullage (air-space) of about 5 percent. The container sampled and the sample container shall be closed and the sample container shall be cleaned on the outside and immediately labelled in accordance with 9.1.

8.2.2 For Viscous Products (Type D) — These products are normally supplied in wide-aperture

containers. Examine the condition of all the containers and select at random for sampling an appropriate number in accordance with Table 1. Open each of the selected containers, remove any protective covering and inspect the contents for homogeneity or separation of phases (for example, phases of oil, solvent or water). If the product appears homogeneous, or is made so by stirring, take a sample from the whole depth of the product in each selected container, using a suitable metal sampling tube or other suitable equipment, and place it in a suitable sample container which shall be filled so that there is an ullage (air-space) of about 5 percent. Close the sample container and label it in accordance with 9.1.

8.2.3 For Powdery Products (Type E) — These products are normally supplied in sacks, paper or plastics bags, drums, barrels or plywood containers. Examine the condition of all the packages and select at random for sampling an appropriate number in accordance with Table 1. Open each of the selected packages and take, from various parts of each package, small portions of the product by means of a suitable sampling instrument and close the packages. Place these portions in a suitable sample container, close the container, mix the contents thoroughly by shaking, and label in accordance with 9.1.

9 LABELLING, SEALING AND STORAGE OF SAMPLES

9.1 Labelling

The containers shall be labelled as soon as the samples are taken; the labels shall bear all the necessary information to enable the samples to be identified without dispute. The labels and marking ink used shall be capable of withstanding moisture and any solvents contained in the sample. The label shall not be attached to the stopper, but to the neck or body of the containers.

It is recommended that the following particulars, whatever applicable shall be given on the label:

- a) The name of the manufacturer code, if necessary, and a description of the product;
- b) The quality and particulars of the consignment;
- c) The reference number of the batch, storage tank, barrel, etc;
- d) The dates of manufacture and of sampling;
- e) The total number of samples taken from the consignment;
- f) The designation and reference number of the sample (where the samples are drawn

from a certain number of selected containers, the latter shall be numbered);

- g) The consignor;
- h) The place of sampling;
- j) The name of the sampler; and
- k) Any hazard symbols necessary

9.2 Sealing

After a sample container has been closed and

contents and label cannot be removed without breaking the seal.

9.3 Storage

The storage sample shall be stored under suitable storage conditions in an airtight container and, where required, protected from light and moisture for the period specified, taking into consideration all relevant safety regulations.

ANNEX A
(Foreword)

COMMITTEE COMPOSITION

Paints, Varnishes and Related Products Sectional Committee, CHD 20

<i>Organization</i>	<i>Representative(s)</i>
Institute of Chemical Technology, Mumbai	PROF P. A. MAHANWAR, (Chairperson)
Akzo Nobel Coatings India Pvt Ltd	SHRI SANATAN HAJRA
Asian Paints Ltd, Mumbai	SHRI RAJEEV KUMAR GOEL SHRI RAJES BARDIA (<i>Alternate</i>)
Berger Paints India Ltd, Howrah	SHRI TAPAN KUMAR DHAR SHRI SWAGATA CHAKROBORTY (<i>Alternate</i>)
Bharat Heavy Electricals Ltd, Tiruchirapalli	SHRI K. SRINIVASAN SHRI V. RAJESHKHARAN (<i>Alternate</i>)
Central Building Research Institute, Roorkee	DR SUKHDEO R. KARADE DR P. C. THAPLIYAL (<i>Alternate</i>)
Central Public Works Dept, New Delhi,	SHRI AMAR SINGH SHRI M. L. PRASAD (<i>Alternate</i>) SHRI DIVAKAR AGRAWAL (<i>Alternate</i>)
Consumer Voice, New Delhi	SHRI M. A. U. KHAN
Controllerate of Quality Assurance (Materials), Ministry of Defence (DGQA), Kanpur	DR GURBACHAN SINGH SHRI A. K. PATRA (<i>Alternate</i>)
Engineers India Limited, New Delhi	SHRI S. GHOSHAL SHRI A. SATYA SRIDHAR (<i>Alternate</i>)
Harcourt Butler Technical University, Kanpur	PROF P. K. KAMANI PROF ARUN MAITHANI (<i>Alternate</i>)
Indian Institute of Technology, Mumbai	PROF SMRUTIRANJAN PARIDA
Indian Paints Association, Kolkata	SHRI SUBROTO BANERJEE DR M. B. GUHA (<i>Alternate</i>)
Indian Small Scale Paint Association	SHRI MUKESH GOYAL SHRI H. SATHYANARAYAN (<i>Alternate I</i>) SHRI NIRAV RAVESHIA (<i>Alternate II</i>)
Institute of Chemical Technology, Mumbai	PROF V. V. SHERTUKADE
J K Cement Limited, Kanpur	SHRI RANA PRATAP SINGH DR PRITI PILLAY (<i>Alternate</i>)
Kansai Nerolac Paints Ltd, Mumbai	SHRI LAXMAN NIKAM SHRI MANOJ KUMAR SOMANI (<i>Alternate</i>)
Meta Chem Paints and Adhesives Private Limited, Nashik	SHRI BISWANATH PANJA SHRI HEMANT KULKARNI (<i>Alternate</i>)

<i>Organization</i>	<i>Representative(s)</i>
Ministry of Defence, Department of Standardization, New Delhi	LT COL PRAVEEN DEO SHRI V. K. CHHABRA (<i>Alternate</i>)
Ministry of Industry, New Delhi	SHRI NAND LAL
National Test House (ER), Kolkata	SHRIMATI P. NATARAJAN DR A. B. MONDAL (<i>Alternate</i>)
Naval Materials Research Laboratory (NMRL), Thane	DR T. K. MAHATO DR G. GUNASEKARAN (<i>Alternate</i>)
Office of the Micro Small & Medium Enterprises (MSME), New Delhi	SHRIMATI M. ANNABACKIAM SHRIMATI M. S. RAMMIYA (<i>Alternate</i>)
Paint and Coating Technologists Association, Kanpur	SHRI USHENDRA SINGH SHRI VIVEK KUMAR SAXENA (<i>Alternate</i>)
Pidilite Industries Ltd, Mumbai	SHRI RAMESH KASHYAP SHRI SUSHANT PANGAM (<i>Alternate</i>)
Research Designs & Standards Organization, Lucknow	SHRI P. K. BALA SHRI K. P. SINGH (<i>Alternate</i>)
Shriram Institute for Industrial Research, Delhi	SHRI A. K. MAJUMDAR
SSPC India Chapter, Kolkata	DR BUDDHADEB DUARI SHRI ANIL SINGH (<i>Alternate</i>)
The Shipping Corporation of India Ltd, Mumbai	SHRI N. K. TRIPATHI SHRI SUSHIL ORAON (<i>Alternate</i>)
In Personal Capacity (<i>Flat 1303, Blooming Heights, Pacific Enclave, Powai, Mumbai 400076</i>)	DR B. P. MALLIK
In Personal Capacity (<i>2, Block Mann Street, Kolkata, West Bengal, 700013</i>)	DR SUNIL KUMAR SAHA
BIS Directorate General	A. K. LAL SCIENTIST 'F'/DIRECTOR AND HEAD (CHEMICAL) [REPRESENTING DIRECTOR GENERAL, BIS (<i>Ex-officio</i>)]

Member Secretary
SHRI PUSHPENDRA KUMAR
SCIENTIST 'B'/ASSISTANT DIRECTOR
(CHEMICAL), BIS

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website- www.bis.gov.in or www.standardsbis.in

This Indian Standard has been developed from Doc No.:CHD 20 (20407).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002
Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 th Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 th Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 { 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 { 2254 1216
Western : Plot No. E-9, Road No.-8, MIDC, Andheri (East), Mumbai 400093	{ 2821 8093

Branches : AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. CHANDIGARH. CHENNAI. COIMBATORE. DEHRADUN. DELHI. FARIDABAD. GHAZIABAD. GUWAHATI. HIMACHAL PRADESH. HUBLI. HYDERABAD. JAIPUR. JAMMU & KASHMIR. JAMSHEDPUR. KOCHI. KOLKATA. LUCKNOW. MADURAI. MUMBAI. NAGPUR. NOIDA. PANIPAT. PATNA. PUNE. RAIPUR. RAJKOT. SURAT. VISAKHAPATNAM.