# इस्पात के तप्त बेलित और स्लिट टी सरिए — आयाम और गुण

IS 1173: 2024

(तीसरा पुनरीक्षण)

# Hot Rolled and Slit Steel Tee Bars — Dimensions and Properties

(Third Revision)

ICS 77.140.70

© BIS 2024



भारतीय मानक ब्यूरो

BUREAU OF INDIAN STANDARDS मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002 MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG NEW DELHI - 110002

www.bis.gov.in www.standardsbis.in

#### **FOREWORD**

This Indian Standard (Third Revision) was adopted by the Bureau of Indian Standards, after the draft finalized by the Structural Engineering and Structural Sections Sectional Committee had been approved by the Civil Engineering Division Council.

This standard was first published in 1957 covering a wide range of hot rolled and slit tee bars and was subsequently revised in 1967 and 1978, which covered slit tee bars to be produced by slitting some of the Indian Standard light weight, medium weight and H-beam sections.

In the preparation of this standard, the sectional committee has kept in view the manufacturing and trade practices followed in the country in this field.

In this revision, the following modifications have been effected:

- a) New clause for customization of sizes through optimum flange width, beam depth, thicknesses of flange and web has been added; and
- b) References clause has been updated.

This standard also aims at satisfying some Sustainable Development Goals by United Nations, especially Goal 9 'Industry, innovation and infrastructure', particularly its target **9.1**.

The composition of the Committee responsible for the formulation of this standard is given in Annex A.

For the purpose of deciding whether a particular requirement of this standard is complied with the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS 2:2022 'Rules for rounding off numerical values (*second revision*)'. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

#### Indian Standard

# HOT ROLLED AND SLIT STEEL TEE BARS — DIMENSIONS AND PROPERTIES

(Third Revision)

#### 1 SCOPE

This standard lays down the nominal dimensions, weight and basic sectional properties of hot rolled and slit steel tee bars.

#### 2 REFERENCES

The standards given below contain provisions which through reference in this text, constitute provision of this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision and parties to agreements based on this standard are encouraged to investigate the possibility of applying the most recent edition of these standards:

IS No.	Title
IS 808 : 2021	Hot rolled steel beam, column, channel and angle sections — Dimensions and properties (fourth revision)
IS 1852 : 1985	Specification for rolling and cutting tolerances for hot-rolled steel products (fourth revision)
IS 2062 : 2011	Hot rolled medium and high tensile structural steel — Specification (seventh revision)

#### 3 TERMINOLOGY

For the purpose of this standard, the definitions given in IS 2062 and the following shall apply.

- **3.1 Y-Y Axis** A line passing through the centre of gravity of the profile of the section, parallel to the axis of the web of the section.
- **3.2 Z-Z Axis** A line passing through the centre of gravity of the profile of the section and at right angles to the Y-Y axis.

#### 4 SYMBOLS

Letter symbols used in this standard have been indicated in Fig. 1, Fig. 2 and Table 1. Other letter

symbols used in the standard have the meaning indicated against each as given below:

а	Sectional	area	in	sq	mm	

$$C_{zz}$$
 Distance of centre of gravity from top of flange

$$e_{yy}$$
 Distance of extreme fibre from the Y-Y axis

$$e_{zz}$$
 Distance of extreme fibre from the Z-Z axis

$$I_{yy}$$
 Moment of inertia about the Y-Y axis

$$I_{zz}$$
 Moment of inertia about the Z-Z axis

$$r_{yy}$$
  $\sqrt{\frac{I_{yy}}{a}}$  = Radius of gyration about the

$$r_{zz}$$
  $\sqrt{\frac{I_{zz}}{a}}$  = Radius of gyration about the Z-Z axis

w Calculated weight in kg/m = 
$$(0.75 a)$$

$$Z_{yy}$$
  $\frac{I_{yy}}{e_{yy}}$  = Modulus section about the Y-Y

$$Z_{zz}$$
  $\frac{I_{zz}}{e_{zz}}$  = Modulus of section about the

#### **5 CLASSIFICATON**

- **5.1** Indian Standard hot-rolled steel tee bars may be classified as follows:
  - a) Indian Standard rolled normal tee bars (ISNT);
  - b) Indian Standard rolled deep legged tee bars (ISDT);
  - Indian Standard slit light weight tee bars (ISLT);
  - d) Indian Standard slit medium weight tee bars (ISMT); and
  - e) Indian Standard slit tee bars from H-sections (ISHT).

To access Indian Standards click on the link below:

**5.2** For shop marking and drawing office purposes, the following abbreviated reference symbols may also be permitted provided specific understanding exists between the fabricator, the producer and the drawing office that members designated by these symbols refer only to Indian Standard sections:

Sl No.	Classification	Abbreviated Reference Symbols
(1)	(2)	(3)
i)	ISNT	NT
ii)	ISDT	DT
iii)	ISLT	LT
iv)	ISMT	MT
v)	ISHT	HT

#### **6 DIMENSIONS AND PROPERTIES**

- **6.1** Nominal dimensions and weight of Indian Standard tee bars shall be as given in Table 1.
- **6.2** The tolerances on the dimensions shall be specified in IS 1852.
- **6.3** The customization of sizes through optimum flange width, beam depth, thicknesses of flange and web will enable cost savings on the overall steel take off in addition to the reliability of connections achieved. A new range of sections suiting to the need of the design requirements can be produced based on the formulae to calculate the geometrical sectional properties as per Annex A and Annex B of IS 808 that fulfils the design criteria.

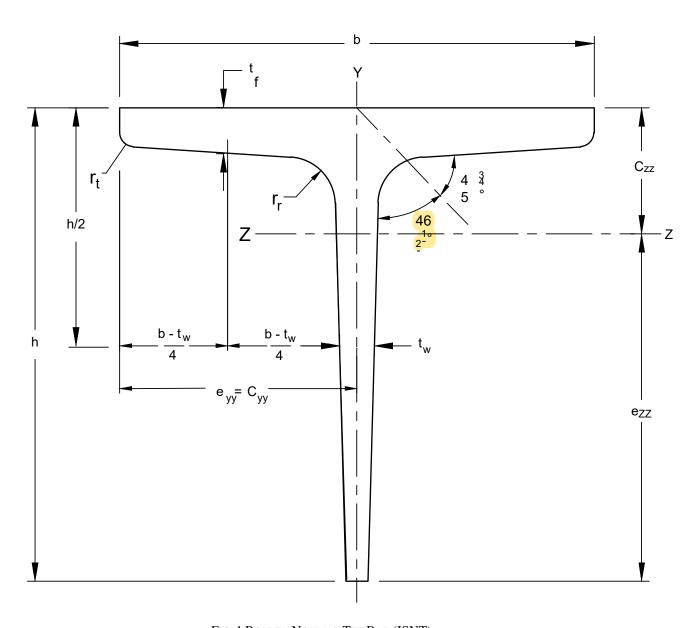


Fig. 1 Rolled Normal Tee Bar (ISNT)

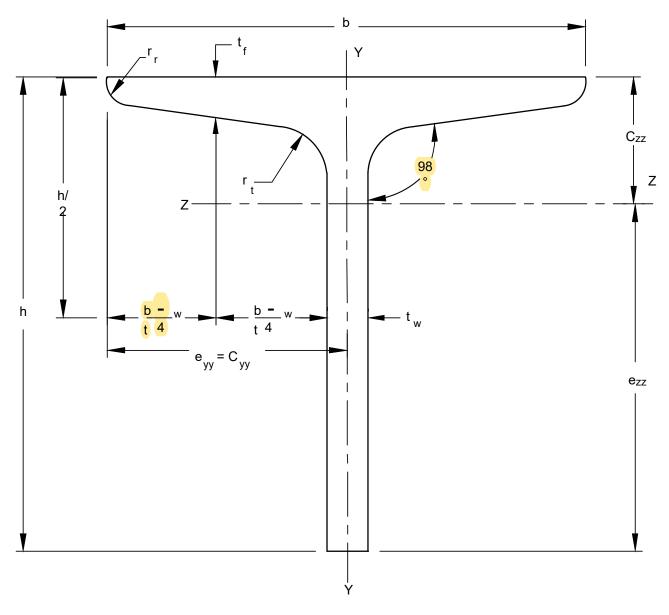


Fig. 2 Slit Tee Bar and Deep Legged Tee Bar

Table 1 Nominal Dimensions, Weight and Geometrical Properties of Indian Standard Tee Bars

(Clauses  $\underline{4}$  and  $\underline{6.1}$ )

Sl No.	Designation	Weight	Sectional Area	Size (Nominal)	Thickness of Web	Thickness of Flange	Radius at Root	Radius at Toe	Slope of Flange	Centre of Gravity Position	Moment	of Inertia		lii of ation	Moduli (	of Section
		(w)	(a)	$(h \times b)$	$(t_w)$	$(t_f)$	$(r_r)$	$(r_t)$	(D°)	$(C_{zz})$	$I_{zz}$	$I_{yy}$	$r_{\rm zz}$	$r_{yy}$	$Z_{zz}$	$Z_{yy}$
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)	(14)	(15)	(16)	(17)
		kg/m	mm <sup>2</sup>	$mm \times mm$	mm	mm	mm	mm		mm	$10^6\mathrm{mm}^4$	$10^6\mathrm{mm}^4$	mm	mm	$10^3\mathrm{mm}^3$	$10^3\mathrm{mm}^3$
						Indian S	Standard 1	Normal T	ee Bars							
i)	ISNT 20	1.1	145	20 × 20	4.0	4.0	4.0	3.0		6.0	0.005	0.002	5.8	4.1	0.3	0.2
ii)	ISNT 30	1.8	226	30 × 30	4.0	4.0	5.0	3.5		8.2	0.018	0.008	8.9	5.9	0.8	0.5
iii)	ISNT 40	3.5	445	40 × 40	6.0	6.0	5.5	4.0		11.4	0.061	0.029	11.8	8.1	2.1	1.5
iv)	ISNT 50	4.4	566	50 × 50	6.0	6.0	6.0	4.0	(See <u>Fig. 1</u> )	13.5	0.123	0.057	14.7	10.1	3.4	2.3
v)	ISNT 60	5.4	685	60 × 60	6.0	6.0	6.5	4.5		15.6	0.214	0.097	17.7	11.9	4.8	3.2
vi)	ISNT 75	10.0	1 270	75 × 75	9.0	9.0	8.0	5.5		20.4	0.620	0.292	22.1	15.2	11.4	7.8
vii)	ISNT 100	14.9	1 900	100 × 100	10.0	10.0	9.0	6.0		26.2	1.64	0.768	29.4	20.1	22.2	15.4
viii)	ISNT 150	22.7	2 890	150 × 150	10.0	10.0	10.0	7.0		36.1	5.41	2.50	43.3	29.4	47.5	33.4
	Indian Standard Deep Legged Tee Bars															
ix)	ISDT 100	8.1	1 040	100 × 150	5.8	10.0	8.0	4.0	98°	30.3	0.990	0.096	30.9	9.6	14.2	3.8
x)	ISDT 150	15.7	2 000	150 × 75	8.0	11.6	9.0	4.5	98°	47.5	4.50	0.370	47.5	13.6	43.9	9.9

**Table 1** (*Concluded*) IS 1173 : 2024

Sl No.	Designation	Weight	Sectional Area	Size (Nominal)	Thickness of Web	Thickness of Flange	Radius at Root	Radius at Toe	Slope of Flange	_	-	_	Flange Gravi	Centre of Gravity Position	Moment of Inertia		y		Radii of Gyration		Moduli of Section	
		(w)	(a)	$(h \times b)$	$(t_w)$	$(t_f)$	$(r_r)$	$(r_t)$	(D°)	$(C_{zz})$	$I_{zz}$	$I_{\rm yy}$	$r_{\rm zz}$	$r_{yy}$	$Z_{zz}$	$Z_{yy}$						
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)	(14)	(15)	(16)	(17)						
	Indian Standard Slit Light Weight Tee Bars*																					
xi)	ISLT 200	28.4	3 620	200 × 165	8.0	12.5	16.0	8.0	98°	47.8	12.7	3.58	59.2	31.5	83.3	43.4						
xii)	ISLT 250	37.5	4 780	250 × 180	9.2	14.1	17.0	8.5	98°	64.0	27.7	5.32	76.2	33.4	149.2	59.1						
					In	dian Standaı	rd Slit Me	edium Wei	ght Tee Bai	rs†												
xiii)	ISMT 50	5.8	735	50 × 70	4.5	7.5	9.0	4.5	98°	10.4	0.108	0.177	12.1	15.5	2.7	5.05						
xiv)	ISMT 62.5	6.7	850	62.5 × 70	5.0	8.0	9.0	4.5	98°	13.9	0.218	0.192	16.5	15.1	4.4	5.50						
xv)	ISMT 75	7.5	955	75 × 75	5.0	8.0	9.0	4.5	98°	17.3	0.412	0.234	20.8	15.7	7.1	6.25						
xvi)	ISMT 87.5	9.8	1 240	87.5 × 85	5.8	9.0	10.0	5.0	98°	20.6	0.756	0.384	24.7	17.6	11.3	9.00						
xvii)	ISMT 100	12.7	1 620	100 × 100	5.7	10.8	11.0	5.5	98°	21.3	1.16	0.750	26.8	21.5	14.7	15.0						
Indian Standard Slit Tee Bars from H-Section;																						
xviii)	ISHT 75	15.3	1 950	75 × 150	8.4	9.0	8.0	4.0	94°	16.2	0.962	2.30	22.2	34.4	16.4	30.1						
xix)	ISHT 100	20.0	2 550	100 × 200	7.8	9.0	9.0	4.5	94°	19.1	1.94	4.97	27.6	44.2	24.0	49.3						
xx)	ISHT 125	27.4	3 480	125 × 250	8.8	9.7	10.0	5.0	94°	23.7	4.15	10.0	34.5	53.7	41.0	79.9						
xxi)	ISHT 150	29.4	3 740	150 × 250	7.6	10.6	11.0	5.5	94°	26.6	5.74	11.0	39.2	54.1	46.5	87.7						

<sup>\*</sup>Slit from ISLB 200 and ISLB 500.

<sup>†</sup>Slit from MB 100, 125, 150, 175 and 200.

<sup>‡</sup>Slit from ISHB 150, 200, 250 and 300.

### ANNEX A

## (<u>Foreword</u>)

## COMMITTEE COMPOSITION

Structural Engineering Sectional Committee, CED 07

Organization	Representative(s)
In Personal Capacity (II, 2A, Rani Meyyammai Towers MRC Nagar, R A Puram Chennai - 600028)	Dr V. Kalyanaraman ( <i>Chairperson</i> )
Ashwathnarayana & Eswara, Chennai	SHRI H. E. SRIPRAKASH SHASTRY
Bhilai Institute of Technology, Durg	Dr Mohan Kumar Gupta
Central Electricity Authority, New Delhi	SHRI A. K. JAIN DIRECTOR (TRANSMISSION) (Alternate)
Central Public Works Department, New Delhi	SHRI D. K. GARG SHRI N. K. BANSAL ( <i>Alternate</i> )
Construma Consultancy Pvt Ltd, Mumbai	Dr Harshavardhan Subbarao
C.R. Narayana Rao, Architects & Engineers, Chennai	Dr C. N. Srinivasan Shri C. R. Arvind ( <i>Alternate</i> )
CSIR - Structural Engineering Research Centre, Chennai	DR G. S. PALANI DR NAPA PRASAD RAO ( <i>Alternate</i> I) DR R. BALAGOPAL ( <i>Alternate</i> II)
Engineers India Ltd, New Delhi	SHRI ANURAG SINHA DR SUDIP PAUL ( <i>Alternate</i> )
GAIL India Ltd, New Delhi	SHRI S. ASHISH VAIDYA
Indian Institute of Engineering Science and Technology, Shibpur	Dr Subrata Chackraborty Ms Chaitali Ray ( <i>Alternate</i> )
Indian Institute of Technology Delhi, New Delhi	Dr Dipti Ranjan Sahoo Dr Alok Madan ( <i>Alternate</i> )
Institute for Steel Development & Growth, Kolkata	SHRI ARIJIT GUHA SHRI LAKHAMANA RAO PYDI ( <i>Alternate</i> )
Jindal Steel & Power Ltd, Gurugram	SHRI SANJAY NANDANWAR
Larsen & Toubro Ltd, Chennai	SHRI T. VENKATESH RAO
MECON Ltd, Ranchi	SHRI B. K. PANDEY SHRI J. K. SARKAR ( <i>Alternate</i> )
M. N. Dastur & Company Pvt Ltd, Kolkata	SHRI SHUVENDU CHATTOPADHYAY SHRI GARGI ADITYA BASU ( <i>Alternate</i> I) SHRIMATI MOHUA CHATTERJEE ( <i>Alternate</i> II)
NTPC Ltd, Noida	SHRI HIMANSHU KUNDU

SHRI CHANDER SHEKHAR (Alternate)

Organization

Representative(S)

Powergrid Corporation of India Limited, New Delhi

SHRI ABHISHEK

Ms Sumana Mukherjee (Alternate)

Ramboll India, Hyderabad

SHRI D. SANKAR GANESH

Salasar Techno Engineering Ltd, Noida

SHRI DAYANAND K.

Steel Authority of India Limited, Ranchi

SHRI GAUTAM KUMAR MITRA

SHRI DEEPAK RANGARAO (Alternate)

STUP Consultants Pvt Ltd, Kolkata

SHRI ANIRBAN SENGUPTA
SHRI SUMANTRA SENGUPTA (Alternate I)
SHRI MANDAR SARDESAI (Alternate II)

Takalkar Power Engineering and Consultants Pvt

Ltd, Vadodara

SHRI S. M. TAKALKAR

SHRI SHREEDHAR V. RANA (Alternate)

Tata Consulting Engineers Ltd, Mumbai

SHRI PRATIP BHATTACHARYA
SHRI T. SHRIPRASAD (Alternate)

SHRI S. H. JAIN

The Institution of Engineers (India), Kolkata

In Personal Capacity (C-401, Greenfield Tower CHS, Kadamwadi, Vakola Santacruz (East), Mumbai)

In Personal Capacity (*Plot No. 686/2884*,

Shantinagar, Canal Road, Jharapada, Bhubaneswar - 751006) SHRI V. N. HEGGADE

SHRI GYANA RANJAN MOHANTY

BIS Directorate General

SHRI DWAIPAYAN BHADRA, SCIENTIST 'E'/DIRECTOR AND HEAD (CIVIL ENGINEERING) [REPRESENTING

DIRECTOR GENERAL (Ex-officio)]

Member Secretary
SHRI ABHISHEK PAL
SCIENTIST 'D'/JOINT DIRECTOR
(CIVIL ENGINEERING), BIS

AND

Member Secretary
Shri Dheeraj Damachya
Scientist 'B'/Assistant Director
(Civil Engineering), BIS

This Pade has been Intentionally left blank

This Pade has been Intentionally left blank

#### **Bureau of Indian Standards**

BIS is a statutory institution established under the *Bureau of Indian Standards Act*, 2016 to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

#### Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

#### **Review of Indian Standards**

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website-www.bis.gov.in or www.standardsbis.in.

This Indian Standard has been developed from Doc No.: CED 07 (22216).

#### **Amendments Issued Since Publication**

Amend No.	Date of Issue	Text Affected	

#### **BUREAU OF INDIAN STANDARDS**

#### **Headquarters:**

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402 Website: www.bis.gov.in

Regional	Offices:	Telephones
Central	: 601/A, Konnectus Tower -1, 6 <sup>th</sup> Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern	: 8 <sup>th</sup> Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	2367 0012 2320 9474
Northern	: Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern	: C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	2254 1442 2254 1216
Western	: Manakalya, 4 <sup>th</sup> Floor, NTH Complex (W Sector), F-10, MIDC, Andheri (East), Mumbai 400093	{ 283 25838

Branches: AHMEDABAD, BENGALURU, BHOPAL, BHUBANESHWAR, CHANDIGARH, CHENNAI, COIMBATORE, DEHRADUN, DELHI, FARIDABAD, GHAZIABAD, GUWAHATI, HARYNA, HUBLI, HYDERABAD, JAIPUR, JAMMU & KASHMIR, JAMSHEDPUR, KOCHI, KOLKATA, LUCKNOW, MADURAI, MUMBAI, NAGPUR, NOIDA, PARWANOO, PATNA, PUNE, RAIPUR, RAJKOT, SURAT, VIJAYAWADA.

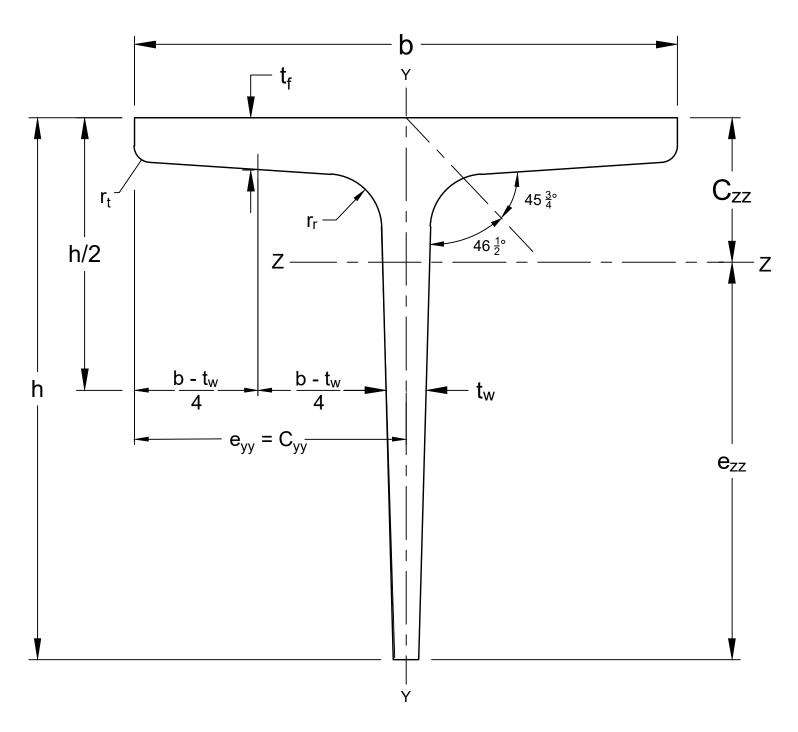


FIG. 1 ROLLER NORMAL TEE BAR (ISNT)

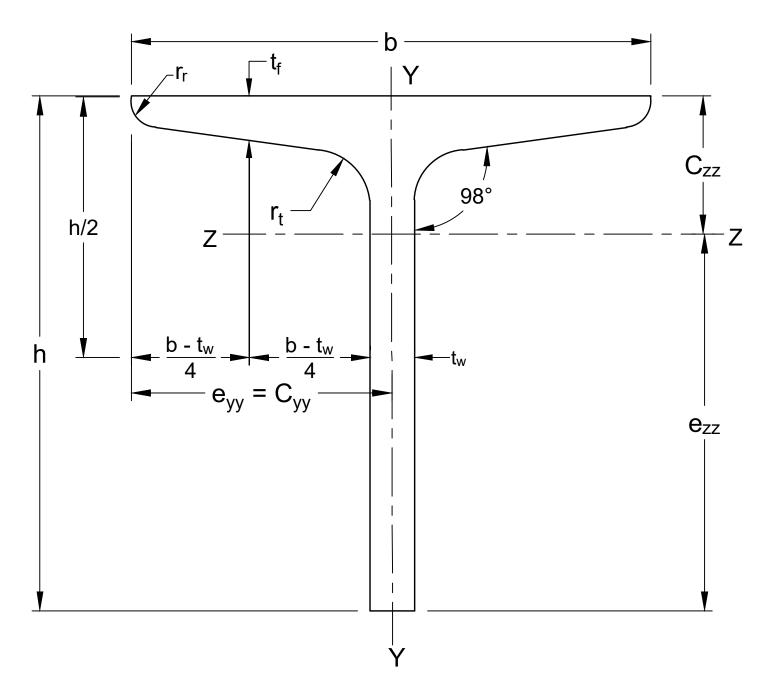


FIG. 2 SLIT TEE AND DEEP LEGGED TEE BAR