

स्टील में फ्यूजन वेल्डेड जोड़ों और
धातु — परीक्षण पद्धति

भाग 4 धात्विक सामग्रियों में वेल्ड संबंधी विनाशी
परीक्षण — फ्यूजन वेल्डेड जोड़ों में वेल्ड धातु पर अनुदैर्घ्य
तन्यता परीक्षण
(तीसरा पुनरीक्षण)

**Fusion Welded Joints and Weld
Metal in Steel — Method of Test**
**Part 4 Destructive Tests on Welds in
Metallic Materials — Longitudinal Tensile
Test on Weld Metal in Fusion Welded
Joints**
(*Third Revision*)

ICS 25.160.40

© BIS 2024
© ISO 2019



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002

www.bis.gov.in www.standardsbis.in

NATIONAL FOREWORD

This Indian Standard (Part 4) (Third Revision) which is identical to ISO 5178 : 2019 'Destructive tests on welds in metallic materials — Longitudinal tensile test on weld metal in fusion welded joints' issued by the International Organization for Standardization (ISO) was adopted by the Bureau of Indian Standards on the recommendation of the Welding General and its Applications Sectional Committee and approval of the Metallurgical Engineering Division Council.

This standard was first published in 1966 and subsequently revised in 1973 and 1984. The third revision of this standard has been undertaken to align it with ISO 5178 : 2019 under dual numbering system to harmonize it with the latest developments that have taken place at international level.

This standard is published in various parts. Other parts in this series are :

- Part 1 **Tensile test on cruciform and lapped joints**
- Part 2 **Impact tests — Test specimen location, notch orientation and examination**
- Part 3 **Transverse tensile test**
- Part 5 **Bend tests**
- Part 8 **Fracture test**
- Part 9 **Macroscopic and microscopic examination of welds**

The text of ISO standard has been approved as suitable for publication as an Indian Standard without deviations. Certain terminologies and conventions are, however, not identical with those used in Indian Standard. Attention is especially drawn to the following:

- a) Wherever the words 'International Standard' appear referring to this standard, it should be read as 'Indian Standard'; and
- b) Comma (,) has been used as a decimal marker, while in Indian Standards, the current practice is to use a point (.) as the decimal marker.

In this adopted standard, reference appears to certain International Standards for which Indian Standards also exist. The corresponding Indian Standards which are to be substituted in their place are listed below along with their degree of equivalence for the edition indicated:

<i>International Standard</i>	<i>Corresponding Indian Standard</i>	<i>Degree of Equivalence</i>
ISO 6892-1 : 2019 Metallic materials — Tensile testing — Part 1: Method of test at room temperature	IS 1608 (Part 1) : 2022/ISO 6892-1 : 2019 Metallic materials — Tensile testing: Part 1 Method of test at room temperature (<i>fifth revision</i>)	Identical

In reporting the result of a test or analysis made in accordance with this standard, is to be rounded off, it shall be done in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'.

Contents

Page

1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Symbols and abbreviated terms	1
5	Principle	1
6	Removal of test specimens	2
6.1	Location.....	2
6.2	Marking.....	2
6.3	Heat treatment and/or ageing.....	2
6.4	Extraction.....	2
6.4.1	General.....	2
6.4.2	Steel.....	2
6.4.3	Other metallic material.....	2
6.5	Machining of test specimens.....	2
6.6	Dimensions.....	3
6.7	Surface quality.....	4
7	Conditions of testing	4
8	Test results	4
8.1	General.....	4
8.2	Examination of fracture surfaces.....	4
9	Test report	4
Annex A (informative) Example of a test report		5

Indian Standard

FUSION WELDED JOINTS AND WELD METAL IN STEEL — METHOD OF TEST

PART 4 DESTRUCTIVE TESTS ON WELDS IN METALLIC MATERIALS — LONGITUDINAL TENSILE TEST ON WELD METAL IN FUSION WELDED JOINTS

(*Third Revision*)

1 Scope

This document specifies the sizes of test specimens and the test procedure for carrying out longitudinal tensile tests on cylindrical test specimens in order to determine the mechanical properties of weld metal in a fusion welded joint.

This document applies to metallic materials in all forms of product with joints made by any fusion welding process, having joint sizes that are sufficient to obtain cylindrical test specimens with dimensions in accordance with ISO 6892-1.

Unless specified otherwise for specific points in this document, the general principles of ISO 6892-1 apply.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Symbols and abbreviated terms

The symbols and abbreviated terms to be used for the longitudinal tensile tests shall be as specified in ISO 6892-1.

5 Principle

An increasing tensile load is continuously applied until rupture occurs in a cylindrical test specimen taken longitudinally from the weld metal in a welded joint.

The test shall be carried out at room temperature between 10 °C and 35 °C, unless otherwise specified.

Tests carried out under controlled conditions shall be made at a temperature of 23 °C ± 5 °C.

6 Removal of test specimens

6.1 Location

The test specimen shall be taken longitudinally from the welded joint of the manufactured product or from the test piece. After machining, the parallel length of the test specimen shall consist only of weld metal (see [Figures 1](#) and [2](#)).

To enable correct positioning of the test specimen in the joint, the joint cross-section at both ends of the test specimen can be macroetched.

6.2 Marking

Each test piece shall be marked in order to identify its exact location in the manufactured product or in the joint from which it has been removed.

Each test specimen shall be marked in order to identify its exact location in the test piece from which it has been taken.

When removed from the test piece, each test specimen shall be marked.

6.3 Heat treatment and/or ageing

No heat treatment shall be applied to the welded joint or to the test specimen unless it is specified or permitted by the relevant application standard dealing with the welded joint to be tested. Details of any heat treatment shall be recorded in the test report. If natural ageing of aluminium alloys takes place, the time between welding and testing shall be recorded.

NOTE The presence of hydrogen in ferrous weld metals can adversely affect the test results and suitable hydrogen release treatment.

6.4 Extraction

6.4.1 General

The mechanical or thermal processes used to extract the test specimen shall not change the properties of the test specimen in any way.

6.4.2 Steel

Shearing is excluded for thicknesses greater than 8 mm. If thermal cutting or other cutting methods which can affect the cut surfaces are used to cut the test specimen from the welded plate, or from the test piece, the cuts shall be made at a distance greater than or equal to 8 mm from the surfaces of the final parallel length of the test specimen. Thermal cutting shall not be used parallel to the original surface of the welded plate or of the test piece.

6.4.3 Other metallic material

Shearing and thermal cutting are excluded and only machining (e.g. sawing and turning) shall be used.

6.5 Machining of test specimens

Unless otherwise specified in the particular application standard dealing with the welded joint under examination, the test specimens shall be taken from the centre of the weld metal as shown in [Figure 1](#) and the cross-section as shown in [Figure 2](#). In the case where the test specimen is not taken from mid-thickness, the distance from the surfaces, t_1 , shall be recorded [see [Figures 2](#) a) and b)]. In the case of very thick or double-sided welded joints, more than one test specimen may be taken at different

locations through the thickness [see Figure 2 c)], in which case the distances, t_1 and t_2 , of each test specimen in the joint cross-section shall be recorded.


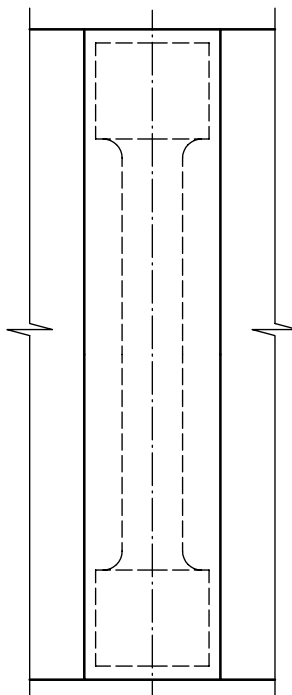


Figure 1 — Examples of location of test specimens — Longitudinal plane section

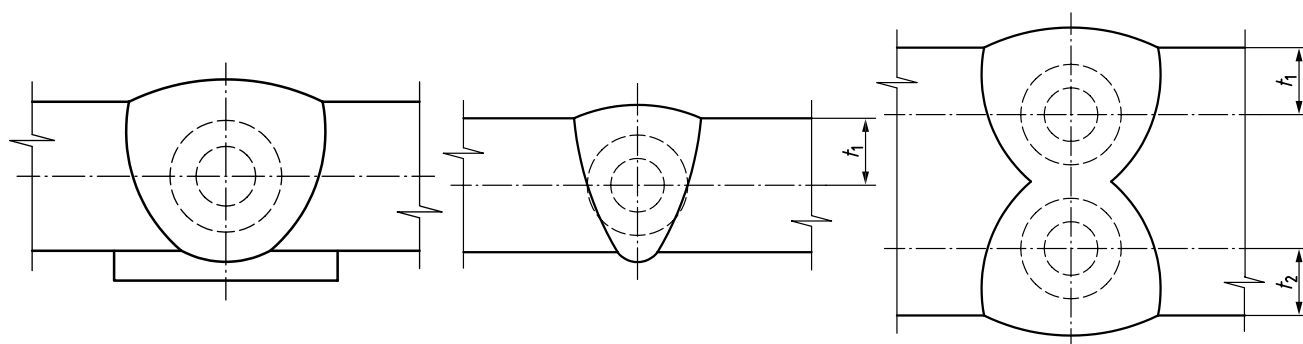

a) All-weld metal test specimen for welding consumable classification

b) Test specimen from a joint welded from one side only

c) Test specimen from a joint welded from both sides

Figure 2 — Examples of location of test specimens — Cross-section

6.6 Dimensions

Each test specimen shall have a circular cross-section, and its dimensions, expressed as functions of the diameter, d_0 , of the parallel length shall conform to ISO 6892-1.

It shall have a normal diameter, d_0 , of 10 mm. If this is not possible, the diameter shall be as large as possible but not less than 4 mm. The actual size shall be recorded in the test report.

The gripped ends of the test specimens shall be compatible with the tensile testing machine used.

6.7 Surface quality

The tolerances specified in ISO 6892-1 shall apply.

Strain-hardening or excessive heating of the material shall be avoided.

7 Conditions of testing

The test specimen shall be loaded gradually and continuously in accordance with ISO 6892-1.

8 Test results

8.1 General

The test results shall be determined in accordance with ISO 6892-1.

8.2 Examination of fracture surfaces

After rupture of the test specimen, the fracture surfaces shall be examined and the existence of any imperfections that can have adversely affected the test shall be recorded, including their type, size and quantity. If fish eyes are present, they shall be recorded and only their central regions shall be considered as imperfections.

9 Test report

The test report shall include the following information in addition to that given in ISO 6892-1:

- a) a reference to this document, i.e. ISO 5178;
- b) the location of test specimen, sketch if required (see [Figures 1](#) and [2](#));
- c) the test temperature, if different from the ambient temperature;
- d) the type and dimensions of imperfections observed;
- e) the diameter, d_0 .

An example of a typical test report is given in [Annex A](#). The proof strength plastic extension, R_p , and the force corresponding to the desired proof strength plastic extension, F_p , in [Table A.1](#) may be replaced with the upper yield strength, lower yield strength, proof strength total extension and the force corresponding to each property according to the requirement.

Annex A (informative)

Example of a test report

No.

According to WPS

According to test result “tensile test”

test result “ ”

Manufacturer:

Purpose of the examination:

Form of product:

Parent metal:

Filler metal:

Table A.1 — Longitudinal tensile test in accordance with ISO 5178

Test specimen No./ position	Dimension/ diameter mm	F_p N	F_m N	R_p N/mm ²	R_m N/mm ²	L_0 mm	A %	Z %	Test temperature °C	Remark e.g. fracture appearance

Examiner or test body:

Certified by:

(name, date and signature)

(name, date and signature)

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website- www.bis.gov.in or www.standardsbis.in

This Indian Standard has been developed from Doc No.: MTD 11 (21493).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002
Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 th Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 th Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Plot No. E-9, Road No.-8, MIDC, Andheri (East), Mumbai 400093	{ 2821 8093

Branches : AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. CHANDIGARH. CHENNAI. COIMBATORE. DEHRADUN. DELHI. FARIDABAD. GHAZIABAD. GUWAHATI. HIMACHAL PRADESH. HUBLI. HYDERABAD. JAIPUR. JAMMU & KASHMIR. JAMSHEDPUR. KOCHI. KOLKATA. LUCKNOW. MADURAI. MUMBAI. NAGPUR. NOIDA. PANIPAT. PATNA. PUNE. RAIPUR. RAJKOT. SURAT. VISAKHAPATNAM.