

धातु पाउडर के आयताकार संघनन के  
अनुप्रस्थ विच्छेदन द्वारा हरित शक्ति  
के निर्धारण की पद्धतियाँ

( पहला पुनरीक्षण )

Methods for Determination of  
Green Strength by Transverse  
Rupture of Rectangular Compacts  
of Metallic Powder

( First Revision )

ICS 77.160

© BIS 2024

© ISO 2023



भारतीय मानक ब्यूरो  
BUREAU OF INDIAN STANDARDS  
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002  
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG  
NEW DELHI - 110002

[www.bis.gov.in](http://www.bis.gov.in) [www.standardsbis.in](http://www.standardsbis.in)

## NATIONAL FOREWORD

This Indian Standard (First Revision) which is identical to ISO 3995 : 2023 'Metallic powders — Determination of green strength by transverse rupture of rectangular compacts' issued by the International Organization for Standardization (ISO) was adopted by the Bureau of Indian Standards on the recommendation of the Powder Metallurgical materials and Products Sectional Committee and approval of the Metallurgical Engineering Division Council.

This standard was published in 1988. This revision of this standard has been brought out to align with the latest version of ISO 3995 : 2023 under dual numbering system to harmonize it with the latest developments that have taken place at international level.

Former title of the Indian Standard IS 12571 : 1988 was 'Determination of Green Strength by Transverse Rupture of Rectangular Compacts of Metallic Powder — Methods' which is change to 'Metallic powders — Determination of green strength by transverse rupture of rectangular compacts' as per the title of ISO 3995 : 2023.

This document covers a test method that may be used to measure the transverse rupture strength of a compacted but unsintered (green) test specimen produced from lubricated or unlubricated metal powders or powder mixtures.

The text of ISO standard has been approved as suitable for publication as in Indian Standard without deviations. Certain terminologies and conventions are, however, not identical with those used in Indian Standard. Attention is especially drawn to the following:

- a) Wherever the words 'International Standard' appear referring to this standard, it should be read as 'Indian Standard'; and
- b) Comma (,) has been used as a decimal marker while in Indian Standards the current practice is to use a point (.) as the decimal marker.

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis shall be rounded off in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

# Contents

Page

<b>1</b>	<b>Scope</b> .....	<b>1</b>
<b>2</b>	<b>Normative references</b> .....	<b>1</b>
<b>3</b>	<b>Terms and definitions</b> .....	<b>1</b>
<b>4</b>	<b>Principle</b> .....	<b>1</b>
<b>5</b>	<b>Apparatus</b> .....	<b>1</b>
<b>6</b>	<b>Sampling</b> .....	<b>4</b>
<b>7</b>	<b>Procedure</b> .....	<b>4</b>
	7.1 Cleaning of the die and punches.....	4
	7.2 Powder testing conditions.....	4
	7.3 Lubrication.....	5
	7.3.1 General.....	5
	7.3.2 Die wall lubrication.....	5
	7.3.3 Lubrication of powder.....	5
	7.4 Compacting and ejection.....	5
	7.5 Compacting pressure.....	6
	7.6 Determination of density.....	7
	7.7 Determination of breaking force.....	7
	7.7.1 General.....	7
	7.7.2 Method 1 — Using a compression testing machine.....	7
	7.7.3 Method 2 — Using a loading beam device (see <a href="#">Figure 3</a> ).....	7
<b>8</b>	<b>Expression of results</b> .....	<b>7</b>
<b>9</b>	<b>Test report</b> .....	<b>8</b>



*Indian Standard*

**METHODS FOR DETERMINATION OF GREEN STRENGTH BY  
TRANSVERSE RUPTURE OF RECTANGULAR COMPACTS OF  
METALLIC POWDER**

*( First Revision )*

## **1 Scope**

This document specifies a method for the determination of green strength by measuring the transverse rupture strength of compacts of rectangular cross-section.

## **2 Normative references**

There are no normative references in this document.

## **3 Terms and definitions**

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

## **4 Principle**


Subjection of a compact pressed from metallic powder to a uniformly increasing transverse force under controlled conditions until fracture occurs. Determination of the transverse rupture strength, or green strength as used herein, as the stress, calculated from the flexure formula, required to break the compact as a simple beam supported near the ends and applying the force midway between the fixed centre of supports.

The green strength is determined on compacts either having a particular density or after compaction at a specific compacting pressure.

## **5 Apparatus**

**5.1 Die**, preferably of cemented carbide or alternatively of tool steel, and two punches for producing rectangular test pieces with dimensions according to [Clause 6](#).

All mating parts shall be fitted and lapped. An example of a design for tooling is shown in [Figure 1](#).

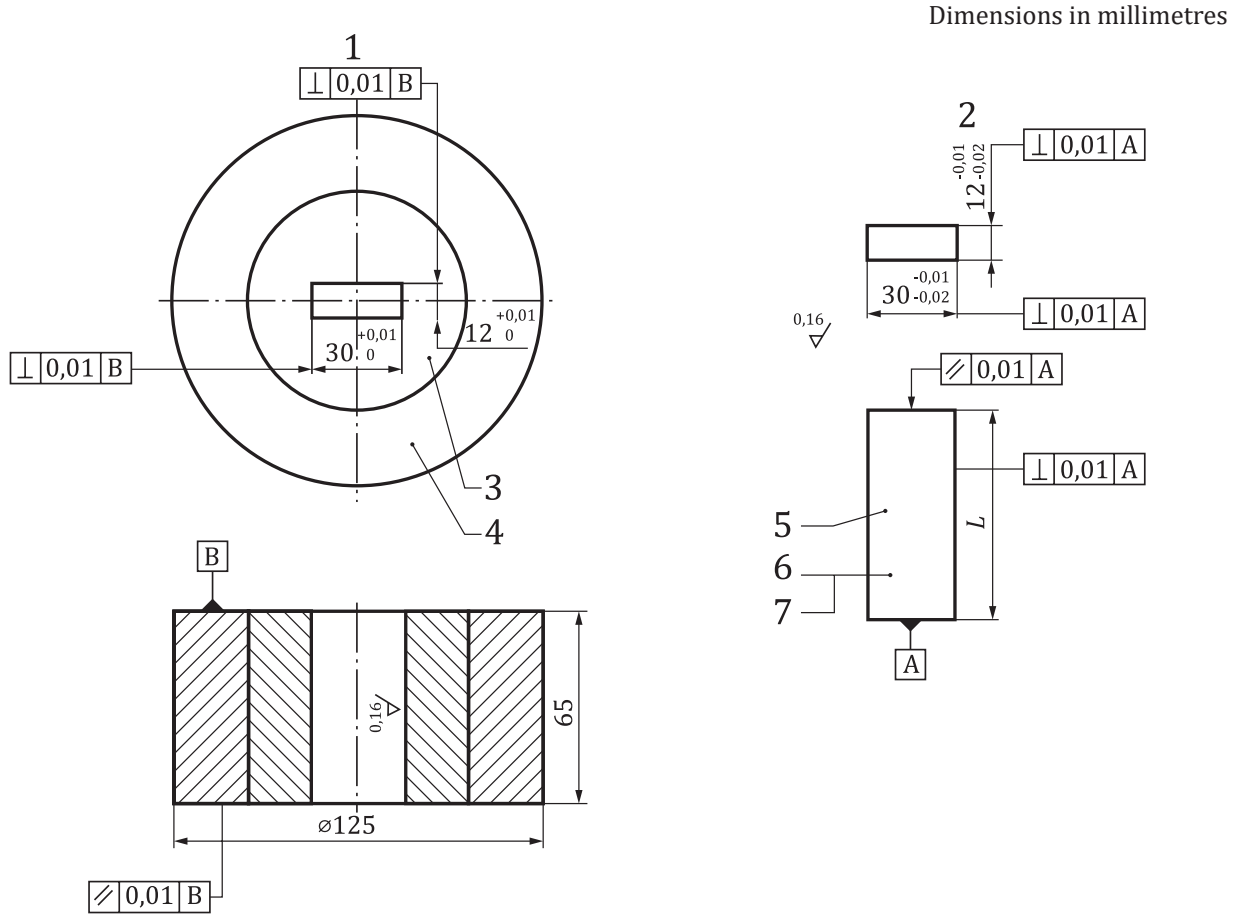

**Key**

- |                    |                       |
|--------------------|-----------------------|
| 1 die              | 5 steel HRC 60 to 62  |
| 2 punches          | 6 upper punch; L = 25 |
| 3 cemented carbide | 7 lower punch; L = 70 |
| 4 shrink ring      |                       |

**Figure 1 — Example of tooling to produce a rectangular test piece**

**5.2 Press**, capable of applying forces up to about 300 kN with a minimum accuracy of  $\pm 2\%$  and adjustable to permit an even increase of the force at a rate no higher than 50 kN/s.

**5.3 Balance**, capable of weighing the compacts to an accuracy of  $\pm 0,01$  g.

**5.4 Micrometer or other measuring device**, suitable for measuring the dimensions of the compacts to an accuracy of  $\pm 0,01$  mm.


**5.5 Fixture for testing**, having two support cylinders (rollers) with a fixed distance between them and a load cylinder (roller).

All three cylinders shall be  $3,0 \text{ mm} \pm 0,1 \text{ mm}$  in diameter and shall be made of hardened steel with a hardness of at least 700 HV, or of hardmetal.

The cylinders shall be mounted parallel and the distance between the centres of the support cylinders shall be  $25 \text{ mm} \pm 0,2 \text{ mm}$  or  $25,4 \text{ mm} \pm 0,2 \text{ mm}$ , measured with an accuracy of  $\pm 0,1 \text{ mm}$ . The load cylinders shall be mounted midway between the support cylinders.

The mounting of the cylinders shall be such as to account for the permitted deviation from parallelism of the top and bottom faces of the test piece.

A diagrammatic arrangement of a typical test fixture is shown in [Figure 2](#).

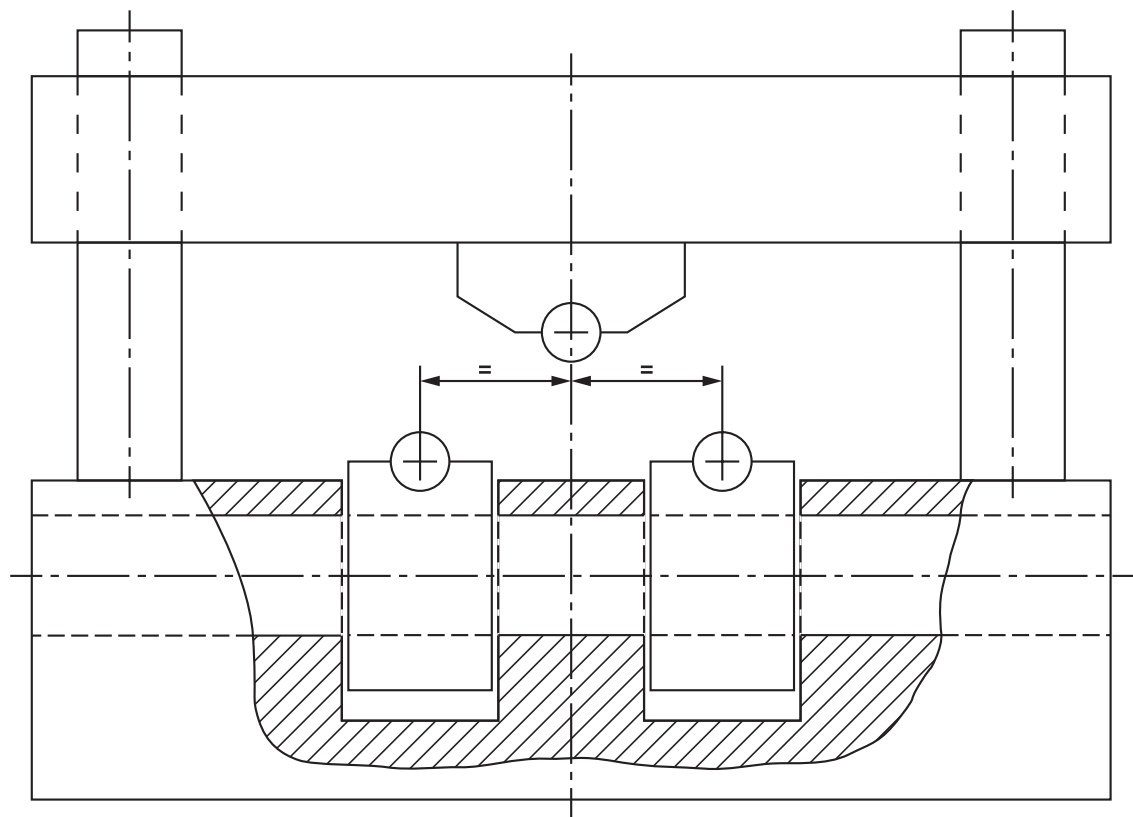


**Figure 2 — Diagram of test fixture**

**5.6 Loading device.** Loading devices shall be either of the devices in [5.6.1](#) or [5.6.2](#).

**5.6.1 A compression testing machine** capable of determining the breaking force with a minimum accuracy of  $\pm 2$  N.

**5.6.2 A loading beam apparatus** to properly locate the test piece and which is capable of applying a breaking force through a lever arrangement. The applied force on the test piece shall be calculated to an accuracy of  $\pm 2$  N.

Note The applied force can be exerted by various systems, an example of which is given in [Figure 3](#).

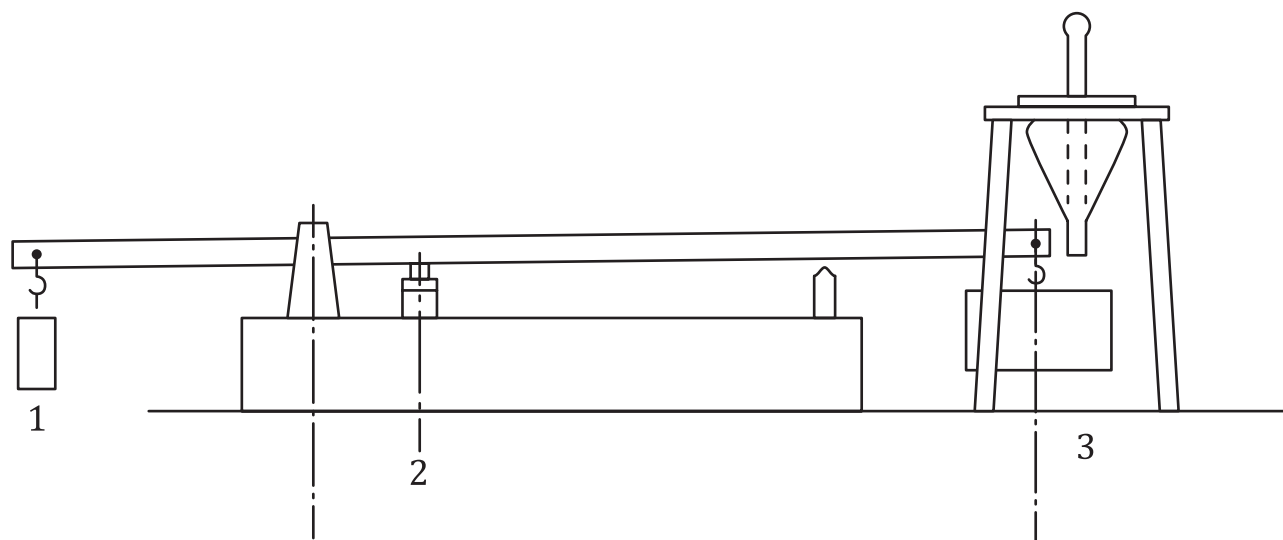

**Key**

- 1 counterbalance
- 2 test fixture
- 3 load

**Figure 3 — Example of loading beam apparatus**

## 6 Sampling

The quantity of the test sample shall be chosen to give three test pieces with the dimensions 10 mm to 13 mm wide, at least 30 mm long and 5,5 mm to 6,5 mm thick. The thickness of the test piece shall be uniform within 0,1 mm over the distance between supports. If necessary, preliminary tests should be made in order to establish the quantity of powder which is needed to fulfil this requirement.

## 7 Procedure

### 7.1 Cleaning of the die and punches

Wipe the die cavity and the punches with soft and clean paper.

### 7.2 Powder testing conditions

**7.2.1** Powders which do not contain a lubricant can be compacted in the following ways:

- a) in a dry die

Note seizure and excessive die wear may occur, particularly at high compacting pressures;

- b) in a die with lubricated walls (see [7.3.2](#));
- c) after admixing a lubricant (see [7.3.3](#)) and in a dry die.

**7.2.2** Powders which contain a lubricant can be compacted the following ways:

- a) in a dry die;
- b) after admixing additional lubricant (see [7.3.3](#)) and in a dry die.



## 7.3 Lubrication

### 7.3.1 General

Lubrication shall be either of the methods in [7.3.2](#) or [7.3.3](#) or a combination of them.

### 7.3.2 Die wall lubrication

Apply to the die walls a mixture or a solution of a lubricant in a volatile liquid, for example 100 g of zinc stearate in 1 000 cm<sup>3</sup> of acetone. After any excess liquid has drained away, allow the solution adhering to the walls to evaporate leaving a thin layer of lubricant.

### 7.3.3 Lubrication of powder

Lubricate the powder to be tested by thoroughly mixing into it a quantity (for example 0,5 % to 1,5 %) of a suitable solid lubricant (for example zinc stearate or synthetic wax).

## 7.4 Compacting and ejection


Insert the lower punch into the die cavity. Position the die to the desired filling height by using supporting spacers between the die and the foot of the lower punch. Pour the sample into the die cavity, taking the usual precautions to ensure that the powder is uniformly distributed in the die cavity. Position the upper punch and place the die with the punches between the platens of the press. Apply and release a preliminary force of approximately 20 kN. Remove the spacers supporting the die. If the die is supported by springs, or in some similar way, it is not necessary to apply the preliminary force.

Apply the final force at a constant rate which shall not exceed 50 kN/s.

Eject the compact from the die by means of the lower punch.

The procedure of compacting and ejection is exemplified in [Figure 4](#).

A press tool built into an adaptor where the powder is filled into the tool die by a fill shoe and compaction and ejection is carried out in an automated sequence by the press is also a viable option. With such arrangement the requirement maximum load rate is still valid. The tool arrangement shall enable to compact the specimen uniaxially by means of supporting the die on springs, or alternatively, by controlling the motion of the tool die in relation to the movement of the upper punch.

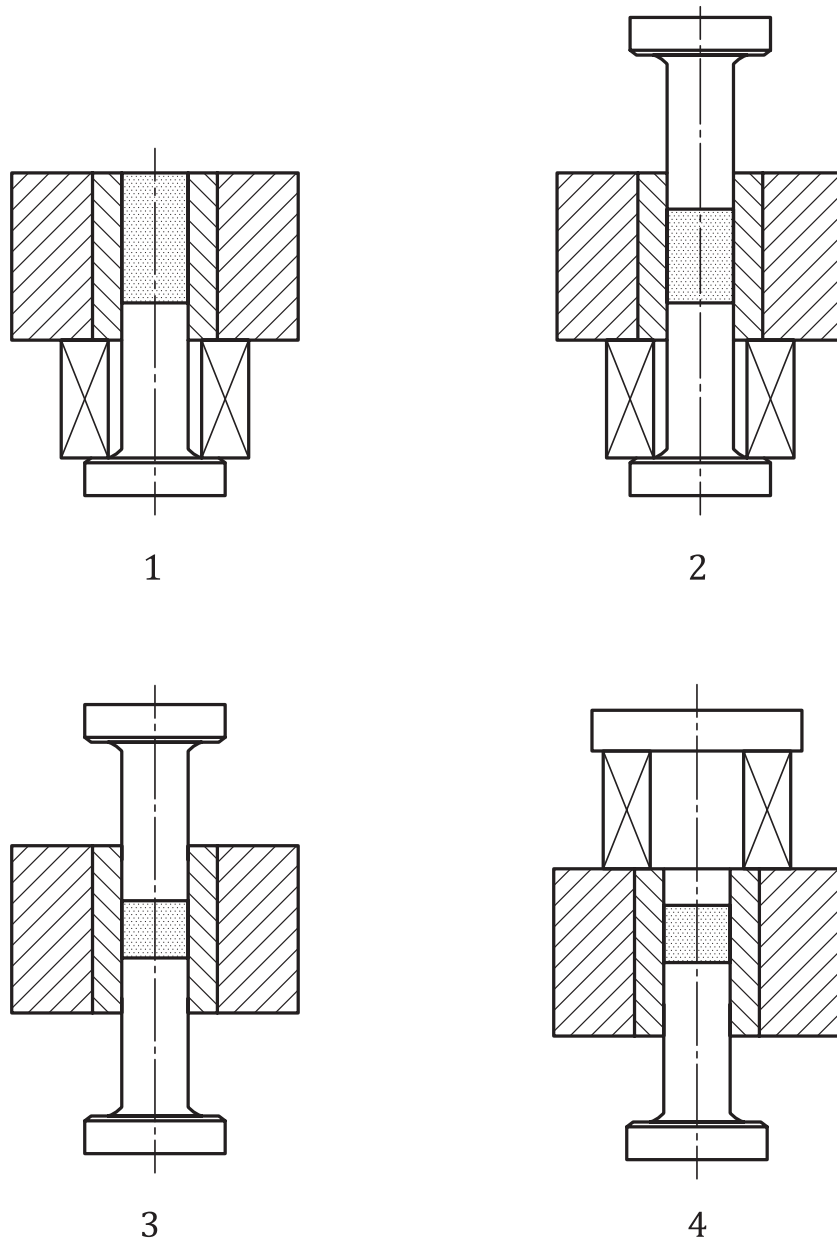

**Key**

- 1 filling
- 2 pre-compacting
- 3 compacting
- 4 ejection

**Figure 4 — Procedure of compacting and ejection**

### 7.5 Compacting pressure

Green strength shall be determined at a given pressure or density following agreement between supplier and customer. In the first case the recommended pressure is  $400 \text{ N/mm}^2$  or  $600 \text{ N/mm}^2$ . In the second case, when test pieces are pressed to a given density, the maximum deviation between the three test pieces shall not exceed  $\pm 0,05 \text{ g/cm}^3$  from target density.

## 7.6 Determination of density

Measure the length, width and thickness of the test piece in the plane of application of the force to the nearest 0,01 mm. Determine the mass and the volume (calculated from the average value of dimensions).

## 7.7 Determination of breaking force

### 7.7.1 General

Break the test piece under controlled conditions using either a compression testing machine or a loading beam device.

### 7.7.2 Method 1 — Using a compression testing machine

Position the test piece in the transverse rupture test fixture (see [Figure 2](#)) so that it is centrally located and perpendicular to the axis of the support cylinders. Place the fixture between the platens of the testing machine and apply a compressive force at a uniform rate such that the test piece fractures within a time not less than 10 s. Record the breaking force to the nearest 2 N.

### 7.7.3 Method 2 — Using a loading beam device (see [Figure 3](#))

Adjust the balance of the beam so that it is level. Position the test piece in the loading beam device so that it is centrally located and perpendicular to the axis of the support cylinders. Increase the load at a uniform rate such that the test piece fractures within a time not less than 10 s.

Determine the input force to the nearest 2 N.

**NOTE** When a container and shot are used, the beam should be balanced with the container in position. The load exerted is then calculated from the mass of the shot only.

## 8 Expression of results

**8.1** Calculate the density of the test piece from its mass and volume. Calculate the arithmetical mean of the determination on three different test pieces to the nearest 0,05 g/cm<sup>3</sup>.

**8.2** The green strength  $S$ , expressed in N/mm<sup>2</sup>, is given by [Formula \(1\)](#):

$$S = \frac{3 \times P \times L}{2 \times t^2 \times w} \quad (1)$$

where

$P$  is the force, in N, required to rupture;

$L$  is the length, in mm, of span of the fixture;

$t$  is the thickness, in mm, of the test piece;

$w$  is the width, in mm, of the test piece.

**8.3** Calculate the arithmetical mean of the three determinations rounded to the nearest 0,2 N/mm<sup>2</sup> for values up to and including 10 N/mm<sup>2</sup> and to the nearest 0,5 N/mm<sup>2</sup> for values greater than 10 N/mm<sup>2</sup>.

## **9 Test report**

The test report shall include the following information:

- a) a reference to this document, i.e. ISO 3995:2023;
- b) all details necessary for identification of the test sample;
- c) the lubrication technique: die wall lubrication, admixed powder lubrication or other technique. In case of admixed powder lubrication, indicate the type and amount of lubricant;
- d) the density of the test pieces or the compacting pressure;
- e) compacting die material (tool steel or cemented carbide);
- f) the result obtained;
- g) all operations not specified by this document (i.e. ISO 3995:2023), or regarded as optional;
- h) details of any occurrence which may have affected the result.



## Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

### Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

### Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website-[www.bis.gov.in](http://www.bis.gov.in) or [www.standardsbis.in](http://www.standardsbis.in).

This Indian Standard has been developed from Doc No.: MTD 25 (24982).

### Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

## BUREAU OF INDIAN STANDARDS

### Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402

Website: [www.bis.gov.in](http://www.bis.gov.in)

### Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 <sup>th</sup> Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 <sup>th</sup> Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Manakalya, 5 <sup>th</sup> Floor/MTNL CETTM, Technology Street, Hiranandani Gardens, Powai Mumbai 400076	{ 25700030 25702715

**Branches :** AHMEDABAD, BENGALURU, BHOPAL, BHUBANESHWAR, CHANDIGARH, CHENNAI, COIMBATORE, DEHRADUN, DELHI, FARIDABAD, GHAZIABAD, GUWAHATI, HARYANA (CHANDIGARH), HUBLI, HYDERABAD, JAIPUR, JAMMU, JAMSHEDPUR, KOCHI, KOLKATA, LUCKNOW, MADURAI, MUMBAI, NAGPUR, NOIDA, PARWANOO, PATNA, PUNE, RAIPUR, RAJKOT, SURAT, VIJAYAWADA.