
प्रकाशिकी और फोटोनिक्स — प्रकाशीय तत्वों
और प्रणालियों के लिए आरेखण तैयार करना
भाग 5 सतह की बनावट

Optics and Photonics — Preparation
of Drawings for Optical Elements
and Systems

Part 5 Surface Texture

ICS 37.020; 01.100.20

© BIS 2024

© ISO 2019



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002

www.bis.gov.in www.standardsbis.in

NATIONAL FOREWORD

This Indian Standard (Part 5) which is identical to ISO 10110-8 : 2017 'Optics and photonics — Preparation of drawings for optical elements and systems — Part 8: Surface texture' issued by the International Organization for Standardization (ISO) was adopted by the Bureau of Indian Standards on the recommendation of the Optics and Photonics Sectional Committee and approval of the Production and General Engineering Division Council.

This standard specifies rules for the indication of the surface texture of optical elements. This standard also specifies method for characterizing the residual surface that is left after detrending by subtracting the surface form.

IS 5920 (Part 1) supersedes the originally published Indian Standard IS 5920 : 1970 'Recommendation for the preparation of drawing for optical elements and system'.

This standard has been published in thirteen parts. The other parts in this series are:

Part 1	General
Part 2	Surface form tolerances
Part 3	Centering tolerances
Part 4	Surface imperfections
Part 6	Surface treatment and coating
Part 7	Non-tolerance data
Part 8	Aspheric surfaces
Part 9	Wave front deformation tolerance
Part 10	Diffraction surfaces
Part 11	Laser irradiation damage threshold
Part 12	Stress birefringence, bubbles and inclusions, homogeneity, and striae
Part 13	General description of surfaces and components

The text of ISO standard has been approved as suitable for publication as an Indian Standard without deviations. Certain conventions are, however, not identical to those used in Indian Standards. Attention is particularly drawn to the following:

- Wherever the words 'International Standard' appear referring to this standard, they should be read as 'Indian Standard'; and
- Comma (,) has been used as a decimal marker while in Indian Standards, the current-practice is to use a point (.) as the decimal marker.

In this adopted standard, reference appears to certain International Standards for which Indian Standards also exist. The corresponding Indian Standards, which are to be substituted in their respective places, are listed below along with their degree of equivalence for the editions indicated.

<i>International Standards</i>	<i>Corresponding Indian Standards</i>	<i>Degree of Equivalence</i>
ISO 1302 : 2002 Geometrical product specifications (GPS) — Indication of surface texture in technical product documentation	IS 10719 : 2015/ISO 1302 : 2002 Geometrical product specifications (GPS) — Indication of surface texture in technical product documentation (<i>first revision</i>)	Identical

[*\(Continued on third cover\)*](#)

Contents

Page

1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Description of surface texture	7
4.1	General	7
4.2	Description of matt surfaces	8
4.3	Description of optically smooth surfaces	8
4.3.1	Description methods	8
4.3.2	Rms roughness and rms waviness	8
4.3.3	Polish grades	9
4.3.4	Power spectral density (PSD) function	9
4.3.5	Area power spectral density (APSD) function	10
4.3.6	Rms slope	11
4.3.7	Area rms slope	11
5	Indication in drawings	11
5.1	General	11
5.2	Indication for matt surface texture	11
5.3	Indication for optically smooth surface texture	12
5.3.1	Optically smooth surface without quantitative modification	12
5.3.2	Indication of smoothness by polish grade	12
5.3.3	Indication of rms roughness and rms waviness	13
5.3.4	Indication of PSD function specification	13
5.3.5	Indication of APSD function specification	13
5.3.6	Indication of rms or area rms slope specification	14
5.3.7	Indication of lay	14
5.4	Location	15
Annex A (informative) Relationship between surface texture and scattering characteristic of textured surfaces		16
Annex B (informative) Examples of indication of surface texture requirements		18
Bibliography		22

Indian Standard

OPTICS AND PHOTONICS — PREPARATION OF DRAWINGS FOR OPTICAL ELEMENTS AND SYSTEMS

PART 5 SURFACE TEXTURE

1 Scope

This document specifies rules for the indication of the surface texture of optical elements, in the ISO 10110 series, which standardizes drawing indications for optical elements and systems. Surface texture is the characteristic of a surface that can be effectively described with statistical methods. Typically, surface texture is associated with high spatial frequency errors (roughness) and mid-spatial frequency errors (waviness).

This document is primarily intended for the specification of polished optics.

This document describes a method for characterizing the residual surface that is left after detrending by subtracting the surface form. The control of the surface form specified in ISO 10110-5, ISO 10110-12, and ISO 10110-19 is not specified in this document.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1302:2002, *Geometrical Product Specifications (GPS) — Indication of surface texture in technical product documentation*

ISO 4287:1997, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

ISO 10110-1, *Optics and photonics — Preparation of drawings for optical elements and systems, Part 1: General*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4287 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

surface texture

characteristic relating to the profile of an optical surface that can be effectively described with statistical methods

Note 1 to entry: Localized defects, known as surface imperfections, are specified in ISO 10110-7.

3.2

matt surface

optical surface for which the height variation of the surface texture is not considerably smaller than the wavelength of light

Note 1 to entry: Matt surfaces are usually produced by brittle grinding of glass or other dielectric material, or by etching.

3.3

optically smooth surface

optical surface for which the height variation of the surface texture is considerably smaller than the wavelength of light

Note 1 to entry: Due to the smaller height variation, the amount of light scattered is small.

Note 2 to entry: Optically smooth surfaces are usually produced by polishing or moulding.

3.4

reference profile

trace on which the probe of contact (stylus) instruments is moved within the intersection plane along the guide

[SOURCE: ISO 3274:1996, 3.1.2, modified — "of contact (stylus) instruments" has been inserted and the Note to entry has been omitted.]

3.5

total profile

digital form of the traced profile relative to the reference profile, with the vertical and horizontal coordinates assigned to each other

[SOURCE: ISO 3274:1996, 3.1.3, modified — The Note to entry has been omitted.]

3.6

profile filter

filter which separates profiles into longwave and shortwave components

Note 1 to entry: There are three filters used in instruments for measuring roughness, waviness and primary profiles (see [Figure 1](#)). They all have the same transmission characteristics, defined in ISO 11610-21, but different cut-off wavelengths.

[SOURCE: ISO 4287:1997, 3.1.1, modified — In the definition, ISO 11562 has been deleted. In Note 1 to entry, ISO 11562 has been replaced by ISO 11610-21.]

3.7

profile filter λ_s

filter which defines the intersection between the roughness and the even shorter wave components present in a surface (see [Figure 1](#))

[SOURCE: ISO 4287:1997, 3.1.1.1, modified — " λ_s profile filter" has been replaced by "profile filter λ_s ".]

3.8

profile filter λ_c

filter which defines the intersection between the roughness and waviness components (see [Figure 1](#))

[SOURCE: ISO 4287:1997, 3.1.1.2, modified — " λ_c profile filter" has been replaced by "profile filter λ_c ".]

3.9

profile filter λ_f

filter which defines the intersection between the waviness and the even longer wave components present in a surface (see [Figure 1](#))

[SOURCE: ISO 4287:1997, 3.1.1.3, modified — " λ_f profile filter" has been replaced by "profile filter λ_f ".]

**3.10
primary profile**

total profile after application of the short wavelength filter, λ_s

[SOURCE: ISO 3274:1996, 3.1.4, modified — The Note to entry has been removed.]

**3.11
roughness profile**

profile derived from the primary profile by suppressing the longwave component using the profile filter λ_c ; this profile is intentionally modified (see [Figure 1](#))

[SOURCE: ISO 4287:1997, 3.1.6, modified — The Notes to entry have been removed.]


**3.12
waviness profile**

profile derived by subsequent application of the profile filter λ_f and the profile filter λ_c to the primary profile, suppressing the longwave component using the profile filter λ_f and suppressing the shortwave component using the profile filter λ_c

Note 1 to entry: This profile is intentionally modified (see [Figure 1](#)).

Note 2 to entry: Most optical components require at most two surface texture bands; typically defined as roughness and waviness. The designation of these two bands as “roughness” and “waviness” is arbitrary. In some applications it will be desirable to segment the surface texture into three or more bands; in this case additional bands can be added using the same profile segmentation logic provided here. The additional bands can be distinguished by an index value (e.g. *Wq1, Wq2, Sq1, Sq2*) if desired.

[SOURCE: ISO 4287:1997, 3.1.7, modified — The notes to entry have been omitted, "(see [Figure 1](#))" and new Notes to entry have been added.]

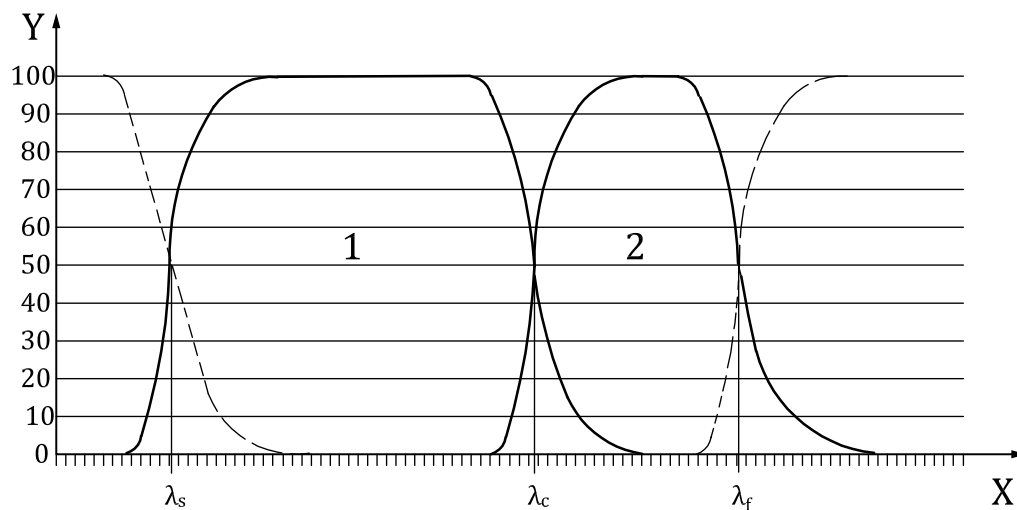

Key

X	wavelength	1	roughness profile
Y	transmission %	2	waviness profile

NOTE The cut-offs are not drawn to scale.

Figure 1 — Transmission characteristics of roughness and waviness profile

3.13 spatial wavelength

peak to peak scale-length of a sinusoidal surface undulation, especially when viewed in a Fourier transform

Note 1 to entry: See ISO 3274 and ISO 16610-21 for more information.

3.14 spatial band

range of surface spatial wavelengths which are to be included in the specification, defined as the band of sinusoidal profile wavelengths which are transmitted at more than 50 % when two phase correct filters of different cut-off wavelength are applied to the profile

Note 1 to entry: This is equivalent to the term “transmission band” as used in ISO 1302. In order to prevent confusion with spectral transmission bands, the term “spatial band” is used instead of “transmission band” in this document.

Note 2 to entry: Profile filters act as longpass or shortpass filters. That is, the profile filter with the shorter cut-off wavelength retains the long wave profile component (longpass) and the profile filter with the longer cut-off wavelength retains the short wave profile component (shortpass).

3.15 sampling length

length in the direction of the X-axis used for identifying the irregularities characterizing the profile under evaluation

Note 1 to entry: The sampling length for the roughness and waviness profile is numerically equal to the characteristic wavelength of the profile filters λ_c and λ_p , respectively. The sampling length for the primary profile is equal to the evaluation length.

[SOURCE: ISO 4287:1997, 3.1.9, modified — The symbols l_p , l_r , l_w have been removed.]

3.16 evaluation length

length in the direction of the X-axis used for assessing the profile under evaluation

Note 1 to entry: The evaluation length may contain one or more sampling lengths.

Note 2 to entry: For default evaluation lengths, see ISO 4288: 1996, 4.4. ISO 4288 does not give a default evaluation length for W -parameters.

[SOURCE: ISO 4287:1997, 3.1.10, modified — The symbol l_n has been removed.]

3.17 profile ordinate value

$Z(x)$
height of assessed profile at any position x

Note 1 to entry: This is equivalent to the term “ordinate value” as used in ISO 4287. In order to differentiate the term from the equivalent areal definition, the term “profile ordinate value” is used in this document.

3.18 surface ordinate value

$Z(x,y)$
height of assessed surface at any position x, y

3.19 detrending

extracting long scale form error from a measurement to mitigate spectral leakage

Note 1 to entry: Detrending is usually applied to the input data to avoid masking low-amplitude high frequency errors with the large amplitude, low frequency surface form errors. The resultant set of data points represents the residual surface. See also [3.21](#), [3.22](#), and [3.23](#).

Note 2 to entry: For the purposes of this document, the surface form used for detrending is a polynomial fit to the measured surface with an order sufficient to remove all spatial wavelengths longer than the spatial band of the specification.

**3.20
measured surface**

Z_m
function of raw surface measurement data, prior to detrending

**3.21
surface form**

Z_f
fit to a measured surface

Note 1 to entry: In a typical 2D polynomial fit to a surface, the surface polynomial can be written as a Zernike polynomial or another polynomial equation. For example in Cartesian coordinates:

$$Z_f(x, y) = \sum_{i=1}^p \sum_{j=1}^q C_{ij} P_{ij}(x, y) \quad (1)$$

where P_{ij} is a polynomial function of order p, q that describes the underlying shape of the surface.

**3.22
residual surface**

Z
function that is calculated by subtracting the surface form Z_f from a measured surface Z_m

Note 1 to entry: For example in 2D, this is expressed mathematically as: $Z(x, y) = Z_m(x, y) - Z_f(x, y)$ or in polar coordinates $Z(r, \theta) = Z_m(r, \theta) - Z_f(r, \theta)$.

Note 2 to entry: Neglecting correction factors for instrument response, the residual surface is taken as the surface height data.

**3.23
average roughness**

R_a
arithmetic mean deviation of the roughness profile within the sampling length

**3.24
rms roughness**

R_q
root mean square value of the height of the roughness profile within the sampling length

**3.25
area average roughness**

S_a
arithmetic mean deviation of the surface within the sampling area

**3.26
area rms roughness**

S_q
root mean square value of the height of the surface within the sampling area

**3.27
average waviness**

W_a
arithmetic mean deviation of the waviness profile within the sampling length

3.28

rms waviness

W_q

root mean square value of the height of the waviness profile within the sampling length

3.29

power spectral density

PSD

squared magnitude of the Fourier transform of the residual surface height function along one dimension using an appropriate weighting function

Note 1 to entry: The PSD describes surface texture in a spatial frequency context allowing the waviness or ripples in the surface to be described and controlled.

Note 2 to entry: An alternative and analogous function for describing and controlling surface texture in a spatial frequency context is the Auto-Covariance or ACV, which is given by the overlap integral of shifted and unshifted 1D profiles over the evaluation length.

3.30

area power spectral density

APSD

squared magnitude of the two-dimensional Fourier transform of a two-dimensional residual surface height function using an appropriate weighting function

3.31

local slope

$\frac{dz}{dx}$

slope of the assessed profile at a position x_i

Note 1 to entry: The numerical value of the local slope, and thus the parameters, $R\Delta q$ and $W\Delta q$, depends critically on the ordinate spacing Δx .

Note 2 to entry: A formula for estimating the local slope is

$$\frac{dz_i}{dx} = \frac{1}{60\Delta x} (z_{i+3} - 9z_{i+2} + 45z_{i+1} - 45z_{i-1} + 9z_{i-2} - z_{i-3}) \quad (2)$$

The above formula should be used for the sample spacing stipulated in ISO 3274 for the filter used, where z_i is the height of the i^{th} profile point and Δx is the spacing between adjacent profile points.

Note 3 to entry: The local slope is unitless, however we express the slope as the arctangent of the surface slope in microradians.

Note 4 to entry: This differencing calculation always results in the loss of data points at each end of the slope profile.

[SOURCE: ISO 4287:1997, 3.2.9, modified — The symbol dZ/dX to the term was changed to $\frac{dz}{dx}$. In Note 1 $P\Delta q$ has been removed; the Notes 2 and 3 to entry have been added and the Figure has been removed.]

3.32

rms slope

$R\Delta q$

root mean square value of the local slope within the sampling length

Note 1 to entry: The rms slope is expressed in microradians.

3.33

area rms slope

$S\Delta q$

root mean square value of the local slope within the sampling area

Note 1 to entry: The area rms slope is expressed in microradians.

3.34

surface lay symbol

symbol indicating the lay of the surface profile parameter

Note 1 to entry: According to ISO 1302:2002, Table 2, the following symbols are used for surface lay; R (radial), C (circular), X (crossed), = (parallel to projection), \perp (perpendicular to projection), etc.

4 Description of surface texture

4.1 General

Surface texture is a global statistical characteristic of the profile of the optical surface. It is assumed for this document that the character and magnitude of the texture in any one area of the surface is similar to all other areas within the effective aperture of the same surface. This assumption is made so that a measurement made in one part of an indicated test region or surface can be considered representative of the entire test region or surface.

Unless stated otherwise, the indication of surface texture applies to surfaces before coating. This is an exception to the general statement in ISO 10110-1:2019, Clause 4, paragraph 1.

Materials having a crystal structure and production processes such as diamond turning can give rise to non-random surface texture. Care should be used in applying statistical surface properties for surface texture with these types of surfaces.

Because the magnitude of the measured roughness is a function of the spatial wavelengths considered, this document provides for the indication of the spatial band.

This document makes use of the terminology of profilometry, as specified in ISO 4287. Although the main effect of surface roughness is optical scattering, no reference is made to scattering measurements because there are causes of scattering other than texture (details of the relationship between surface texture and optical scattering are given in References [7] to [17]). Although the terminology in this document is that of profilometry, areal measurements (that is, measurements over a specified area) can also be used to characterise surface texture.

Surface texture specifications are applicable to matt surfaces as well as to optically smooth surfaces made by polishing or moulding. In this document, texture also refers to statistical properties of micro-roughness. Surface texture also refers to other statistical properties of the surface of longer scale-lengths, such as mid-spatial frequency waviness, which can be specified using root mean square (rms) roughness, rms slope, PSD and other statistical methods.

Depending on the application of a surface and the magnitude of surface height variation, one or more methods outlined below can be appropriate for describing surface texture numerically.

In calculating any statistical surface property, care should be taken regarding the spatial wavelength ranges over which the calculation is to be made. Both limits of the spatial band, in a long-scale length sense and a short-scale length sense, should be carefully considered. Significant errors can be introduced in the process of bandpass filtering or detrending of surface height data. See also References [18] to [20].

NOTE Computing the slope between adjacent sampled height points results in a large rms slope number that is usually dominated by instrument noise. To suppress the high frequency slope bias, one needs to first filter the height data with a low-pass filter before differentiating the height profile.

4.2 Description of matt surfaces

Matt surfaces shall be specified by indication of the rms height variation, Rq (as defined ISO 4287:1997, 4.2.2). This quantity depends on the range of spatial wavelengths to be considered. For this reason it is often necessary to specify the lower and upper limits of the spatial band.

If no spatial band is specified, the spatial band is assumed to be 0,002 5 mm to 0,08 mm.

In some cases, functional requirements can dictate a roughness criterion other than Rq or the other mentioned ones. In such cases, that other criterion shall be indicated as described in Clause 6 of ISO 1302:2002.

4.3 Description of optically smooth surfaces

4.3.1 Description methods

There are eight statistical methods of describing optically smooth surfaces which are explicitly defined in this document:

- a) by means of the rms roughness, Rq ;
- b) by rms waviness, Wq ;
- c) by area rms roughness, Sq ;
- d) by indicating a polish grade P1, P2, P3, or P4;
- e) by using a power spectral density (PSD) function;
- f) by using an area power spectral density (APSD) function;
- g) by specifying the rms slope, $R\Delta q$;
- h) by specifying the area rms slope, $S\Delta q$.

These methods can be used in combination, and can be used over various spatial bands in the same region.

Alternative means of describing surface texture parameters of interest such as skew (Rsk), kurtosis (Rku), average roughness (Ra), roughness amplitude (Rz), average waviness (Wa) or autocovariance (ACV), or their areal equivalents area skew (Ssk), area kurtosis (Sku), area average roughness (Sa), area roughness amplitude (Sz), or area autocovariance ($AACV$) are not supported explicitly in this document, but may be used in an analogous manner. In these cases, the terms shall be defined in a note or reference on the drawing.

4.3.2 Rms roughness and rms waviness

Optically smooth surfaces are commonly specified by indication of the rms roughness, Rq . For longer spatial wavelength ranges, the rms waviness, Wq , is used.

If the surface height variations obey certain statistical distribution properties, the rms value, Rq , can be related to the magnitude of the optical scattering (see [Annex A](#)). The rms description is incomplete without indicating the spatial band limits.

In the event that no spatial band is specified, the spatial band is assumed to be 0,002 5 mm to 0,08 mm for roughness (e.g. Rq) and 0,08 mm to 2,5 mm for waviness (e.g. Wq).

NOTE These default values can be significantly different depending on the requirements for Rq or Wq . Therefore, the correct requirements for Rq or Wq are necessary to ensure that they are consistent with the spatial band of the specification.

The rms computed over the band can vary depending on specific filtering implementation. The default is that the metrologist may use their choice of filters unless the designer communicates a required filtering scheme.

Optically smooth surfaces can also be specified by indication of the areal rms, Sq . In the event that no spatial band is specified, the spatial band is assumed to be 0,002 5 mm to 0,08 mm for Sq .

4.3.3 Polish grades

Optically smooth surfaces may be specified by polish grade. Polish grade shall be determined by estimating the rms roughness, Rq , over the spatial frequencies 0,002 mm to 1,0 mm and comparing to [Table 1](#) below. Only polish grades P1, P2, P3, and P4 are allowed.

Table 1 — Indication of the degree of smoothness by polish grade.

Polish grade designation	Estimated Rq over a spatial band of 0,002 mm to 1,0 mm
P1	≤8 nm
P2	≤4 nm
P3	≤2 nm
P4	≤1 nm

NOTE In previous versions of this standard, the polish grades were defined by a number of micro-defects per 10 mm trace.

4.3.4 Power spectral density (PSD) function

The PSD function is directly related to the frequency spectrum of the surface roughness. It allows a complete description of the surface texture characteristics, and is particularly useful for specifying super-smooth surfaces used in high technology applications, or in controlling mid-spatial frequency waviness on a surface. The PSD function description places no restrictions on the nature of, or the statistical properties of, the measured surface.

In the one-dimensional case, i.e. when the surface texture can be determined by measurement along a line on the surface, the PSD, expressed in $\text{nm}^2 \times \text{mm}$, can be modelled by [Formula \(3\)](#):

$$PSD = \frac{A}{f^B} \text{ for } \frac{1}{D} < f < \frac{1}{C} \quad (3)$$

where

f is the spatial frequency of the roughness or waviness, in inverse millimetres (mm^{-1});

B is the power to which the spatial frequency is raised;

C and D are the limits of the spatial band, in millimetres;

A is a constant.

The value of B shall be greater than zero. (For many real surfaces, $1 < B < 3$, see Reference [\[21\]](#)).

In this way, the surface texture requirement can be given by specifying the four values A , B , C and D , for which [Formula \(3\)](#) shall hold.

This one dimensional PSD can be calculated for any line of data. Such a line of data can be generated from 1D surface profilometry along any direction on a surface or by integrating an area PSD (described in [4.3.5](#)) along one dimension. The calculation of the PSD from the line data is described in Reference [\[17\]](#) and elsewhere. Note that windowing of the data is required prior to calculation of the PSD; such windowing can be described in a note, or is assumed to be a Hamming filter as described in

Reference [20]. In the event that the directionality of the PSD is considered significant, a surface lay symbol is added to the surface texture specification.

The Cartesian 1D PSD of a 2D residual surface can be calculated from the measured surface by taking any single linear slice of the data, e.g. the slice of data for all $Z(x)$ at $y = 0$, or any vertical slice of the data, e.g. the slice of data for all $Z(y)$ at $x = 10$ mm. If a specific linear slice or set of linear slices is desired, this shall be indicated in a note. These line traces can be used as 1D residual data for PSD calculations. The result of the PSD calculation often is strongly dependent on the way the data is sliced.

The polar coordinate 1D PSD of a 2D residual surface can be calculated by taking a radial slice of the data, e.g. the slice of data for all $Z(r)$ at an angle $\theta = 0^\circ$, or circumferential slice of the data, e.g. the slice of data for all $Z(\theta)$ at $r = 10$ mm. If a specific radial or circumferential slice or set of slices is desired, this shall be indicated in a note. These line traces can be used as 1D residual data for PSD calculations.

In the case of a circumferential slice, no windowing shall be applied.

If an optic is produced with a high likelihood of a center singularity, an inner diameter specification is recommended to avoid inclusion of the singularity in the average.

In the event that no spatial band is specified, the PSD is expected to be evaluated with a spatial band of 0,08 mm to 2,5 mm.

It is recommended that both limits of the spatial band are indicated in drawings, since spatial bands depend on the applications, wavelengths of use, and measurement equipment available.

4.3.5 Area power spectral density (APSD) function

The APSD function is a two-dimensional equivalent function to the one dimensional PSD described above.

In the two-dimensional case, i.e. when the surface texture is described as an array of points such as $Z(x,y)$ or $Z(r,q)$, the APSD, expressed in $\text{nm}^2 \times \text{mm}^2$, can be modelled by [Formula \(4\)](#):

$$APSD = \frac{A'}{B' \left(f_x^2 + f_y^2 \right)^2} \quad \text{for} \quad \frac{1}{C'} \leq \sqrt{f_x^2 + f_y^2} \leq \frac{1}{D'} \quad (4)$$

where

f_x, f_y are the spatial frequencies of the roughness or waviness, in inverse millimetres (mm^{-1});

B' is the power to which the spatial frequencies are raised;

C' and D' are the limits of the spatial band, in millimetres;

A' is a constant.

The value of B' shall be greater than zero. (For many real surfaces, $1 < B < 3$, see Reference [21]).

In this way, the surface texture requirement can be given by specifying the four values A' , B' , C' and D' , for which [Formula \(4\)](#) shall hold.

This two-dimensional PSD can be calculated for any array of data. The calculation of the APSD from the array of data is described in Reference [17] and elsewhere. Note that windowing of the data is required prior to calculation of the PSD; such windowing can be described in a note, or is assumed to be a Hamming filter as described in Reference [20].

In the event that no spatial band is specified, the APSD is expected to be evaluated with a spatial band of 0,08 mm to 2,5 mm.

It is recommended that both limits of the spatial band are indicated in drawings, since spatial bands depend on the applications, wavelengths of use, and measurement equipment available.

NOTE The Cartesian 1D PSD can be calculated from the 2D APSD.

4.3.6 Rms slope

Optically smooth surfaces can also be specified by indication of the rms slope, $R\Delta q$.

If the surface slope variations obey certain statistical distribution properties, the rms value, $R\Delta q$, can be related to the image quality. The rms slope description is incomplete without indicating the spatial band limits.

In the event that no spatial band is specified, the surface slope spatial band is assumed to be 0,08 mm to 2,5 mm.

4.3.7 Area rms slope

Optically smooth surfaces can also be specified by indication of the area rms slope, $S\Delta q$.

The rms slope description is incomplete without indicating the spatial band limits.

In the event that no spatial band is specified, the surface slope spatial band is assumed to be 0,08 mm to 2,5 mm.

NOTE The area rms slope is defined as the rms of the local slope for all points within the areal field. That is, the Area rms slope is described by the following formula:

$$S\Delta q = \sqrt{\frac{1}{A} \iint \left[\left(\frac{\delta z}{\delta x} \right)^2 + \left(\frac{\delta z}{\delta y} \right)^2 \right] dx dy .}$$

5 Indication in drawings

5.1 General

The symbols for indicating surface texture in drawings shall be in accordance with ISO 1302, if necessary, they can be modified as described below.

5.2 Indication for matt surface texture

The matt surface texture is indicated according to ISO 1302:2002, Clause 5, with the addition of the letter G [for "Ground"¹⁾] above the horizontal line, as shown in [Figure 2](#). The maximum permissible rms roughness Rq in micrometres, is indicated under the horizontal line. When a single value of Rq is given, it represents the upper limit of the surface roughness parameter. When the roughness is not permitted to lie below a certain value the upper and lower limits of the rms roughness is indicated with a bilateral tolerance according to ISO 1302:2002, 6.6. The upper limit of the rms roughness is identified with "U", and the lower limit is identified with "L". See [Figure 2](#) b).

The spatial band can be indicated under the horizontal line, as shown in [Figure 2](#) a). The upper limit is separated from the lower limit by a hyphen, and the spatial band is separated from the Rq notation by an oblique stroke (/). Spatial band limits shall be expressed in millimetres.

In the event that only the upper limit of the spatial band is to be specified, it is given as shown in [Figure 2](#) b), after the hyphen.

EXAMPLE 1 0,002 5-0,8/ Rq 2 (example where the spatial band is specified); see [Annex B](#).

1) The letter "G" is used to denote all matt surfaces, including those not produced by brittle grinding, e.g. etching.

EXAMPLE 2 $-0,8/Rq\ 2$ (example where only the upper limit of the spatial band is specified); see [Annex B](#).

NOTE The default evaluation length is five times the upper limit of the spatial band.



a) Indication for matt surface texture with $Rq \leq 2$ mm over a spatial band of 0,002 5 mm to 0,8 mm


b) Indication for matt surface texture with $0,05\ \mu\text{m} \leq Rq \leq 2$ mm and an upper limit of spatial band of 5 mm

Figure 2 — Indication for matt surface texture

5.3 Indication for optically smooth surface texture

5.3.1 Optically smooth surface without quantitative modification

The indication for optically smooth surface texture shall include the letter P [for “Polished”²⁾] above the horizontal line, as shown in [Figure 3](#). The use of the letter P alone means that no quantification of the surface texture is required but that the surface shall be smooth.

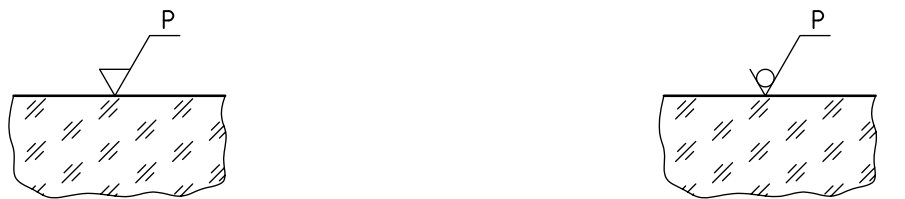

a) Polished surface

b) Moulded surface

Figure 3 — Indication for optically smooth surface texture without quantitative modifiers

5.3.2 Indication of smoothness by polish grade

The degree of surface smoothness can be indicated by placing a grade number between 1 and 4 to the right of the letter P, as shown in [Figure 4](#). The range of the corresponding permissible roughness is given by grade in [Table 1](#).




Figure 4 — Indication for optically smooth surface with quantitative modifiers; polish grade with $Rq \leq 0,004\ \mu\text{m}$ over a spatial band of 0,002 mm to 1,0 mm

2) The letter “P” is used to indicate all optically smooth surfaces, including those not produced by polishing, e.g. moulded or float glass surfaces.

5.3.3 Indication of rms roughness and rms waviness

The rms roughness Rq or the rms waviness Wq is indicated by placing the maximum permissible value of the rms, expressed in micrometres, under the horizontal line, as shown in [Figure 5](#). In this example, the rms roughness specification below the horizontal line is equivalent to a polish grade P3.

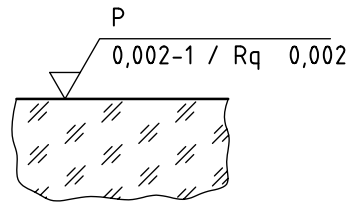


Figure 5 — Indication for optically smooth surface with quantitative modifiers; polish grade of $Rq \leq 0,002 \mu\text{m}$ over a spatial band of 0,002 mm to 1 mm

A lower limit of the spatial band or alternatively a spatial band can be indicated under the horizontal line, separated from the indication for rms roughness or rms waviness by an oblique stroke (/). Limits of spatial bands shall be given in mm.

EXAMPLE 1 $-1,0/Rq 0,002$ (surface roughness with only the upper limit of spatial band); see [Annex B](#).

EXAMPLE 2 $0,002-1,0/Rq 0,002$ (surface roughness with spatial band); see [Annex B](#).

EXAMPLE 3 $0,5-2,5/Wq 0,002$ (surface waviness with spatial band); see [Annex B](#).

NOTE The evaluation length is five times the minimum sampling length.

This indication may be complemented by an indication of the polish grade according to [5.3.2](#).

5.3.4 Indication of PSD function specification

The maximum permissible value of the PSD function is indicated by placing the letters PSD and the values for A and B , as defined in [4.3.4](#) and separated by an oblique stroke (/), under the horizontal line, as shown in [Figure 6](#). The upper and lower limits of the spatial band, C and D , expressed in millimetres, are placed under the horizontal line before the PSD note separated by an oblique stroke (/), as shown in [Figure 6](#).

This indication can be complemented by an indication of the smoothness by polishing in accordance with [5.3.2](#).

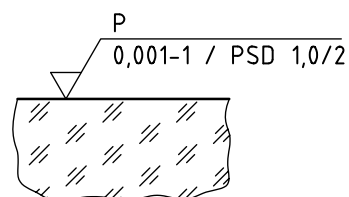


Figure 6 — Indication for an optically smooth surface; $PSD \leq \frac{1,0}{f^2} (\text{nm}^2 \times \text{mm})$ over a spatial band of 0,001 mm to 1 mm

5.3.5 Indication of APSD function specification

The maximum permissible value of the APSD function is indicated by placing the letters APSD and the values for A' and B' , as defined in [4.3.5](#) and separated by an oblique stroke (/), under the horizontal line, as shown in [Figure 7](#). The upper and lower limits of the spatial band, C' and D' , expressed in millimetres,

are placed under the horizontal line before the APSD note separated by an oblique stroke (/), as shown in [Figure 7](#).

This indication can be complemented by an indication of the smoothness by polishing in accordance with [5.3.2](#).

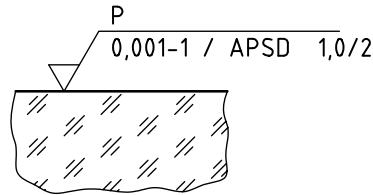


Figure 7 — Indication for an optically smooth surface; $APSD \leq \frac{1,0}{(f_x^2 + f_y^2)}$ ($\text{nm}^2 \times \text{mm}^2$) over a spatial band of 0,001 mm to 1 mm

5.3.6 Indication of rms or area rms slope specification

The rms slope $R\Delta q$ or its' areal equivalent, $S\Delta q$ is indicated by placing the maximum permissible value of the rms slope, expressed in microradians, under the horizontal line as shown in [Figure 8](#).



a) Rms slope

b) Areal rms slope

Figure 8 — Indication for an optically smooth surface; rms slope or areal rms slope of $\leq 0,7 \mu\text{rad}$ for a spatial band of 0,01 mm to 5 mm

A spatial band can be indicated under the horizontal line, as shown in [Figure 8](#). Spatial bands shall be expressed in millimetres.

5.3.7 Indication of lay

In the event that the orientation of the surface texture parameter is significant, the addition of a surface lay symbol can be used. The letter C indicates a circular lay, while the letter R indicates a radial lay, as shown in [Figure 9](#). Additional lay symbols are given in ISO 1302:2002, Table 2. If no indication of lay is given, then the surface parameter is assumed to apply for all orientations.

On rotationally symmetric parts, the lay indications C and R (for circular and radial) are recommended. On square or rectangular parts, the lay indications = and \perp are recommended.

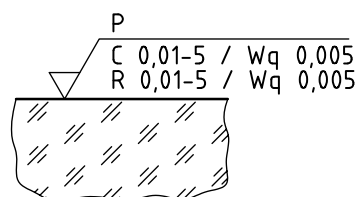


Figure 9 — Indication for optically smooth surface with $Wq \leq 0,005 \mu\text{m}$ for a spatial band of 0,01 mm to 5 mm, evaluated radially and circularly

5.4 Location

The indication of the surface roughness shall be located on the drawing as described in ISO 10110-1. In tabular drawings (see also ISO 10110-1), the texture symbol and indication can be shown either in the drawing field or in the appropriate surface fields. In alternate drawings the tip of the texture symbol shall be in contact with the line representing the surface or with a corresponding subsidiary line (see [Figures 2 to 9](#), as well as the examples given in ISO 10110-1).

Annex A (informative)

Relationship between surface texture and scattering characteristic of textured surfaces

It has been shown that there is an analytical expression relating surface texture to the angular distribution of light scattered by textured surfaces, see Reference [21]. Since scattered light can seriously compromise optical system performance and the measurement of surface texture or roughness tends to be easier than making scattered light measurements, it is useful to understand the relationship between surface roughness and scattered light.

It has also been shown experimentally that most polished surfaces scatter light according to a power law, see References [9] and [10]. Similarly a relationship between the two-dimensional power spectral density (PSD) of surface roughness or texture and the differential angular scatter has been obtained theoretically, see Reference [11]. Also the one-dimensional PSD, the raw data for which can be obtained with a one-dimensional profilometer, is simply related to the two-dimensional form for isotropic surfaces. It was shown that the one-dimensional PSD can be expressed as


$$PSD = \frac{A}{f^B}$$

where

- A is a constant, expressed in $\text{nm}^2 \times \text{mm}^{1-B}$;
- f is the spatial frequency of the surface roughness, in reciprocal millimetres (mm^{-1});
- B is the value of the exponent (or power) with which the PSD falls off with increasing spatial frequency. For most “real” surfaces, $1 < B < 3$.

This description of the PSD function is valid for a given range of spatial frequencies. The minimal spatial frequency is $1/D$, where D is the sampling length over which the sample was measured. The maximal spatial frequency is $1/C$, where C is the shortest lateral feature on the surface that the measuring instrument can resolve (C and D are expressed in millimetres).

[Figure A.1](#) gives an example of three PSD functions for the case in which $B = 2$, and illustrates that the surface texture has smaller features as A is made smaller. These curves are for illustrative purposes only.

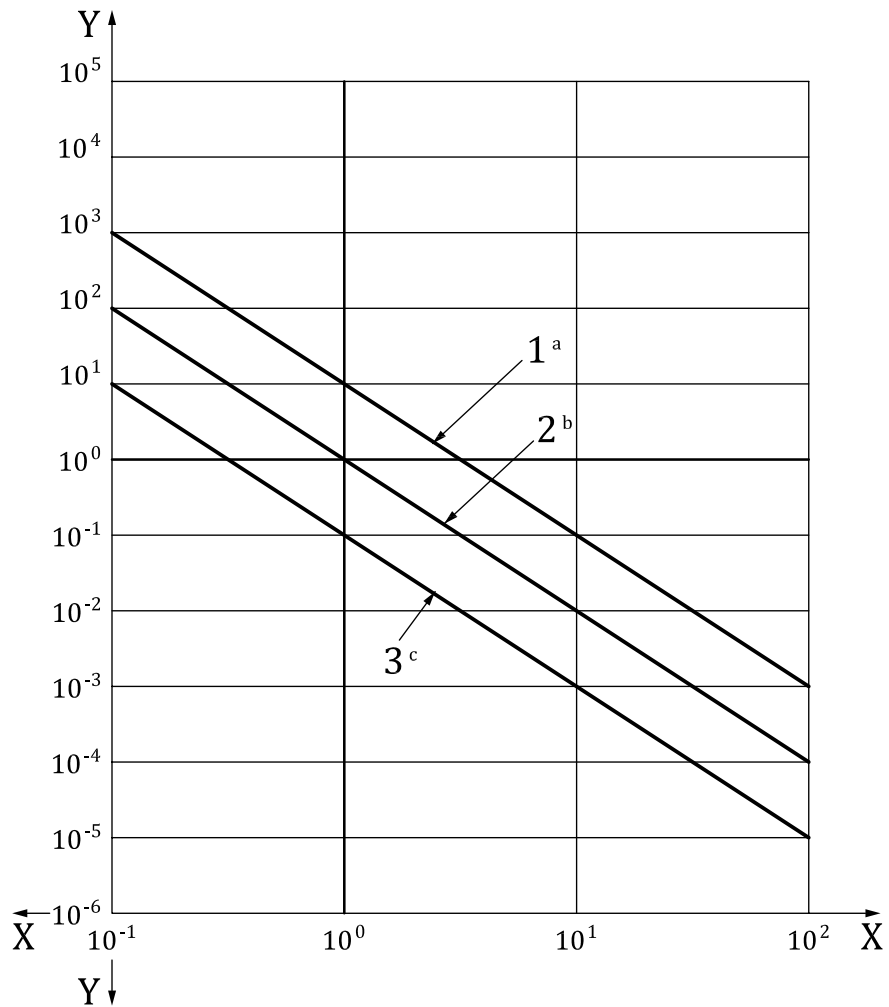

Key

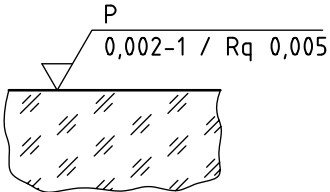
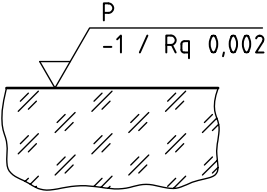
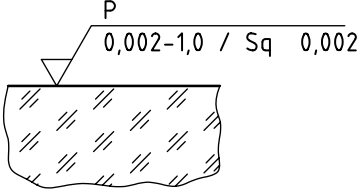
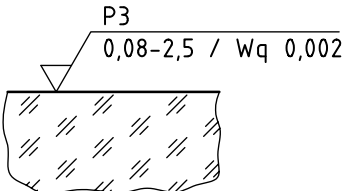
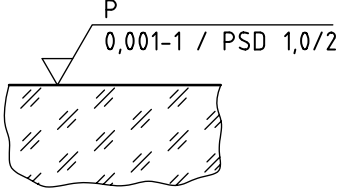
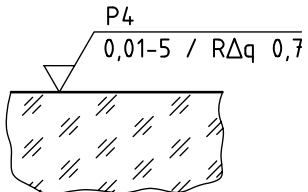
- X spatial frequency, in mm^{-1}
- Y power spectral density, $\text{nm}^2 \times \text{mm}$
- 1 ordinary polish PSD
- 2 precision polish PSD
- 3 super polish PSD
- a $A = 10 \text{ nm}^2 \times \text{mm}^{-1}$.
- b $A = 1 \text{ nm}^2 \times \text{mm}^{-1}$.
- c $A = 0,1 \text{ nm}^2 \times \text{mm}^{-1}$.





Figure A.1 — Examples of three PSD functions for $B = 2$


Annex B (informative)

Examples of indication of surface texture requirements

Reference Number	Requirement	Example
B.1	Optical surface: — matt surface. Surface roughness: — a single, unilateral/upper specification limit; — $Rq \leq 2 \mu\text{m}$; — spatial band from 0,002 5 mm to 0,8 mm.	
B.2	Optical surface: — matt surface. Surface roughness: — a single, unilateral/upper specification limit; — $Rq \leq 2 \mu\text{m}$; — upper limit of spatial band 0,8 mm.	
B.3	Optical surface: — matt surface. Surface roughness: — bilateral specification limit; — upper specification limit $Rq = 2 \mu\text{m}$; — lower specification limit $Rq = 0,05 \mu\text{m}$; — upper limit of spatial band 5 mm.	
B.4	Optical surface: — optically smooth surface; — polish grade, no requirement; — numerical limit value of roughness, no requirement.	
B.5	Optical surface: — optically smooth surface; — polish grade 2.	
B.6	Optical surface: — optically smooth moulded surface; — numerical limit value of roughness, no requirement.	

Reference Number	Requirement	Example
B.7	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface. <p>Surface roughness:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $Rq \leq 0,005 \mu\text{m}$; — spatial band from 0,002 mm to 1 mm. 	
B.8	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface. <p>Surface roughness:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $Rq \leq 0,002 \mu\text{m}$; — upper limit of spatial band 1 mm. 	
B.9	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface. <p>Surface roughness:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $Sq \leq 0,002 \mu\text{m}$; — spatial band from 0,002 mm to 1 mm. 	
B.10	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface; — polish grade 3. <p>Surface waviness:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $Wq \leq 0,002 \mu\text{m}$; — spatial band from 0,08 mm to 2,5 mm. 	
B.11	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface. <p>Surface power spectral density:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $PSD \leq 1,0/f^2 \text{ (nm}^2 \times \text{mm)}$; — spatial band from 0,001 mm to 1 mm. 	
B.12	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface; — polish grade 4. <p>Surface slope:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $R\Delta q \leq 0,7 \mu\text{rad}$; — Spatial band from 0,01 mm to 5 mm. 	

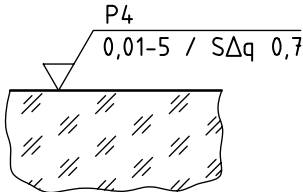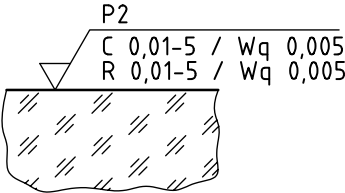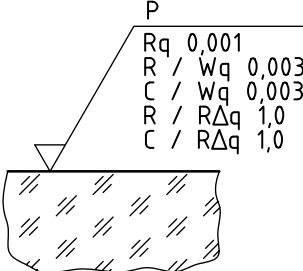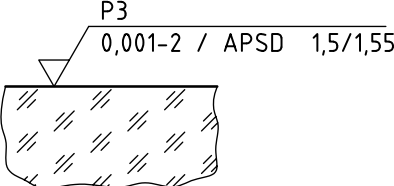Reference Number	Requirement	Example
B.13	Optical surface: — optically smooth surface; — polish grade 4. Surface slope: — a single, unilateral/upper specification limit; — $S\Delta q \leq 0,7 \mu\text{rad}$; — Spatial band from 0,01 mm to 5 mm.	 <p>P4 0,01-5 / $S\Delta q$ 0,7</p>
B.14	Optical surface: — optically smooth surface; — polish grade 2. Surface waviness: — two unilateral/upper specification limits; — $Wq \leq 0,005 \mu\text{m}$; — spatial band from 0,01 mm to 5 mm; — surface lay, radial from center and circular around centre.	 <p>P2 C 0,01-5 / Wq 0,005 R 0,01-5 / Wq 0,005</p>
B.15	Optical surface: — optically smooth surface. Surface roughness: — a single, unilateral/upper specification limit; — $Rq \leq 0,001 \mu\text{m}$; — default spatial band from 0,002 5 mm to 0,08 mm; — surface lay, no requirement. Surface waviness: — two unilateral/upper specification limits; — $Wq \leq 0,003 \mu\text{m}$; — default spatial band from 0,08 mm to 2,5 mm; — surface lay radial from centre and circular around centre. Surface slope: — two unilateral/upper specification limits; — $R\Delta q \leq 1,0 \mu\text{rad}$; — default spatial band from 0,08 mm to 2,5 mm; — surface lay radial from centre and circular around centre.	 <p>P Rq 0,001 R / Wq 0,003 C / Wq 0,003 R / $R\Delta q$ 1,0 C / $R\Delta q$ 1,0</p>
B.16	Optical surface: — optically smooth surface; — polish grade 3. Surface power spectral density: — a single, unilateral/upper specification limit; — $2D PSD \leq 1,5/f^{1,55} (\text{nm}^2 \times \text{mm}^2)$; — spatial band from 0,001 mm to 2 mm.	 <p>P3 0,001-2 / APSD 1,5/1,55</p>

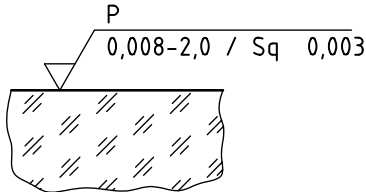Reference Number	Requirement	Example
<p>B.17</p>	<p>Optical surface:</p> <ul style="list-style-type: none"> — optically smooth surface. <p>Surface roughness:</p> <ul style="list-style-type: none"> — a single, unilateral/upper specification limit; — $Sq \leq 0,003$; — Spatial band 0,008 mm to 2,0 mm. 	

Bibliography

- [1] ISO 10110-5, *Optics and photonics — Preparation of drawings for optical elements and systems — Part 5: Surface form tolerances*
- [2] ISO 10110-12, *Optics and photonics — Preparation of drawings for optical elements and systems — Part 12: Aspheric surfaces*
- [3] ISO 10110-19, *Optics and photonics — Preparation of drawings for optical elements and systems — Part 19: General description of surfaces and components*
- [4] ISO 10110-7, *Optics and photonics — Preparation of drawings for optical elements and systems — Part 7: Surface imperfections*
- [5] ISO 3274:1996, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Nominal characteristics of contact (stylus) instruments*
- [6] ISO 16610-21, *Geometrical product specifications (GPS) — Filtration — Part 21: Linear profile filters: Gaussian filters*
- [7] CHURCH E.L., JENKINSON H.A., ZAVADA J.M., Relationship between surface scattering and microphotographic features. *Opt. Eng.* 1979, **18**, pp. 125-36
- [8] CROCE P., PROD'HOMME L., Analyse des surfaces polies par la distribution spatiale de la lumière diffusée. *Opt. Commun.* 1980, **35**, pp. 20-24
- [9] CROCE P., PROD'HOMME L., Sur les conditions d'application de la diffusion optique à la caractérisation des surfaces rugueuses. *J. Opt.* 1984, **15**, pp. 95-104
- [10] STOVER J.C. *Optical Scattering: Measurement and Analysis*, McGraw-Hill, New York, 1990
- [11] AIKENS D.M., ROUSSEL A., BRAY M., Derivation of preliminary specifications for transmitted wavefront and surface roughness for large optics used in inertial confinement fusion, Proc. SPIE Monterey SSLA conference, May 1995
- [12] GOODMAN J.W. *Statistical Optics*, John Wiley and Sons, Inc. New York, 1995
- [13] HARVEY J.R., KOTHA A., Scattering effects from residual optical fabrication errors, *Proc. SPIE*, 1995, **2576**, pp. 155-174
- [14] BENNETT J.M., MATSSON L., Introduction to surface roughness and scattering. Optical Society of America, 2nd Edition, Washington, 1999
- [15] YOUNGWORTH R.N., STONE B.D., Simple estimates for the effects of mid-spatial frequency surface errors on image quality, *Applied Optics*. 2000, **39**(13), pp. 2198-2209
- [16] YOUNGWORTH R.N., GALLAGHER B.B., STAMPER B.L., An overview of power spectral density (PSD) calculations, Proc. SPIE 5869-34, 2005, pp. 206-216
- [17] SHIBUYA M. et al. , Classification of undulated wavefront aberration in projection optics by considering its physical effects, *Optical Engineering*. 2007, **46**(5), pp. 053001-6
- [18] BLACKMAN R.B., TUKEY J.W. *The Measurement of Power Spectra from the Point of View of Communications Engineering*, Dover Publications, New York, 1959
- [19] HAMMING R.W. *Digital Filters*, Prentice-Hall, Englewood Cliffs, NJ (1977)
- [20] CHETWYND D.G., Slope Measurement in Surface Texture Analysis, *Journal of Mechanical Engineering Science* **20**, pp. 115-119 (1978)

- [21] ROGERS J.R., Slope error tolerances for optical surfaces. Presentation at OptiFab Conference, SPIE TD04-4, May 2007
- [22] ISO 25178-2, *Geometrical product specifications (GPS) — Surface texture: Areal — Part 2: Terms, definitions and surface texture parameters*

[\(Continued from second cover\)](#)

<i>International Standards</i>	<i>Corresponding Indian Standards</i>	<i>Degree of Equivalence</i>
ISO 4287 : 1997 Geometrical product specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters	IS 18432 (Part 2) : 2023/ISO 21920-2 : 2021 Geometrical product specifications (GPS) — Surface texture — Profile: Part 2 Terms, definitions and surface texture parameters (ISO 4287 has been amalgamated into ISO 21920)	Identical
ISO 10110-1 Optics and photonics — Preparation of drawings for optical elements and systems — Part 1: General	IS 5920 (Part 1) : 2024/ISO 10110-1 : 2019 — Optics and photonics — Preparation of drawings for optical elements and systems: Part 1 General	Identical

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website-www.bis.gov.in or www.standardsbis.in.

This Indian Standard has been developed from Doc No.: PGD 39 (23505).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

Central : 601/A, Konnectus Tower -1, 6th Floor,
DMRC Building, Bhavbhuti Marg, New
Delhi 110002

Telephones

{ 2323 7617

Eastern : 8th Floor, Plot No 7/7 & 7/8, CP Block, Sector V,
Salt Lake, Kolkata, West Bengal 700091

{ 2367 0012
{ 2320 9474

Northern : Plot No. 4-A, Sector 27-B, Madhya Marg,
Chandigarh 160019

{ 265 9930

Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113

{ 2254 1442
{ 2254 1216

Western : 5th Floor/MTNL CETTM, Technology Street, Hiranandani Gardens, Powai
Mumbai 400076

{ 25700030
{ 25702715

Branches : AHMEDABAD, BENGALURU, BHOPAL, BHUBANESHWAR, CHANDIGARH, CHENNAI, COIMBATORE, DEHRADUN, DELHI, FARIDABAD, GHAZIABAD, GUWAHATI, HARYANA (CHANDIGARH), HUBLI, HYDERABAD, JAIPUR, JAMMU, JAMSHEDPUR, KOCHI, KOLKATA, LUCKNOW, MADURAI, MUMBAI, NAGPUR, NOIDA, PARWANOO, PATNA, PUNE, RAIPUR, RAJKOT, SURAT, VIJAYAWADA.