

अपघर्षी कण — नमूने लेना और विघटित
करना
(पहला पुनरीक्षण)

**Abrasive Grains — Sampling and
Splitting**
(*First Revision*)

ICS 25.100.70

© BIS 2024

© ISO 2015



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002
www.bis.gov.in www.standardsbis.in

June 2024

Price Group 5

NATIONAL FOREWORD

This Indian Standard (First Revision) which is identical to ISO 9138 : 2015 'Abrasive grains — Sampling and splitting' issued by the International Organization for Standardization (ISO), was adopted by the Bureau of Indian Standards on recommendation of the Abrasives Sectional Committee and approval of the Production and General Engineering Division Council.

This standard was first published in 2003. This revision of this standard has been undertaken to align it with latest version of ISO 9138.

The major changes have been incorporated in this revision are as follows:

- a) Many more detailed specifications are included in the entire document;
- b) Requirements for four different types of sampling are specified;
- c) A detailed description of the splitter is included;
- d) Whole sampling and splitting procedure described in much more detail for big-bags and paper-bags; and
- e) A detailed specification of sampling preparation included.

The text of ISO standard has been approved as suitable for publication as an Indian Standard without deviations. Certain conventions are, however, not identical to those used in Indian Standards. Attention is particularly drawn to the following:

- a) Wherever the words 'International Standard' appear referring to this standard, they should be read as 'Indian Standard'; and
- b) Comma (,) has been used as a decimal marker while in Indian Standards, the current practice is to use a point (.) as the decimal marker.

In this adopted standard, reference appears to certain International Standards for which Indian Standards also exist. The corresponding Indian Standards, which are to be substituted in their respective places, are listed below along with their degree of equivalence for the editions indicated:

<i>International Standard</i>	<i>Corresponding Indian Standard</i>	<i>Degree of Equivalence</i>
ISO 6344-1 Coated abrasives — Grain size analysis — Part 1: Grain size distribution test	IS 15287 (Part 1) : 2003/ISO 6344-1 : 1998 Coated abrasives — Grain size analysis: Part 1 Grain size distribution test	Identical
ISO 8486-1 Bonded abrasives — Determination and designation of grain size distribution — Part 1: Macrogrits F4 to F220	IS 15288 (Part 1) : 2003/ISO 8486-1 : 1996 Bonded abrasives — Determination and designation of grain size distribution : Part 1 Macrogrits F 4 to F 220	Identical
ISO 8486-2 Bonded abrasives — Determination and designation of grain size distribution — Part 2: Microgrits F230 to F2000	IS 15288 (Part 2) : 2018/ISO 8486-2 : 2007 Bonded abrasives — Determination and designation of grain size distribution: Part 2 Microgrits F 230 to F 1200 (<i>first revision</i>)	Identical

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*).' The number of significant places retained in the rounded-off value should be the same as that of the specified value in this standard.

Contents

Page

1	Scope	1
2	Normative references	1
3	Apparatus	1
	3.1 Sampling thief.....	1
	3.1.1 General.....	1
	3.1.2 Sampling thief type 1 (with holes).....	2
	3.1.3 Sampling thief type 2 (with one slot).....	2
	3.1.4 Sampling thief type 3 (with three to five slots).....	2
	3.1.5 Sampling thief type 4 (motor driven).....	2
	3.2 Splitter.....	3
4	Procedure	4
	4.1 General.....	4
	4.2 Sampling from big-bags or “drums”.....	4
	4.2.1 With sampling thief, type 1.....	4
	4.2.2 With sampling thief (motor driven), type 4.....	5
	4.3 Sampling from paper-bags.....	5
	4.4 Sample preparation.....	5
	4.4.1 General.....	5
	4.4.2 Splitting by using a splitter.....	5
	4.4.3 Splitting by quartering manually.....	5
	4.5 Segregation.....	5
	Bibliography	6

Indian Standard

ABRASIVE GRAINS — SAMPLING AND SPLITTING

(*First Revision*)

1 Scope

This International Standard specifies the apparatus and the method for sampling and splitting of a lot of abrasive grains, to be used in the comparative testing of uniformly produced abrasive grains.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6344-1, *Coated abrasives — Grain size analysis — Part 1: Grain size distribution test*

ISO 8486-1, *Bonded abrasives — Determination and designation of grain size distribution — Part 1: Macrogrits F4 to F220*

ISO 8486-2, *Bonded abrasives — Determination and designation of grain size distribution — Part 2: Microgrits F230 to F2000*

3 Apparatus

3.1 Sampling thief

3.1.1 General

The sampling thieves described in [3.1.2](#), [3.1.3](#), [3.1.4](#), or [3.1.5](#) shall be used.

The sampling thief shall be made from seamless steel tubing of inside diameter of 25 mm to 30 mm and a wall thickness of 1,5 mm to 3,0 mm. The length is depending of the packaging, but shall be 90 % at an angle of 45° of the packaging from top to bottom. The tube shall be pointed at one end. Holes shall be bored in a straight line.

Length, diameter, and hole or slot size shall fit to the packaging type and size in order to ensure representative samples.

The hole or slot sizes are depending on the grain size (see ISO 6344-1, ISO 8486-1, and ISO 8486-2) and shall be according to [Table 1](#).

Table 1 — Diameter of holes or width of slot(s) of sampling thieves

Grain size	Diameter of holes or width of slot(s) in mm
F4 to F10	25
F12 to F800 or P12 to P2500	10
F1000 to F2000	20

3.1.2 Sampling thief type 1 (with holes)

The sampling thief type 1 with holes shall be used for sampling from “drums” or big-bags. The sampling thief type 1 shall have a “T” handle or an equivalent handle at the other end.

[Figure 1](#) shows an example for a sampling thief type 1.

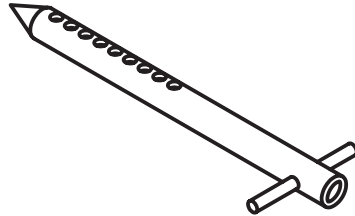


Figure 1 — Example for a sampling thief type 1

3.1.3 Sampling thief type 2 (with one slot)

The sampling thief type 2 (with one slot) is recommended when sampling from small bags. Length of sampling device is typically 500 mm, and slot is 10 mm in width and 250 mm in length.

[Figure 2](#) shows an example for a sampling thief type 2.

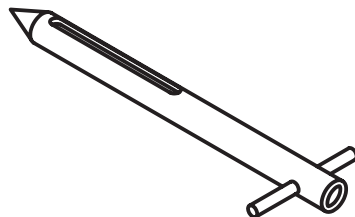


Figure 2 — Example for a sampling thief type 2

3.1.4 Sampling thief type 3 (with three to five slots)

The sampling thief type 3 (with three to five slots) is recommended when sampling from small bags. Length of sampling device is typically 500 mm. This equipment is provided with three slots of 10 mm in width and 80 mm in length, 50 mm between slots.

[Figure 3](#) shows an example for a sampling thief type 3.

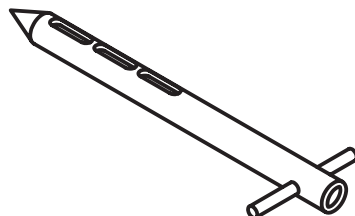


Figure 3 — Example for a sampling thief type 3

3.1.5 Sampling thief type 4 (motor driven)

Several types of motor-driven sampling thieves are commercially available. They shall be used for compacted powders. This is to ensure representative sampling from the compacted bag. Compacted powders occur when the material has been stored for a long time or powder has been transported.

[Figure 4](#) shows an example for a sampling thief type 4.

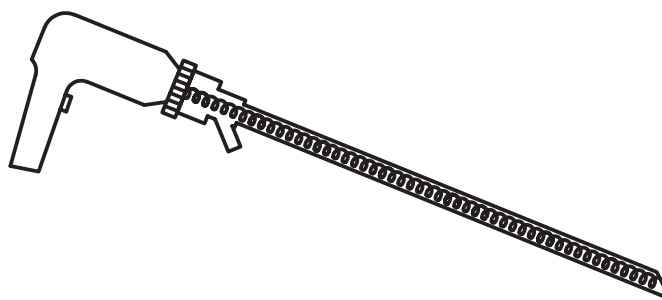


Figure 4 — Example for a sampling thief type 4

3.2 Splitter

A riffle-type sampler (commonly known as a Jones sampler) is generally used (see [Figure 5](#)). It consists of a hopper made of a series of slots that are constructed to discharge alternately in opposite directions.

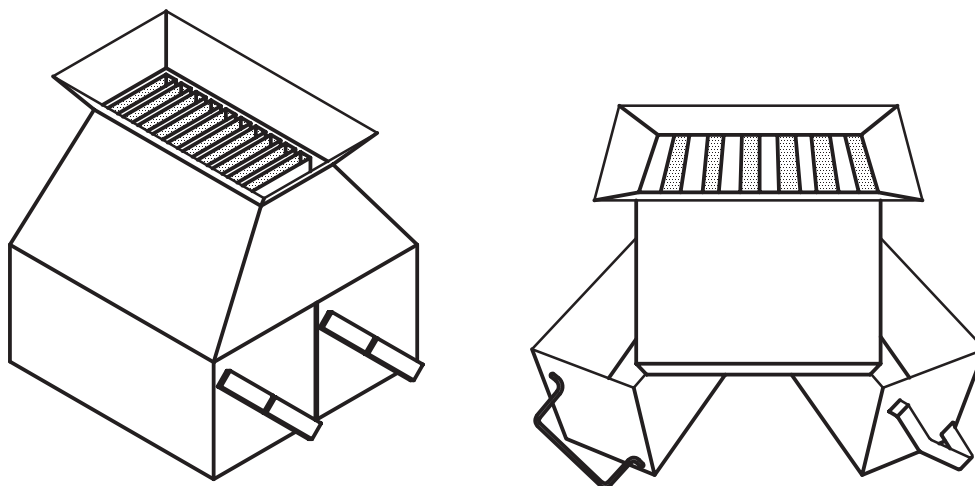


Figure 5 — Example of a riffle-type sampler

The sizes of the slots and the splitter are depending on the grain size and shall be according to [Table 2](#).

Table 2 — Sample splitter external dimensions (capacity) to suit relevant sample sizes

Grain size	Sample mass in kg	Slot width in mm
F4 to F220 or P12 to P220	≤10	10
	>10	20
F230 to F2500 or P240 to P3000	<1	7

Alternatively to the use of a splitter, samples may be quartered manually. see [4.4](#).

4 Procedure

4.1 General

During transportation and storage, segregation might occur. Samples shall be a representative homogeneous mixture of the grain size under investigation. To obtain a representative sample, the sample thief shall be completely filled during sampling. See also [4.5](#).

4.2 Sampling from big-bags or “drums”

4.2.1 With sampling thief, type 1

Press the sampling thief at an angle of 60° (see [Figure 6](#)) into the packaging unit with the holes or slot(s) facing downwards. Press down until the sample thief has reached 90 % of the packaging diagonal. Then twist the tube through 180° and allow it to fill. Withdraw the tube, taking care not to rotate the thief, and remove the sample. Take at least two samples from each big-bag. In case of a defect, repeat sampling from a different part of the same big-bag or, if available, from a different big-bag.

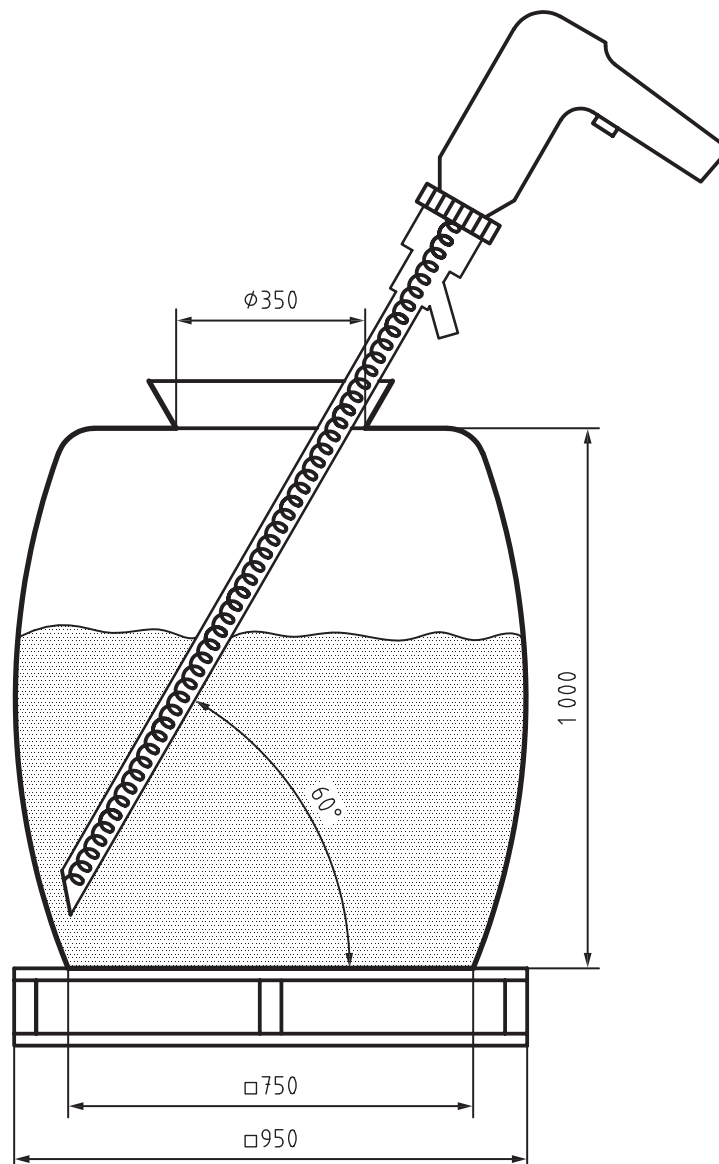


Figure 6 — Sampling big-bags

4.2.2 With sampling thief (motor driven), type 4

Insert the sampling thief at an angle of 60° (see [Figure 6](#)) to horizontal into the container at uniform movement. Make sure that the sampling thief reaches the bottom of the container. The motor should be stopped while the sampling thief is redrawn from the container before it is emptied.

Repeat the procedure until a representative sample is obtained.

4.3 Sampling from paper-bags

Sampling thieves type 2 or type 3 shall only be used in horizontal orientation. Press into the packaging with holes or slot(s) facing downwards. Press in until the sample thief has reached 90 % of the packaging horizontal length. Then twist the tube through 180° and allow it to fill. Withdraw the tube, taking care not to rotate the thief, and remove the sample. Repeat this procedure from all sides of the pallet to ensure representative sample. For procedure, see [Figure 7](#).

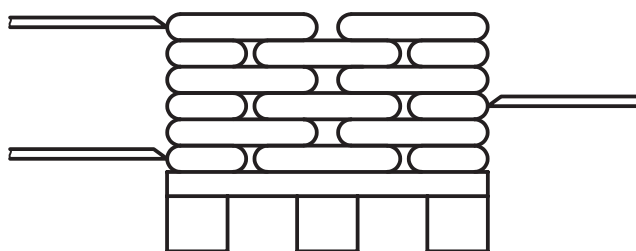


Figure 7 — Sampling paper-bags

4.4 Sample preparation

4.4.1 General

Suitable sample size shall be achieved by one of the two methods described in [4.4.2](#) and [4.4.3](#).

4.4.2 Splitting by using a splitter

Pass the sample through the splitter (according to [3.2](#)), dividing it into two equal portions. Take one of these portions and by passing it through the splitter, divide it into two portions again. Repeat this procedure until a sample amount is obtained; this is 25 % larger than the amount required for testing.

4.4.3 Splitting by quartering manually

A sample can be quartered manually by mixing two of the opposite portions and reducing them again to quarters. Continue until a sample amount is obtained; this is 25 % larger than the amount finally required for testing.

4.5 Segregation

Sometimes segregation can be a problem. For materials, which are strongly segregating during transportation, above mentioned sampling procedure might not lead to a representative sample in all cases. Other methods have to be applied or developed (e.g. again homogenization followed by sampling or increase number of samples taken according to raster process, which have to be defined.)

Bibliography

- [1] ISO 3310-1, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*
- [2] ISO 6344-2, *Coated abrasives — Grain size analysis — Part 2: Determination of grain size distribution of macrogrits P12 to P220*
- [3] ISO 6344-3, *Coated abrasives — Grain size analysis — Part 3: Determination of grain size distribution of microgrits P240 to P2500*
- [4] ISO 9136-1, *Abrasive grains — Determination of bulk density — Part 1: Macrogrits*
- [5] ISO 9136-2, *Abrasive grains — Determination of bulk density — Part 2: Microgrits*
- [6] ISO 9284, *Abrasive grains — Test-sieving machines*
- [7] ISO 9285, *Abrasive grains and crude — Chemical analysis of fused aluminium oxide*
- [8] ISO 9286, *Abrasive grains and crude — Chemical analysis of silicon carbide*

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website-www.bis.gov.in or www.standardsbis.in.

This Indian Standard has been developed from Doc No.: PGD 09 (23616).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 th Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 th Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Manakalya, 4 th Floor, NTH Complex (W Sector), F-10, MIDC, Andheri (East), Mumbai 400093	{ 283 25838

Branches : AHMEDABAD, BENGALURU, BHOPAL, BHUBANESHWAR, CHANDIGARH, CHENNAI, COIMBATORE, DEHRADUN, DELHI, FARIDABAD, GHAZIABAD, GUWAHATI, HARYNA, HUBLI, HYDERABAD, JAIPUR, JAMMU & KASHMIR, JAMSHEDPUR, KOCHI, KOLKATA, LUCKNOW, MADURAI, MUMBAI, NAGPUR, NOIDA, PARWANOO, PATNA, PUNE, RAIPUR, RAJKOT, SURAT, VIJAYAWADA.