

पैकेजबंद प्राकृतिक मिनरल जल और
पैकेजबंद पेय जल के लिए एल्युमिनियम के
डिब्बे — विशिष्टि

Aluminium Cans for Packaged
Natural Mineral Water and Packaged
Drinking Water — Specification

ICS 55.120

© BIS 2023



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002
www.bis.gov.in www.standardsbis.in

FOREWORD

This Indian Standard was adopted by the Bureau of Indian Standards, after the draft finalized by the Metal Containers Sectional Committee had been approved by the Production and General Engineering Division Council.

Food Safety and Standards (Packaging) First Amendment Regulations, 2022 states that 'Provided further that food grade packaging materials as specified in regulation 4 (1) to (3), which may or may not contain plastic as component compatible with the water to be packaged may also be used. In such cases requirements of transparency would not apply.' This allows for the use of metal and metal alloys for the packaging of drinking water. In view of this, this standard has been formulated to cover the specification of aluminium cans which may be used for natural mineral water and packaged drinking water.

The requirements for two-piece aluminium cans for the packaging of alcoholic, non-alcoholic and dairy based beverages are covered in IS 14407 : 2023 'Aluminium Cans for Beverages — Specification (*first revision*)'.

The composition of the Committee responsible for formulation of this standard is given in Annex E.

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

Indian Standard

ALUMINIUM CANS FOR PACKAGED NATURAL MINERAL WATER AND PACKAGED DRINKING WATER — SPECIFICATION

1 SCOPE

This standard covers the specification for two-piece aluminium cans for the packaged natural mineral water (*see* IS 13428) and packaged drinking water (*see* IS 14543).

2 REFERENCES

The standards listed in Annex A contain provisions which, through reference in this text, constitute provisions of this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision and parties to agreements based on this standard are encouraged to investigate the possibility of applying the most recent editions of these standards.

3 TERMINOLOGY

For the purpose of this standard, the definitions given in IS 1394, IS 11104 and the following shall apply:

3.1 Brimful Capacity — The volume of fluid required to fill the bottle completely to brim level at $(27 \pm 2)^\circ\text{C}$.

3.2 Nominal Capacity — The volume of fluid

normally expected to be filled in the bottles at $(27 \pm 2)^\circ\text{C}$.

3.3 Traceability — The ability to follow the movement of a food article through specified stage(s) of its production, processing and distribution.

4 CAPACITY

Cans shall be of 150 ml, 185 ml, 200 ml, 250 ml, 300 ml, 330 ml, 355 ml, 450 ml, 500 ml, 550 ml, 750 ml and 1 000 ml capacity. In addition, cans may be of any capacity as agreed between the manufacturer and the purchaser.

5 MATERIAL

5.1 The can body stock shall be made from aluminium alloy of composition as given in Table 1A. The can end stock and can tab stock shall be made from aluminium alloy of composition as given in Table 1B. The test method for analysing the composition should be as per IS 504 (Part 1 to 12) and IS 504 (Part 13 to 16). Any other suitable instrumental/chemical method may also be used.

Table 1A Composition of Aluminium Alloy for Can Body Stock

(Clause 5.1)

Sl No.	Cu	Mg	Si	Fe	Mn	Zn	Ti	Cr	Ga	V	Others	Al
											Total	
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)
i)	0.05 - 0.25	0.8 - 1.3	0.6	0.8	0.8 - 1.4	0.25	0.1	—	0.05	0.05	0.15	Remainder

NOTE — Composition limits are in weight percent maximum, unless shown as a range or a minimum.

Table 1B Composition of Aluminium Alloy for Can End Stock (Shell) and Can Tab Stock

(Clause 5.1)

Sl No.	Cu	Mg	Si	Fe	Mn	Zn	Ti	Cr	Ga	V	Others	Al
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	Total	(13)
i)	0.15	4.0 - 5.0	0.2	0.35	0.2 - 0.5	0.25	0.1	0.1	—	—	0.15	Remainder

NOTE — Composition limits are in weight percent maximum, unless shown as a range or a minimum.

5.2 The temper of the aluminium alloy shall be as given in the table below (see Annex B for the temper designations).

Component	Temper
Body	H18 or H19
End	H48 or H49
Tab	H38, H39, H48 or H49

5.3 The mechanical properties of the alloys for the body and closure shall be as given in Table 2A and Table 2B, respectively.

Table 2A Mechanical Properties of Aluminium Alloy for Can Body

(Clause 5.3)

Sl No.	Temper	Tensile Test						Bend Test	
		Specified Thickness mm		Tensile Strength MPa		0.2% Proof Stress MPa		Elongation Min %	
		over	up to	Min	Max	Min	Max	A _{50mm}	A
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)
i)	H18	≥ 0.2	0.5	265	—	215	—	1	—
ii)	H19	≥ 0.2	0.5	275	—	—	—	1	—

Table 2B Mechanical Properties of Aluminium Alloy for Can Closure

(Clause 5.3)

Sl No.	Temper	Tensile Test							
		Specified Thickness mm		Tensile Strength MPa		0.2% Proof Stress MPa		Elongation Min %	
		over	up to	Min	Max	Min	Max	A _{50mm}	A
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)
i)	H18 or H38	≥ 0.2	0.5	345	—	—	—	1	—
ii)	H19 or H38	≥ 0.2	0.5	365	—	—	—	1	—

5.4 For the can body stock, there shall be lubrication applied to protect from post coil production oxidation.

6 REQUIREMENTS

6.1 Manufacture

6.1.1 Can Body

The can body shall be of seamless construction, that is manufactured using draw and ironing process.

6.1.2 Can Ends

6.1.2.1 The cans shall have leakproof and pilferproof closure system. The closure component 'Easy Open End (EOE)' may be used as the can end. Each EOE shall be made from two different pieces, shell and the tab. Can ends diameter shall be in sizes of 200, 202, 206 and 209.

NOTE — 202 stands for 2 inches + 02/16 of an inch. Other sizes shall be read accordingly.

6.1.2.2 The resealable can ends may be used as per agreed specifications between manufacturer and purchaser.

6.1.2.3 The closure components shall be lined with a suitable liner compound. The liner compound shall be non-toxic, compatible with the product packed and shall not impart off-flavour, off-odour, off-taste or loss of flavour. The position of the liner compound shall be in such a way that it does not get in contact with product filled inside.

6.2 Internal Finish

The internal surface of the can and the can end shall be suitably lacquered. Epoxy, polyester or acrylic water-based lacquers can be used for the coating. The coating shall not allow the beverage to come in contact with the metal surface. This can be achieved through applying sufficient amount of coating with respect to the type of aggressiveness of the product filled in.

6.3 External Coating

Each can body shall be applied with an external coating material. Polyester or acrylic water-based lacquer can be used for the coating. This shall be compatible with the suitable heat treatment meeting maximum time and temperature requirement of beverage filling process. Cans should be cured properly to avoid any mobility and scuffing issues. There are varieties of external finishes such as gloss, matt, tactile, etc, which may be used based on the agreement between the supplier and the customer.

Cans shall have a bottom coating at its rim, to facilitate easy movement of empty can on conveyers.

6.4 Shape and Dimensions

6.4.1 The shape and nominal dimensions of the cans shall be as given in Table 3. Cans of capacity other than those mentioned in Table 3 may be of shape and dimensions as agreed between the manufacturer and the purchaser. For cans of any capacity, the minimum wall thickness should be 50 µm.

6.4.2 The shape and nominal dimensions of the closure components for cans shall be as given in Table 4.

7 TESTS

7.1 Testing of Cans

7.1.1 Top Load /Axial Load /Column Strength

Empty can shall have a minimum axial load of 675 N. Top load shall be applied uniformly on the top of the can at a constant rate of 13 mm per minute.

7.1.2 Enamel Rater Criteria

The average enamel rater reading for a sample of minimum 24 cans shall not exceed 5 mA and no individual reading shall exceed 25 mA.

7.1.3 Air Pressure Test

The cans shall be subjected to air pressure of 620 kPa for a period of 15 s as per the test method described in IS 2471. The cans shall show no leakage when immersed in water.

7.1.4 Slip Angle Test/Wall Mobility Test

The slip angle should be not more than 20° (0.1 µ coefficient of friction) for gloss over varnish when tested as per methods described in Annex B. For another speciality over varnish, slip angle should be as agreed between the customer and the supplier.

7.2 Testing of Ends

The force required to achieve venting shall not exceed 35.6 N force for a can end, and the average of a lot shall be less than 28.9 N force, when measured using a can end opening performance testing gauge.


7.3 Migration Tests

7.3.1 Overall Migration Limit

All cans shall have overall migration limit of 60 mg/kg or 10 mg/dm² when tested as per IS 9845 with no visible colour migration.

Table 3 Dimensions of Aluminium Beverage Cans

(Clause 6.4.1)

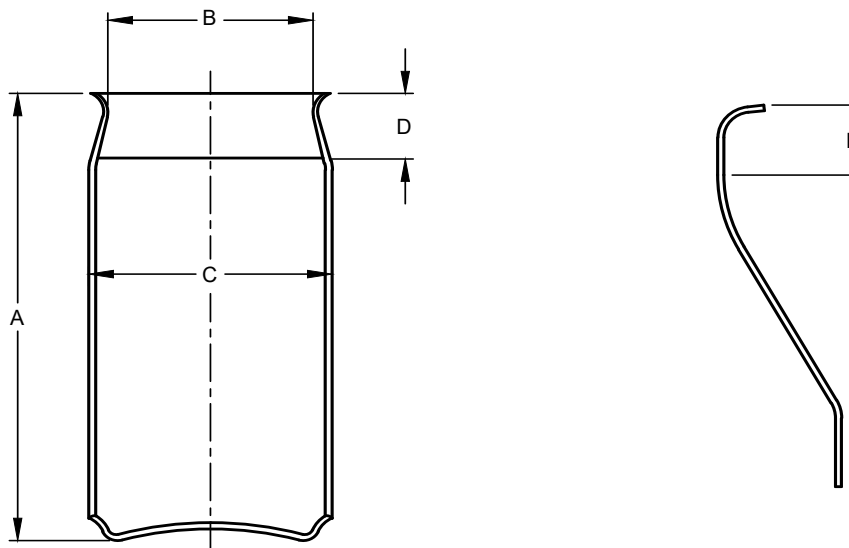

CROSS SECTIONAL VIEW OF CAN BODY


CROSS SECTIONAL VIEW OF NECK

SI No.	Nominal Capacity ml	Can Type ¹⁾	Dimensions					Brimful Capacity ml
			Finished Can Height, <i>A</i> mm	Inside Neck/Plug Diameter, <i>B</i> mm	Outside Can Diameter, <i>C</i> mm	Free Board, <i>D</i> mm	Neck Seaming Clearance, <i>E</i> mm	
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)
i)	150	Slim	88.50	50.00	53.6	14.10	3.05	180.00
ii)	185	Slim	103.38	50.00	53.6	14.10	3.05	211.00
iii)	250	Slim	134.00	50.00	53.4	14.10	3.05	278.00
iv)	250	Stubby	91.49	52.40	66.6	11.90	3.05	276.00
v)	200	Fit	95.20	50.0 or 52.4	58.1	13.50	3.05	228.50
vi)	300	Fit	133.89	50.0 or 52.4	58.1	13.50	3.05	328.50
vii)	330	Fit	145.40	50.0 or 52.4	58.1	13.50	3.05	358.00
viii)	355	Fit	156.60	50.0 or 52.4	58.1	15.00	3.05	388.00
ix)	330	Standard	115.20	52.40	66.6	12.00	3.05	358.00
x)	355	Standard	122.20	52.40	66.6	11.90	3.05	382.00
xi)	500	Standard	168.00	52.40	66.6	14.50	3.05	533.50
xii)	450	Standard	168.00	52.40	63.8	16.50	3.05	493.00
xiii)	750	Jumbo	160.00	62.56	84.7	14.00	3.05	798.00
xiv)	1 000	Jumbo	204.80	62.56	84.7	13.00	3.05	1046.00

¹⁾ Jumbo, standard, stubby, sleek, fit and slim are the can size names based on 3 variables, that is, finished can height, outer can diameter and the neck diameter to differentiate from each other.

Table 4 Dimensions for Can Ends

(Clause 6.4.2)

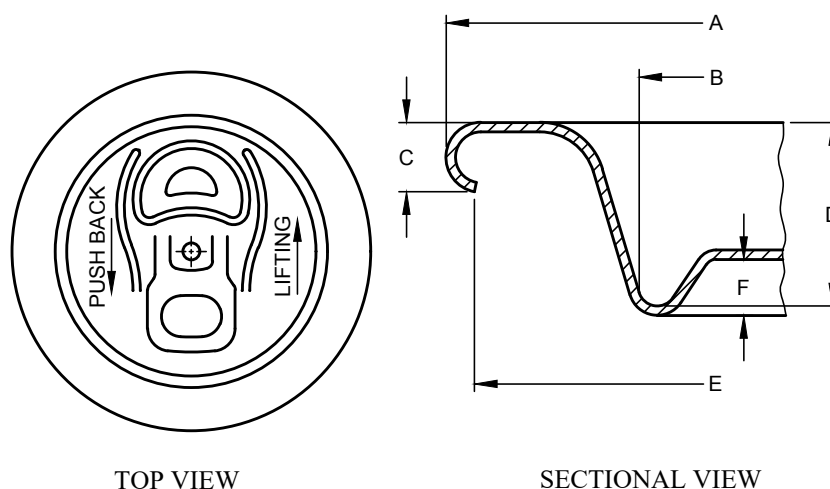

Sl No.	Can End Size	Can End Type ²⁾	Dimensions					Panel Height, F ¹⁾
			Outside Curl Diameter, A	Punch Plug Diameter, B ¹⁾	Curl Height, C	Inside Curl Diameter, E	Countersink Depth, D	
			mm	mm	mm	mm	mm	mm
			± 0.25	—	± 0.15	Min	± 0.15	—
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)
i)	200	B64	57.15	46.46	2.08	55.45	6.73	2.24
ii)	202	B64	59.41	48.59	2.08	57.66	6.86	2.44
iii)	206	B64	64.82	54.62	2.11	62.71	6.5	2.21
iv)	209	B64	69.6	62.56	2.21	67.92	6.86	1.91
v)	200	CDL	56.9	45.03	2.07	55.25	6.35	2.04
vi)	202	CDL	59.3	47.42	2.07	57.66	6.35	2.04
vii)	202	ISE	59.29	47.12	2.03	57.66	6.17	2.13

¹⁾ This dimension is given for reference only.

²⁾ B64, CDL and ISE are the reference names for specific design type for the can ends.

7.3.2 Specific Migration Limit

The specific migration shall not exceed the maximum limit given in Table 5. The sample for the specific migration test shall be prepared as per IS 9845 wherein the lacquer would be exposed to the simulants. The extracted simulants shall be then

detected for elements given in SI No. 1 to 8 of Table 5 in accordance with the test method specified in IS 3025 (Part 2) or IS 3025 (Part 65). DEHP shall be measured as per the method specified in ISO 18856.

7.4 Water Potability Test

Packaged natural mineral water or packaged drinking water stored in cans for 30 days, shall not acquire any unpleasant odour or bitter taste when tested according to the method prescribed in Annex C.

8 SAMPLING

The representative samples of cans for attributed defects and tests shall be drawn as prescribed in IS 2500 (Part 1).

9 MARKING

9.1 Each can body and can end shall be marked with

the following particulars:

- a) Indication of the source of manufacture;
- b) Date of manufacture and lot number so as to facilitate complete traceability; and
- c) Any other information as required by the purchaser.

9.2 BIS Certification Marking

The product(s) conforming to the requirements of this standard may be certified as per the conformity assessment schemes under the provisions of the *Bureau of Indian Standards Act, 2016* and the Rules and Regulations framed there under, and the product(s) may be marked with the Standard Mark.

Table 5 Specific Migration Limits

(Clause 7.3.2)

Sl No.	Substances	Maximum Migration Limit mg/kg
(1)	(2)	(3)
i)	Barium	1
ii)	Cobalt	0.05
iii)	Copper	5.0
iv)	Iron	48.0
v)	Lithium	0.6
vi)	Manganese	0.6
vii)	Zinc	25
viii)	Antimony	0.04
ix)	Phthalic acid, bis(2- ethylhexyl)ester (DEHP)	1.5

ANNEX A

(Clause 2)

LIST OF REFERRED STANDARDS

<i>IS No./Other Publications</i>	<i>Title</i>	<i>IS No./Other Publications</i>	<i>Title</i>
IS 504 (Part 1 to 12) : 2002	Chemical analysis of aluminium and its alloys (Parts 1 to 12) (<i>second revision</i>)	IS 3025 (Part 65) : 2022/ISO 17294-2 : 2016	Methods of sampling and test (physical and chemical) for water and wastewater: Part 65 Application of inductively coupled plasma mass spectrometry (ICP-MS) — Determination of selected elements including uranium isotopes (<i>first revision</i>)
IS 504 (Part 13 to 16) : 2003	Chemical analysis of aluminium and its alloys (Parts 13 to 16) (<i>second revision</i>)	IS 9845 : 1998	Determination of overall migration of constituents of plastics materials and articles intended to come in contact with foodstuffs — Method of analysis (<i>second revision</i>)
IS 1394 : 1984	Glossary of terms relating to metal containers (<i>third revision</i>)	IS 11104 : 2012	Glossary of terms relating to open top sanitary cans
IS 2471 : 1963	Methods of tests for metal containers	IS 13428 : 2005	Packaged natural mineral water — Specification (<i>second revision</i>)
IS 2500 (Part 1) : 2000/ISO 2859-1 : 1999	Sampling procedures for inspection by attributes: Part 1 Sampling schemes indexed by acceptance quality limit (AQL) for lot-by-lot inspection (<i>third revision</i>)	IS 14543 : 2016	Packaged drinking water (other than packaged natural mineral water) — Specification (<i>second revision</i>)
IS 3025 (Part 2) : 2019/ISO 11885 : 2007	Methods of sampling and test (physical and chemical) for water and wastewater: Part 2 Determination of selected elements by inductively coupled plasma optical emission spectrometry (ICP-OES) (<i>first revision</i>)	ISO 18856 : 2004	Water quality — Determination of selected phthalates using gas chromatography/mass spectrometry
IS 3025 (Part 5) : 2018	Methods of sampling and test (physical and chemical) for water and waste water: Part 5 Odour (<i>second revision</i>)		
IS 3025 (Part 8) : 1984	Methods of sampling and test (physical and chemical) for water and waste water: Part 8 Taste rating (<i>first revision</i>)		

ANNEX B

(Clause 5.2)

TEMPER DESIGNATIONS

B-1 H TEMPER DESIGNATION

H temper designation (strain-hardened) applies to products subjected to the application of cold work after annealing (or after hot forming), or to a combination of cold work and partial annealing or stabilizing, in order to achieve the specified mechanical properties. The letter H is always followed by two digits, the first indicating the specific combination of basic operations and the second indicating the degree of strain hardening.

B-2 SUBDIVISIONS OF H TEMPER DESIGNATION**B-2.1 First Digit After H**

The first digit following the letter H indicates the specific combination of basic operations as follows:

- a) *H1X Strain-hardened only* — These designations apply to products that are strain-hardened to obtain the desired strength without supplementary thermal treatment.
- b) *H2X Strain-hardened and partially annealed* — These designations apply to products that are strain-hardened more than the desired final amount and then reduced in strength to the desired level by partial annealing. For alloys that age-soften at room temperature, the H2X tempers have the same minimum ultimate tensile strength as the corresponding H3X tempers. For other alloys, the H2X tempers have the same minimum ultimate tensile strength as the corresponding H1X tempers and slightly higher elongation.
- c) *H3X Strain-hardened and stabilized* — These designations apply to products that are strain-hardened and whose mechanical properties are stabilized either by a low temperature thermal treatment or as a result of heat introduced during fabrication. Stabilization usually improves ductility. This designation is applicable only to those alloys which, unless stabilized, gradually age-soften at room temperature.
- d) *H4X Strain-hardened and lacquered or painted* — These designations apply to products that are strain-hardened and which are subjected to some thermal operation during the subsequent painting or lacquering operation.

B-2.2 Second Digit After H

The second digit following the letter H indicates the final degree of strain hardening, as identified by the minimum value of the ultimate tensile strength.

- a) 8 has been assigned to the hardest tempers normally produced. The minimum tensile strength of tempers HX8 may be determined from Table 6 and is based on the minimum tensile strength of the alloy in the annealed temper.
- b) Tempers between O (annealed) and HX8 are designated by numerals 1 to 7:
 - 1) HX4 designates tempers whose ultimate tensile strength is approximately midway between that of the O temper and that of the HX8 tempers;
 - 2) HX2 designates tempers whose ultimate tensile strength is approximately midway between that of the O temper and that of the HX4 tempers;
 - 3) HX6 designates tempers whose ultimate tensile strength is approximately midway between that of the HX4 tempers and that of the HX8 tempers; and
 - 4) HX1, HX3, HX5 and HX7 designate tempers intermediate between those defined above.

The ultimate tensile strength of the odd numbered intermediate (-HX1, -HX3, -HX5 and -HX7) tempers, determined as described above, shall be rounded to the nearest multiple of 5 MPa.

- c) HX9 designates tempers whose minimum ultimate tensile strength exceeds that of the HX8 tempers by 10 MPa or more.

Table 6 Determination of HX8 Minimum Tensile Strength*(Clause B-2.2)*

SI No.	Minimum Tensile Strength in Annealed Temper	Increase in Tensile Strength to HX8 Temper
(1)	MPa (2)	MPa (3)
i)	up to 40	55
ii)	45 - 60	65
iii)	65 - 80	75
iv)	85 -100	85
v)	105 -120	90
vi)	125 -160	95
vii)	165 - 200	100
viii)	205 - 240	105
ix)	245 - 280	110
x)	285 - 320	115
xi)	325 and over	120

ANNEX C

(Clause 7.1.4)

METHOD OF TEST FOR SIDE WALL MOBILITY

C-1 Side wall mobility of the beverage aluminium can is important to ensure that the cans move smoothly at the customer filling line, track works etc. This can be measured by using either tilt table or through mobility testing unit.

C-2 USING TILT TABLE

C-2.1 Procedure

Place the can to be tested on top of two other cans placed on a tilt table and allow the equipment to start. The angle at which the test can slides, stop the equipment and take the reading to measure the surface smoothness for the mobility.

C-2.2 Observation

At the end of the test record the reading in the dial gauge marked in degrees. It should be less than

20° to say that the cans will run smoothly.

C-3 USING MOBILITY TESTER

C-3.1 Procedure

Place the test sled on the can sample and connect the sled hook to the eye on the force gauge. Place the fixture mounted 'speed control' to the '5' position. Move the test switch to the 'Test' position. The gauge will drag the testing sled across the sample and the coefficient of friction can be read directly from the force gauge dial indicator. At the end of the test carriage remove the test sled.

C-3.2 Observation

At the end of the test, record the reading in the dial gauge marked in coefficient of friction. It should be less than 0.1 μ to say that the cans will run smoothly.

ANNEX D*(Clause 7.4)***METHOD OF TEST FOR POTABILITY****D-1 GENERAL**

D-1.1 Odour of water, though very important, cannot be determined in absolute units. Olfactory sense, which is most sensitive means of detecting small concentration of odoriferous substances is universally adopted in such cases.

D-1.2 Natural mineral water or packaged drinking water for testing shall be clear and fresh.

D-2 PROCEDURE

Heat the water to a temperature of (38 ± 2) °C, and

fill the container to its nominal capacity and close tightly. Keep the container at (38 ± 2) °C, for a period of 30 days. The containers shall be opened after 30 days of storage period and the water shall be examined for any disagreeable odour or taste.

D-3 OBSERVATIONS

At the end of the 30 days, the water shall not give any unpleasant odour or taste, when tested as per IS 3025 (Part 5) and IS 3025 (Part 8), respectively.

ANNEX E

(Foreword)

COMMITTEE COMPOSITION

Metal Containers Sectional Committee, PGD 38

<i>Organization</i>	<i>Representative(s)</i>
In Personal Capacity (Flat No. P04, IVY Tower, Nahar Amrit Shakti, Chandivali, Powai, Mumbai — 400072)	DR N. C. SAHA (Chairperson)
Ace Cans Manufacturing Company, Mumbai	SHRI KANAK RAJ PARMAR SHRI DINESH PARMAR (<i>Alternate</i>)
Akzo Nobel India Limited, Gurugram	SHRI MANOJ KUMAR SHARMA SHRI SWAPAN KUMAR BHANDARI (<i>Alternate</i>)
Asian Paints Limited, Mumbai	SHRI NAVNINDER SINGH MS SHWETA TIWARI (<i>Alternate</i>)
Ball Beverage Packaging (India) Private Limited, Bengaluru	SHRI GANESH NETHA
Balmer Lawrie and Company Limited, Mumbai	SHRI R. S. PATEL SHRI AMIT MITRA (<i>Alternate</i>)
Balmer Lawrie-Van Leer Limited, Mumbai	SHRI TUSHAR SHIRWALKAR
Blossom Industries Limited, Daman	SHRI RAJ KUMAR SHARMA
Canpack India Private Limited, Aurangabad	SHRI SWAPNIL KHESE SHRI AKSHAY SUDAME (<i>Alternate</i>)
Caps and Containers, Mumbai	SHRI O. P. AGARWAL MS MANISHA AGARWAL (<i>Alternate</i>)
Cargill India Private Limited, Gurugram	SHRI SEKHAR PAL MS NEHA PARASHAR (<i>Alternate</i>)
Central Insecticide Laboratory, Faridabad	DR J. P. SINGH DR BRIJESH TRIPATHI (<i>Alternate</i>)
Chemco Plastic Industries Private Limited, Mumbai	SHRI GAURAV SARAOGI MS RUPANDE SAMPAT (<i>Alternate</i>)
Coca-Cola India Private Limited, Gurugram	SHRI VIRENDRA LANDGE MS NISHTHA CHAUHAN (<i>Alternate</i>)
Dharampal Satyapal Group, Noida	SHRI SANJAY GUPTA
Directorate General of Quality Assurance, CQA (GS), Kanpur	SHRI M. SATYANARAYANA SHRI BANMALI BEHRA (<i>Alternate</i>)
Hindustan Petroleum Corporation Limited, Mumbai	SHRI RAVI KUMAR SHRI SUNIL SHANKAR PATIL (<i>Alternate</i>)
Hindustan Tin Works Limited, New Delhi	SHRI GAJENDRA SINGH SHRI R. K. TYAGI (<i>Alternate</i>)
Indian Institute of Packaging, Delhi	PROF TANVEER ALAM SHRI MADHAB CHAKRABORTY (<i>Alternate</i>)

<i>Organization</i>	<i>Representative(s)</i>
Indian Oil Corporation Limited, Mumbai	SHRI S. MARIMUTHU SHRI S. SHRIDHAR (<i>Alternate</i>)
JSW Steel Coated Products Limited, Mumbai	SHRI ABHIJIT CHIVANE SHRI CHANCHAL KUMAR KARMAKAR (<i>Alternate</i>)
Kaira Can Company Limited, Mumbai	SHRI K. M. SHENOY SHRI SURESH PANCHAL (<i>Alternate</i>)
Ministry of Consumer Affairs, Food and Public Distribution, New Delhi	SHRI B. N. DIXIT
Nestle India Limited, Gurugram	SHRI BISWAJIT BASU SHRI BARUN BANERJEE (<i>Alternate</i>)
PPG Asian Paints Private Limited, Mumbai	SHRI SANJAY GHEMAD
Recon Machine Tools Private Limited, Mumbai	SHRI P. A. PAI SHRI ASHWIN PAI (<i>Alternate</i>)
Shetron Limited, Bengaluru	SHRI KARTIK NAYAK SHRI NITHIN KUMAR SHETTY (<i>Alternate</i>)
The Tinsplate Company of India Limited, Jamshedpur	DR SOURAJYOTI DEY SHRI BABLU KUMAR SINGH (<i>Alternate</i>)
Valspar (India) Coatings Corporation Private Limited, Bengaluru	SHRI RAJAT BHATTACHARJEE SHRI SANJAY TYAGI (<i>Alternate</i>)
BIS Directorate General	SHRI R. R. SINGH, SCIENTIST 'F'/SENIOR DIRECTOR AND HEAD (PRODUCTION AND GENERAL ENGINEERING) [REPRESENTING DIRECTOR GENERAL (<i>Ex-officio</i>)]

Member Secretary
SHRI KRISHNA SUDHEENDRAN
SCIENTIST 'C'/DEPUTY DIRECTOR
(PRODUCTION AND GENERAL ENGINEERING), BIS

Panel for Aluminium Container for Beverages, PGD 38/P2

<i>Organization</i>	<i>Representative</i>
Coca-Cola India Private Limited, Gurugram	SHRI VIRENDRA LANDGE (Convenor)
Akzo Nobel India Limited, Gurugram	SHRI SWAPAN KUMAR BHANDARI
Ball Beverage Packaging (India) Private Limited, Bengaluru	SHRI GANESH NETHA
Blossom Industries Limited, Daman	SHRI RAJ KUMAR SHARMA
Canpack India Private Limited, Aurangabad	SHRI SWAPNIL KHESE
Coca-Cola India Private Limited, Gurugram	MS NISHTHA CHAUHAN
Hindalco Industries Limited, Mumbai	SHRI GAURAV MAHAJAN
Nestle India Limited, Gurugram	SHRI BISWAJIT BASU
PPG Asian Paints Private Limited, Mumbai	SHRI VISHAL GANDHI
Valspar (India) Coatings Corporation Private Limited, Bengaluru	SHRI MANISH NARAIN

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website- www.bis.gov.in or www.standardsbis.in.

This Indian Standard has been developed from Doc No.: PGD 38 (20182).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002
Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 th Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 th Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Plot No. E-9, Road No.-8, MIDC, Andheri (East), Mumbai 400093	{ 2821 8093

Branches : AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. CHANDIGARH. CHENNAI. COIMBATORE. DEHRADUN. DELHI. FARIDABAD. GHAZIABAD. GUWAHATI. HIMACHAL PRADESH. HUBLI. HYDERABAD. JAIPUR. JAMMU & KASHMIR. JAMSHEDPUR. KOCHI. KOLKATA. LUCKNOW. MADURAI. MUMBAI. NAGPUR. NOIDA. PANIPAT. PATNA. PUNE. RAIPUR. RAJKOT. SURAT. VISAKHAPATNAM.