

BUREAU OF INDIAN STANDARDS

Draft Indian Standard

**METHODS OF TEST FOR PETROLEUM AND ITS PRODUCTS PART
DETERMINATION OF THE LEAKAGE TENDENCIES OF AUTOMOTIVE
WHEEL BEARING GREASES**

ICS 75.100

Not to be reproduced without permission of BIS

Last date for receipt of comment is
06 January 2022

FOREWORD

(Formal clause shall be added later)

Evaporation loss is an important quality criterion. When volatile components of the base oil evaporate, there are changes in the viscosity and lubrication behaviour of the oil.

In the formulation of this draft standard, assistance has been derived from ASTM D1263-94 'Leakage tendencies of automotive wheel bearing greases'

This draft standard is one of the series of Indian Standards on 'Methods of test for petroleum and its products' IS 1448.

In reporting the result of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 1960 'Rules for rounding off numerical values (*revised*)'.

1 SCOPE

1.1 This draft test method describes the assessment of the leakage tendencies of wheel bearing greases when tested under prescribed laboratory conditions.

WARNING — This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

2 TERMINOLOGY

2.1 Lubricating Grease — A semi-fluid to solid product of a dispersion of a thickener in a liquid lubricant.

2.1.1 A two-phase system is formed by the dispersion of thickener, immobilizing the liquid lubricant, due to surface tension and other physical forces. Other ingredients are added to get other special properties.

2.2 Lubricant

Any material, which when interposed in between two surfaces, lowers down the friction or wear between them.

2.3 Thickener

In lubricating grease, a substance used to form the structure of product, composed of finely-divided particles dispersed in a liquid lubricant.

2.3.1 The solid thickener can be spheres (such as certain non-soap thickeners) or fibers (such as various metallic soaps) or plates. The solid particles are insoluble or, at the most, only very slightly soluble in the liquid lubricant. Solid particles should generally be uniformly dispersed, extremely small, and capable of forming a gel-like, relatively stable structure with the liquid lubricant.

2.4 Automotive Wheel Bearing Grease

A lubricating grease categorically created formed to lubricate automotive wheel bearings at relatively high temperature of grease and bearing speed.

2.5 Leakage of Wheel Bearing Grease

Segregation and overflow of oil or grease from the bulk grease charge, activated by high temperature and bearing rotation.

3 PRINCIPLE

3.1 The grease is distributed in a modified front-wheel hub and spindle assembly. Spindle temperature is raised to and maintained at $105 \pm 1.2^\circ\text{C}$. The hub is rotated at a speed of 660 ± 30 rpm for $6 \text{ h} \pm 5$ min. Leakage of oil or grease, or both, is measured, and at the end of the test, the condition of the bearing surface is noted.

3.2 A screening device is provided by the test method that allows differentiation among products of distinctly different leakage characteristics. This test method is not equivalent to longtime service tests and it is also not aimed at distinguishing between wheel bearing greases showing similar or borderline leakage.

NOTE — Skilled operators may observe significant changes in other important grease characteristics that occur during the test. Such additional information can be of special interest to individual operators. The observations, however, cannot be used effectively for quantitative rating, as these are subject to differences in personal judgment among operators.

4 APPARATUS


4.1 The suitable apparatus is shown in Fig. 1 and Fig. 2. The tester has a special front wheel hub and spindle assembly and the hub is rotated by an electric motor using a V-belt drive. The assembly is encased in a thermostatically controlled air bath. There are means to measure both ambient (cabinet) and spindle temperatures. A torque wrench is also required, which is suitable for use on 31.75 mm hexagonal nuts.

4.2 The apparatus (spindle, case, and motor) must be electrically grounded, otherwise the thermocouples will not function due to accumulated static charges. Provision is made for this, as shown in Fig. 2.

4.3 Usually machine having 660 W heaters will provide sufficient heat input to attain the temperatures in the specified time intervals. However, if proper balance cannot be obtained, heaters with required wattage can be substituted.




FIG. 1 APPARATUS FOR TESTING LEAKAGE TENDENCIES OF WHEEL BEARING GREASES

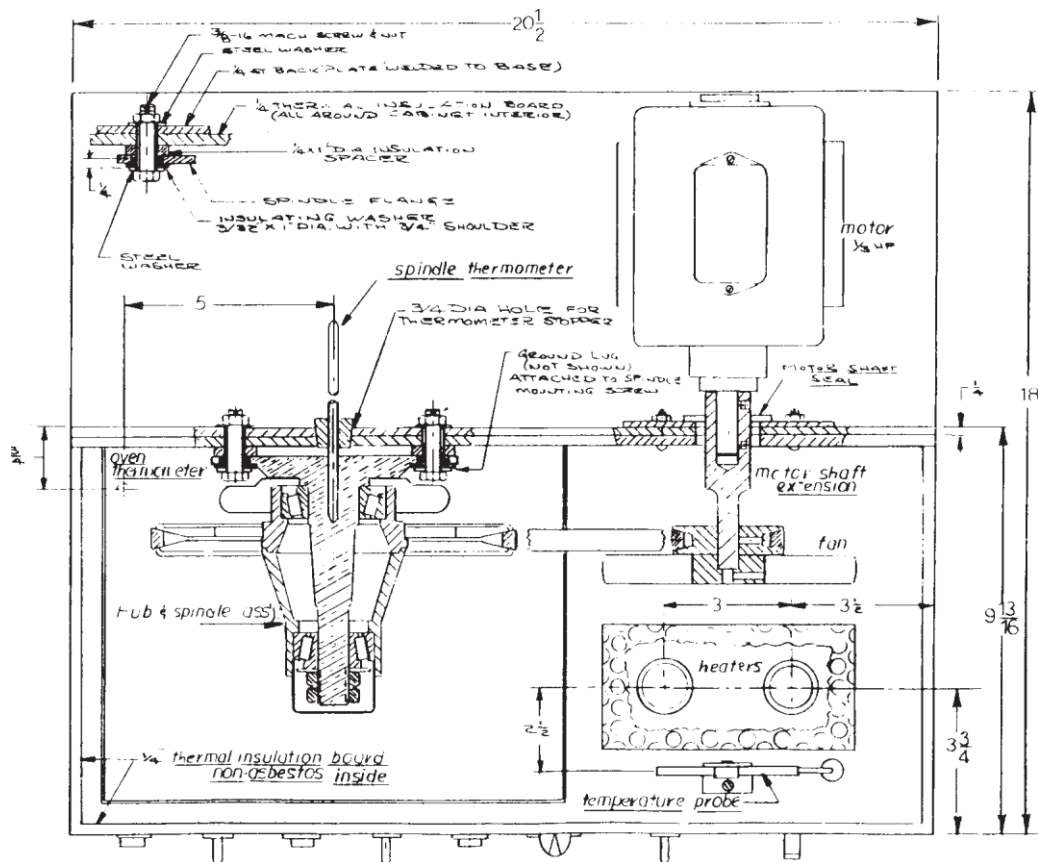

All dimensions in inch

FIG. 2A DETAILS OF MAIN ASSEMBLY

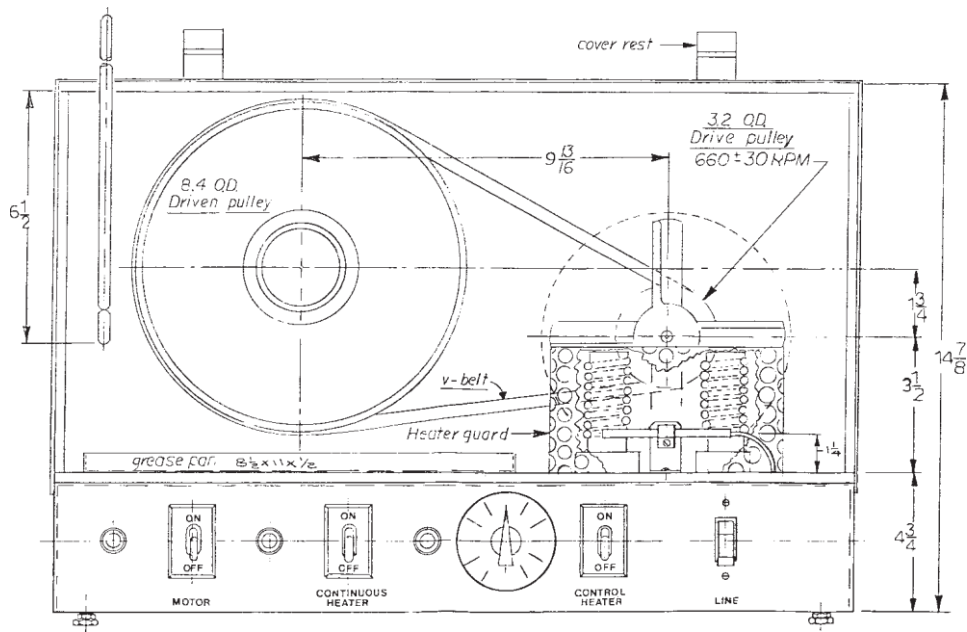

All dimensions in inch

FIG. 2B DETAILS OF MAIN ASSEMBLY

4.4 Main Assembly

The main assembly shall consist of spindle assembly mounted in a thermostatically controlled air bath and a special front-wheel hub. The assembly is arranged so that the hub will be rotated by an electric motor through a V-belt drive, as shown in Fig. 2. One continuous and one intermittent heater shall be mounted on the base of the apparatus and shall be controlled thermostatically.

4.5 Bearing Spindle

The spindle shall be constructed as shown in Fig. 3.

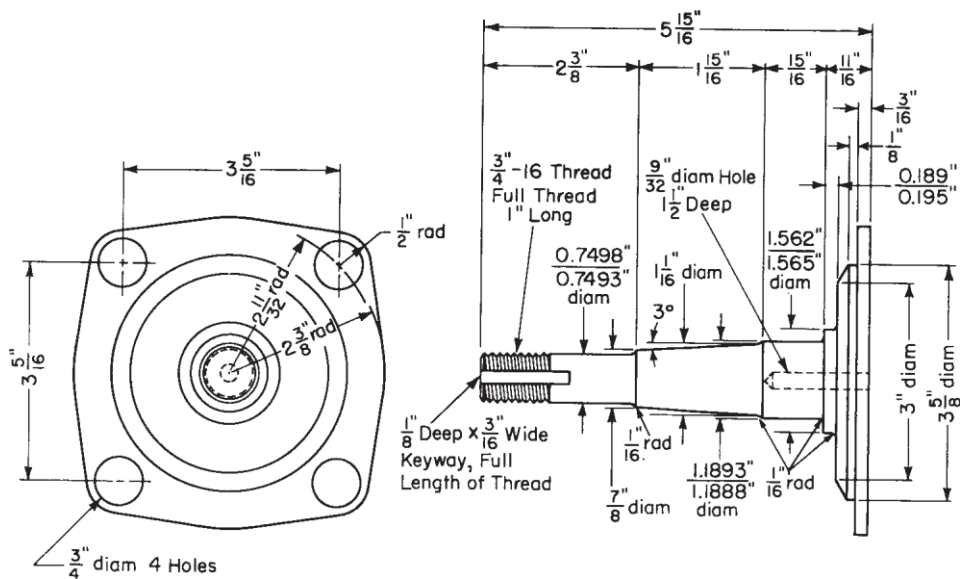


FIG. 3 DETAILS OF MAIN SPINDLE

4.6 Bearing Hub

The bearing hub shall be constructed as shown in Fig. 4.

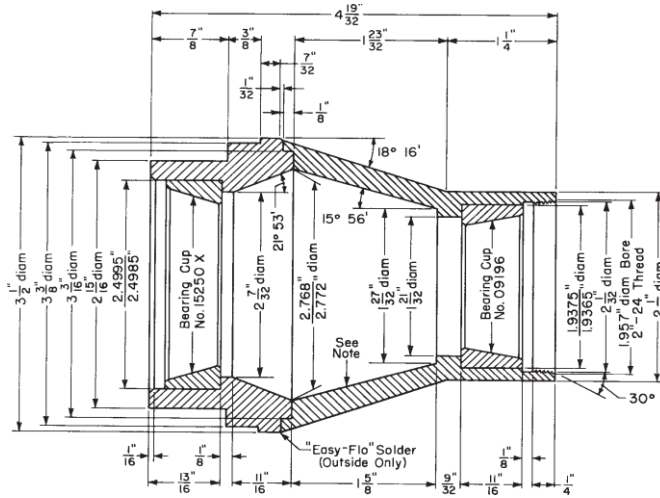


FIG. 4 DETAILS OF BEARING HUB

4.7 Leakage Collector

A cup-shaped ring shall be used as a leakage collector to catch any leaked grease from the inner end of the hub, as shown in Fig. 5. The ring shall be removable providing a method for determining the grease loss. The ring is held in place by the large bearing.

NOTE — The regular grease retainer is not suitable for this purpose, as it is required to accelerate any leakage that may occur. Also retainers are frequently found to be defective.

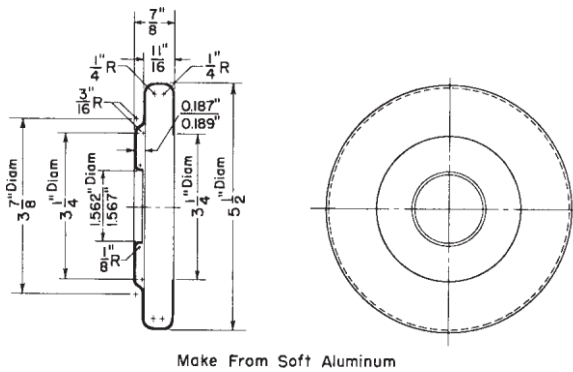


FIG. 5 DETAILS OF GREASE COLLECTOR

4.8 Fan

The fan shall be constructed as shown in Fig. 6.

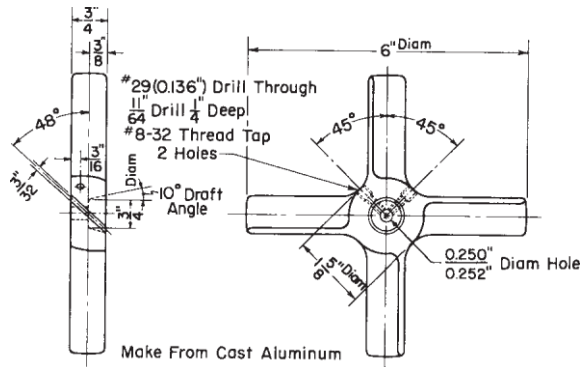


FIG. 6 DETAILS OF FAN

NOTE — Polish inside tapered surfaces with waterproof paper. Do not round off sharp corners when polishing. Make both parts of hub assembly from 3.5 inch round cold drawn steel rod.

4.9 Test Bearings

4.9.1 *Inner Bearing (Tapered Roller)* — Timken 15118. The corresponding cup No. 15250.

4.9.2 *Smaller Outer Bearing* — Timken 09074. The corresponding cup No. 09196.

5 REAGENT

5.1 **Heptane** — 99.87 percent purity.

WARNING — Flammable. Harmful if inhaled.

6 PROCEDURE

6.1 Weigh 90 ± 1 g of sample on a flat plate. Pack 2 ± 0.1 g of grease in the small bearing using a spatula. Similarly, pack 3 ± 0.1 g of grease in the large bearing.

6.2 On the inside of the hub, distribute the balance of the test grease (85 g) in a uniform layer. Apply a thin film of grease to the bearing races in the hub.

NOTES

1 A narrow, wedge-cut spatula is suitable for packing the bearings.

2 Rest of the grease will fill the hub sufficiently, even with the races and except for very fibrous greases, it can be distributed quickly and uniformly with a spatula of 150 mm blade.

6.3 Weigh the leakage collector and the hub cap to the nearest 0.1 g separately. Put the large (inner) bearing and leakage collector in the proper position on the spindle. Put small (outer) bearing and the hub and on the spindle, followed by the loose-fitting retainer ring. Tighten the hexagonal nut which holds the hub assembly in place, applying a torque of 6.8 ± 0.1 N·m using the torque wrench. Then back off the hexagonal nut $60 \pm 5^\circ$ (or one flat), and lock it in position with a second hexagonal nut. Put screws on the hub cap and V-belt on the pulleys, and close the cabinet.

Caution — Inspect all the grease collectors carefully to make sure that the inner lip is flush with the sealing face. Otherwise, this lip will interfere with the correct seating of the inner bearing.

Caution — Prevent contact between grease pack and spindle, while assembling the packed hub on the spindle.

Caution — From time to time, the drive pulley and the driven pulley should be checked for alignment. Misalignment can introduce leakage variations.

NOTE — Excessive end play of the hub assembly is sometimes due to worn bearings. Therefore new bearings, both cups and cones, should be installed after each 250 tests, or sooner if inspection indicates wear or other damage to the bearings.

6.4 Close the cabinet and turn on both the heaters and motor. Operate at a speed of 660 ± 30 rpm for $6 \text{ h} \pm 5$ min. The spindle temperature to be raised to and then maintained at $105 \pm 1.4^\circ\text{C}$ during the test period. Maintain the ambient temperature at $115 \pm 3^\circ\text{C}$ to obtain the spindle temperature of $105 \pm 1.4^\circ\text{C}$. Keep the auxiliary heater on till an ambient or oven temperature of 115°C is attained. Keep the thermoregulator previously adjusted to maintain oven temperature of 115°C , or to have a reproducible setting for this temperature. The ambient temperature of $115 \pm 3^\circ\text{C}$ shall be attained within 15 ± 5 min. The spindle temperature of $105 \pm 1.4^\circ\text{C}$ shall be attained within 60 ± 10 min. These two combining result in the spindle maintaining at $105 \pm 1.4^\circ\text{C}$ for $5 \text{ h} \pm 15$ min.

Caution — Rate of heating can be affected by drafts. Therefore, location of the tester should be carefully chosen.

6.5 Shut off the power after 6 h from the time motor and heater are turned on and dismantle the apparatus while hot. Wear appropriate protective clothing while handling the hot equipment.

6.6 Let the apparatus cool and measure the weight of the hub cap and leakage collector separately to the nearest 0.1 g.

NOTE — In case of overflow from leakage collector, the amount of overflow grease or oil, or both, should be weighed and included in the reported total leakage.

6.7 Wash the two bearings in heptane, at room temperature for at least 2 min, to remove the grease. Inspect for varnish, gum, or lacquer-like deposits.

NOTE — In case of some wheel bearing greases, it will be found that the soaps are not completely washed from the bearings with *n*-heptane and film of soap may remain on the bearings. However, such film can be easily distinguished from varnish, gum, or lacquer-like deposits resulting from deterioration of the lubricant.

7 REPORT

7.1 Report the total amount of leakage of grease or oil, or both, into the collector and into the hub cap. Report the presence of any adherent deposit of varnish, gum, or lacquer-like material on the bearing surface, which is evident after removal of the grease.

8 PRECISION AND BIAS

8.1 Repeatability

The difference between two test results, obtained by the same operator with the same apparatus under constant operating conditions on identical test material, would in the long run, in the normal and correct operation of the test method, exceed the following values only in one case in twenty:

Leakage in Area of	Acceptable Difference
2 g	1.5 g
15 to 20 g	9 g

8.2 Reproducibility

The difference between two single and independent results obtained by different operators working in different laboratories on identical test material would, in the long run, in the normal and correct operation of the test method, exceed the following values only in one case in twenty:

Leakage in Area of	Acceptable Difference
2 g	4 g
15 to 20 g	9 g

8.3 Bias

The procedure in this test method for measuring leakage tendencies of automotive wheel bearing greases has no bias because the value of leakage can be defined only in terms of a test method.